



**HAL**  
open science

## Calcium hydrazinidoborane: Synthesis, characterization, and promises for hydrogen storage

Salem Ould-Amara, Vibhav Yadav, Eddy Petit, Guillaume Maurin, Pascal Yot, Umit Demirci

### ► To cite this version:

Salem Ould-Amara, Vibhav Yadav, Eddy Petit, Guillaume Maurin, Pascal Yot, et al.. Calcium hydrazinidoborane: Synthesis, characterization, and promises for hydrogen storage. *International Journal of Hydrogen Energy*, 2020, 45 (3), pp.2022-2033. 10.1016/j.ijhydene.2019.10.213 . hal-02494011

**HAL Id: hal-02494011**

**<https://hal.umontpellier.fr/hal-02494011>**

Submitted on 21 Jul 2022

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution - NonCommercial 4.0 International License

# Calcium hydrazinidoborane: synthesis, characterization, and promises for hydrogen storage

Salem OULD-AMARA,<sup>1</sup> Vibhav YADAV,<sup>2</sup> Eddy PETIT,<sup>1</sup> Guillaume MAURIN,<sup>2</sup> Pascal G. YOT,<sup>2,\*</sup>  
Umit B. DEMIRCI<sup>1,\*</sup>

<sup>1</sup> Institut Européen des Membranes, IEM – UMR 5635, Univ Montpellier, CNRS, ENSCM, Montpellier, France

<sup>2</sup> Institut Charles Gerhardt Montpellier, ICGM – UMR 5253, Univ Montpellier, CNRS, ENSCM, Montpellier, France

\* [umit.demirci@umontpellier](mailto:umit.demirci@umontpellier); [pascal.yot@umontpellier.fr](mailto:pascal.yot@umontpellier.fr)

## Abstract

Viewing calcium hydrazinidoborane  $\text{Ca}(\text{N}_2\text{H}_3\text{BH}_3)_2$  (9.3 wt% H) as a potential hydrogen storage material, we long sought to synthesize it by solid-solid reaction of calcium hydride  $\text{CaH}_2$  and hydrazine borane  $\text{N}_2\text{H}_4\text{BH}_3$ . However, it was elusive because of unsuitable experimental conditions. In situ synchrotron thermodiffraction helped us to identify the key role played by the temperature in the formation of the new phase. From 45°C, new diffraction peaks appear, and the DSC analysis shows an exothermic signal. Thermal activation is thus required to make solid-state  $\text{CaH}_2$  react with melted (liquid-state)  $\text{N}_2\text{H}_4\text{BH}_3$ . The XRD pattern can be indexed using a mixture of two phases: (i) unreacted  $\text{CaH}_2$  as a minor phase (29 wt%) and (ii) the hitherto elusive  $\text{Ca}(\text{N}_2\text{H}_3\text{BH}_3)_2$  (71 wt%). The as-formed  $\text{Ca}(\text{N}_2\text{H}_3\text{BH}_3)_2$  crystallizes in a monoclinic *Ic* (No. 9) unit cell where the intermolecular interactions form chains (layers) along the *a* axis, resulting in intra-chain and inter-chain Ca...Ca distances as short as 4.39 and 7.04 Å respectively. Beyond 90°C,  $\text{Ca}(\text{N}_2\text{H}_3\text{BH}_3)_2$  decomposes, as evidenced by the diffraction peaks fading, an exothermic signal revealed by DSC, a weight loss (5.3 wt% at 200°C) observed by TGA, and a gas release ( $\text{H}_2$ , and some  $\text{N}_2$ ,  $\text{NH}_3$ ,  $\text{N}_2\text{H}_4$ ) monitored by MS. The as-formed thermolytic residue is amorphous and of complex polymeric composition. These results and the next challenges, are discussed herein.


## Keywords

Calcium hydrazinidoborane; Dehydrogenation; Hydrazine borane; Hydrogen storage.

## 1. Introduction

In the field of chemical hydrogen storage, B-N-H materials emerged as promising candidates. They draw their strength from high gravimetric hydrogen densities as well as the concomitant existence of B–H<sup>δ-</sup> and N–H<sup>δ+</sup> bonds resulting in heteropolar dihydrogen B–H<sup>δ-</sup>...H<sup>δ+</sup>–N interactions which drive their solid state at ambient conditions and their ability to release H<sub>2</sub> at relatively mild conditions. A typical representative of B-N-H materials is ammonia borane NH<sub>3</sub>BH<sub>3</sub> (AB), composed of 19.5 wt% of hydrogen [1-4]. In pristine state, AB decomposes more than it dehydrogenates, and is not suitable for the targeted application [5-8]. A number of derivatives has been further developed. The strategy is to substitute one H<sup>δ+</sup> of the NH<sub>3</sub> group of AB by a cation to form alkali and alkaline-earth amidoboranes M(NH<sub>2</sub>BH<sub>3</sub>)<sub>n</sub>, with M<sup>n+</sup> being e.g. Li<sup>+</sup>, Na<sup>+</sup>, Mg<sup>2+</sup>, or Ca<sup>2+</sup> [9,10]. The idea is to destabilize the anionic entity [NH<sub>2</sub>BH<sub>3</sub>]<sup>-</sup> so that the ionic solid M(NH<sub>2</sub>BH<sub>3</sub>)<sub>n</sub> releases pure H<sub>2</sub> at temperatures lower than those required for AB decomposition. A typical example is sodium amidoborane NaNH<sub>2</sub>BH<sub>3</sub> (9.5 wt% H) that starts to dehydrogenate at about 50°C and is able to release 7.5 wt% H (2 equiv H<sub>2</sub>) up to 200°C [11].

Another representative of B-N-H materials is hydrazine borane N<sub>2</sub>H<sub>4</sub>BH<sub>3</sub> (HB), composed of 15.4 wt% of hydrogen [12]. HB is a derivative of AB, the NH<sub>3</sub> of which being substituted by N<sub>2</sub>H<sub>4</sub>. Yet, HB, in pristine state, is not suitable for hydrogen storage because, under heating, it releases N<sub>2</sub>H<sub>4</sub> together with H<sub>2</sub>, and it generates a shock-sensitive solid when heated above 300°C [13]. Alkali hydrazinidoboranes NH<sub>2</sub>NH(M)BH<sub>3</sub> (or MN<sub>2</sub>H<sub>3</sub>BH<sub>3</sub>; denoted MHB) were synthesized by reaction of HB with an alkali hydride MH in such a way that one H<sup>δ+</sup> of the middle NH<sub>2</sub> was substituted by M<sup>+</sup> [14]:



MHB is an ionic solid [15]. Compared to HB, the B–H and N–H bonds of MHB are weaker, which results in more attractive dehydrogenation properties [16]. To date, four MHBs have been successfully synthesized.

The first example of MHB is the polymorphic LiN<sub>2</sub>H<sub>3</sub>BH<sub>3</sub> (denoted LiHB), prepared by ball-milling equimolar amounts of HB and LiH [17,18]. The low-temperature  $\beta$  phase (orthorhombic, s.g. *Pbca*) transforms into the metastable high-temperature  $\alpha$  phase (monoclinic, s.g. *P2<sub>1</sub>/c*) at around 90°C [19]. LiHB is able to release about 2.5 equiv H<sub>2</sub> when heated up to 150°C (i.e. 9.9

wt% H released, out of a gravimetric hydrogen density of 11.7 wt% H). The second example is  $\text{NaN}_2\text{H}_3\text{BH}_3$  (NaHB; monoclinic, s.g.  $P2_1/n$ ) [20]. NaHB is prepared at a temperature below  $-30^\circ\text{C}$  because the reaction of HB with NaH is exothermic ( $-27.8 \text{ kJ mol}^{-1}$ ) [21]. NaHB is less stable than LiHB: it releases  $\text{H}_2$  from about  $60^\circ\text{C}$ , with about 2.6 equiv  $\text{H}_2$  generated up to  $150^\circ\text{C}$  (i.e. 7.6 wt% H released, out of a gravimetric hydrogen density of 8.9 wt% H). The third example is  $\text{KN}_2\text{H}_3\text{BH}_3$  (KHB; monoclinic, s.g.  $P2_1$ ). It is synthesized in high pressure vessel and tetrahydrofuran [22], since the solid state reaction between HB and KH is violent ( $-70.2 \text{ kJ mol}^{-1}$ ) [21]. KHB, less stable than the previous hydrazinidoboranes, starts to dehydrogenate below  $50^\circ\text{C}$  and, cumulatively, about 2.5 equiv  $\text{H}_2$  are released up to  $193^\circ\text{C}$  (i.e. 6 wt% H released, out of a gravimetric hydrogen density of 7.2 wt% H). The fourth and last example is  $\text{RbN}_2\text{H}_3\text{BH}_3$  (monoclinic, s.g.  $P2_1$ ) [23]. Its dehydrogenation properties are favorably compared to those of LiHB. However, with a gravimetric hydrogen density of 4.65 wt% H and a very low terrestrial abundance of the element Rb, the potential of RbHB as hydrogen carrier appears to be rather limited.

To date, alkaline-earth hydrazinidoboranes  $\text{M}(\text{N}_2\text{H}_3\text{BH}_3)_2$  (denoted  $\text{M}(\text{HB})_2$ , with  $\text{M}^{2+} = \text{e.g. Mg}^{2+}, \text{Ca}^{2+}$ ) have not been properly considered and really investigated. Advantageously, they carry more hydrogen than NaHB (8.9 wt% H) and KH (7.2 wt% H) do; for instance, the theoretical gravimetric hydrogen densities of  $\text{Mg}(\text{HB})_2$  and  $\text{Ca}(\text{HB})_2$  are calculated to be 10.6 and 9.3 wt% H respectively. Another attractive feature is that calcium is, on earth, the most abundant element of the periodic table s block. One has to mention one study that reports the possible synthesis of  $\text{Ca}(\text{HB})_2$  through an X-ray diffraction pattern that has not been refined and solved [17]. In a previous work [21], we tried to get such a  $\text{Ca}(\text{HB})_2$  derivative by ball milling one equivalent of  $\text{CaH}_2$  and 2 equivalents of HB at different milling conditions. However, all of our attempts failed. Soft ball milling conditions (e.g. 200 rpm for 10 min) resulted in binary mixtures of unreacted starting materials whereas harsher conditions (e.g. 450 rpm for 30 min) led to decomposition of HB into an amorphous polymeric solid. Consequently, we integrated another variable, the temperature. We focused our efforts in following the temperature-dependent evolution of the binary mixture  $\text{CaH}_2$ -2HB by synchrotron X-ray thermodiffraction and differential scanning calorimetry. Our approach met with the successful synthesis of the first representative of alkaline-earth hydrazinidoboranes, i.e. calcium hydrazinidoborane  $\text{Ca}(\text{N}_2\text{H}_3\text{BH}_3)_2$  (denoted  $\text{Ca}(\text{HB})_2$ ), as described below.  $\text{Ca}(\text{HB})_2$  was fully characterized by X-

ray diffraction, magic-angle spinning nuclear magnetic resonance spectroscopy, and Fourier transform infrared spectroscopy, and its dehydrogenation properties were followed by thermogravimetric analysis coupled to mass spectrometry.

## 2. Materials and methods

### 2.1. Materials

Hydrazine borane  $\text{N}_2\text{H}_4\text{BH}_3$  (HB) was synthesized according to a protocol we previously optimized [13]. Calcium hydride  $\text{CaH}_2$  (98%) purchased from Alfa Aesar was used as received. Both chemicals were stored and systematically handled in an argon-filled glove box (MBraun M200B, with  $\text{O}_2 < 0.1$  ppm and  $\text{H}_2\text{O} < 0.1$  ppm).

### 2.2. Preliminary comment

In the present project, we first attempted to synthesize  $\text{Ca}(\text{HB})_2$  via a wet chemistry approach. Anhydrous tetrahydrofuran (THF;  $\geq 99.9\%$ ; Sigma-Aldrich) was used. Under argon atmosphere (i.e. in the glove box) and at room temperature, 50 mg of HB (1.09 mmol) was dissolved in 10 mL of THF. In parallel, 23 mg of  $\text{CaH}_2$  (0.546 mmol) was dispersed in 10 mL of THF. The borane solution was slowly added to the hydride dispersion. The mixture was allowed to age for 48 h under stirring. After solvent extraction, a solid consisting of unreacted HB and  $\text{CaH}_2$  was recovered. This synthesis approach was thus abandoned, and we returned to our solid-solid reaction approach.

### 2.3. Temperature-dependent evolution of $\text{CaH}_2$ -2HB

The synthetic conditions for  $\text{Ca}(\text{HB})_2$  were defined as follows. Under argon atmosphere, 275 mg of  $\text{CaH}_2$  (6.5 mmol) and 600 mg of HB (13 mmol) were put in a stainless steel jar of 50 mL (containing 12 g of stainless steel balls) and mixed at 200 rpm for 10 min (Retsch PM 100 planetary mill). The resulting mixture, denoted **1**, was recovered to be stored under argon atmosphere. In another argon-filled glove box (MBraun Unilab,  $\text{O}_2 < 0.1$  ppm and  $\text{H}_2\text{O} < 0.1$  ppm), **1** was loaded into a glass capillary of 0.5 mm diameter. The capillary was sealed to prevent the sample from air and moisture. **1** was analyzed by X-ray thermodiffractometry using synchrotron radiation (Swiss Norwegian Beam Line SNBL BM01A, at European Synchrotron

Facility ESRF, Grenoble, France). The diffraction patterns were collected using a monochromatic beam and a PILATUS 2M detector. NIST standard LaB<sub>6</sub> was used for the calibration of all the parameters of the detector, the sample-detector distance (343.71 mm), and the wavelength of 0.70814 Å. The temperature change was controlled with an Oxford Cryostream 700+ allowing working over the range of temperature 19-100°C. The diffraction patterns were recorded simultaneously using a rotation of the capillary of 60° min<sup>-1</sup>. In parallel, **1** was analyzed by differential scanning calorimetry (DSC; Q600, TA Instruments). The sample was heated from 0 to 75°C at 1°C min<sup>-1</sup>, and then it was cooled down to 0°C at the same rate.

On the basis of the aforementioned thermodiffraction and DSC experiments, **2** (in fact a Ca(HB)<sub>2</sub>-rich sample) was synthesized from **1**. Typically, **1** was loaded in a stainless reactor under argon atmosphere (in the glove box) and then sealed. The sample was heated up to 62°C at 1°C min<sup>-1</sup>, kept at this temperature for 50 min, and quickly cooled down (by immersing the reactor in a tap water bath). The as-formed **2** was recovered and stored in the argon-filled glove box.

#### 2.4. Characterization of Ca(HB)<sub>2</sub>

Two XRD patterns among those collected were selected to be solved and indexed. The first pattern was that obtained at 19°C for **1** and consists in a mixture of CaH<sub>2</sub> and HB. It was refined using the Rietveld method to confirm the proportion of the two phases (cf. SI). The second pattern was the one collected at 62°C; it belongs to **2** that was found to consist in a mixture of Ca(HB)<sub>2</sub> and CaH<sub>2</sub>. The unit cell parameters of Ca(HB)<sub>2</sub> were determined using DICVOL06 [24]. Starting from the determined parameters, the structural model of Ca(HB)<sub>2</sub> was obtained by using FOX [25]. The as-obtained model was refined using the JANA2006 software package [26]. The Rietveld refinement was carried out considering the two phases, Ca(HB)<sub>2</sub> and CaH<sub>2</sub>, while for Ca(HB)<sub>2</sub> the fragments N–N–B were considered as being two different molecular fragments and as being rigid. The Rietveld refinement was carried out using a Pseudo-Voigt peak shape with a cut-off of 12 for the two phases. Considering the quality of the diffraction pattern, the isotropic thermal parameters ( $B_{\text{iso}}$ ) were constrained to be identical for the same atom type in the unit cell. The locations of the H atoms linked to the N and B atoms were determined by performing a geometry constrained optimization of the structure (Ca, B and N atoms fixed in their initial positions) at the force-field level. All atoms of the system were represented as Lennard-Jones

charged sites with LJ parameters taken from the UFF force field [27] while the charges were calculated using the QeQ [28] method. In addition, the uncertainties of the atomic coordinates for the H atoms are not reported here because they were not refined.

**2** was analyzed by magic-angle spinning nuclear magnetic resonance (MAS NMR) spectroscopy on the nuclei  $^{11}\text{B}$  (Varian VNMR400; 128.37 MHz; 20000 rpm) and  $^{43}\text{Ca}$  (Varian VNMR600; 40.37 MHz; 20000 rpm). To this end, **2** was loaded in the NMR rotor in the glove box. The rotor was afterwards put in an argon-filled vial (to prevent the sample from air and moisture) and transferred to the spectrometer localized in another building. The NMR analyses were performed at  $-10^\circ\text{C}$ . **2** was also analyzed by Fourier transform infrared spectroscopy (FTIR; IS50 Thermo Fisher Scientific). The thermal behavior of **2** was studied by thermogravimetric (TG) analysis (Netzsch STA 449 F1 Jupiter) coupled to mass spectrometry (MS; Netzsch QMS 403D Aëolos Quadro) and by differential scanning calorimetry (DSC; Q600, TA Instruments). The heating rate was  $1^\circ\text{C min}^{-1}$  and the analyses were performed up to  $300^\circ\text{C}$ .



The thermolytic residue, denoted **3**, forming upon the decomposition of **2** at  $200^\circ\text{C}$  was prepared in high amount for analysis. Typically, **2** was loaded in a stainless reactor under argon atmosphere and sealed. It was heated up to  $200^\circ\text{C}$  at  $1^\circ\text{C min}^{-1}$ . Then it was allowed to cool down. The as-obtained **3** (recovered in the argon-filled glove box) was analyzed by powder X-ray diffraction (XRD; PANalytical X'Pert Multipurpose diffractometer equipped with an X'Celerator detector; Cu  $K\alpha_1/\alpha_2$  radiation,  $\lambda = 1.5418 \text{ \AA}$ , 45 kV, 30 mA). The XRD pattern was collected using Bragg-Brentano geometry on a spinning zero background sample holder loaded in the glove box. The powder was protected using a Kapton foil stuck onto the sample holder with Apiezon grease (H quality) to prevent any air and moisture contamination. **3** was also analyzed by  $^{11}\text{B}$  MAS NMR and FTIR spectroscopy.

### **3. Results and discussion**

#### **3.1. Synthesis of $\text{Ca}(\text{HB})_2$**

Though the coveted  $\text{Ca}(\text{HB})_2$  was elusive in our previous attempts [21], the TG analysis results of the binary mixture  $\text{CaH}_2\text{-2HB}$  opened up a new possibility. An interesting feature was the

evolution of some H<sub>2</sub> starting from about 60°C, which was interpreted as a possible reaction of CaH<sub>2</sub> with melted HB, in some extent, such as:




The key to synthesize Ca(HB)<sub>2</sub> appeared to be the temperature. Then, our further efforts, through the present work, focused on the use of in situ synchrotron X-ray thermodiffraction to validate our assumption and to find the temperature at which the sought phase Ca(HB)<sub>2</sub> could be obtained.


We prepared a mixture of one equivalent of CaH<sub>2</sub> and two equivalents of HB, ball-milled at 200 rpm for 10 min under argon atmosphere. The as-obtained homogeneous mixture, denoted **1**, was heated at 1°C min<sup>-1</sup>, starting from 19°C. The temperature evolution of **1** was analyzed by thermodiffraction up to 100°C (Figure 1 and S1). The thermodiffraction data were analyzed in conjunction with the DSC results (collected over the temperature range 0-75°C) (Figure 2). Below 45°C, the diffraction peaks can be all assigned to the CaH<sub>2</sub> and HB phases. For example, the XRD pattern collected at 19°C was refined using the Rietveld method (Figures 3 and S2, Table S1). The unit cell parameters and atomic positions for the two phases, i.e. HB and CaH<sub>2</sub>, were found to be in good agreement with those published previously [13,29]. The relative amounts of the HB and CaH<sub>2</sub> solids obtained by the refinement of the powder XRD data were 27.9(5) and 72.1(2) wt%, leading to a molar ratio of 2.36.

Beyond 45°C, a baseline deviation of the heat flow is observed, suggesting an exothermic reaction. Concomitantly, new diffraction peaks appear, for example between 4 and 10°, and they grow with the increase of the temperature. Their apparition is correlated with the decrease of the intensity of the peaks of both CaH<sub>2</sub> and HB. In other words, a new phase, denoted **2**, is forming.




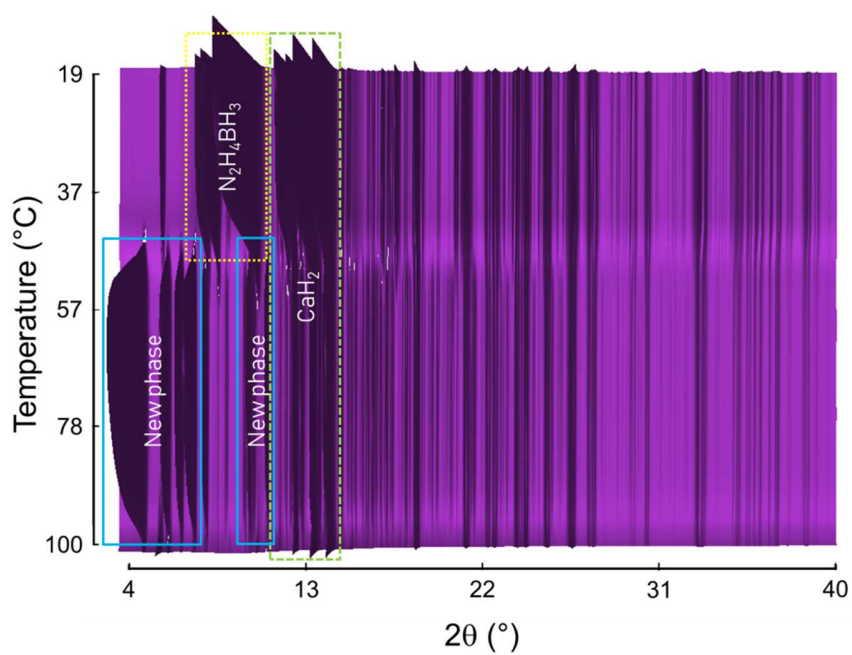

**Figure 1.** Sequential plot of the diffraction patterns obtained from **1** (the mixture of 1 equiv  $CaH_2$  and 2 equiv HB) within the temperature range 19-100°C. The new phase is  $Ca(HB)_2$ .

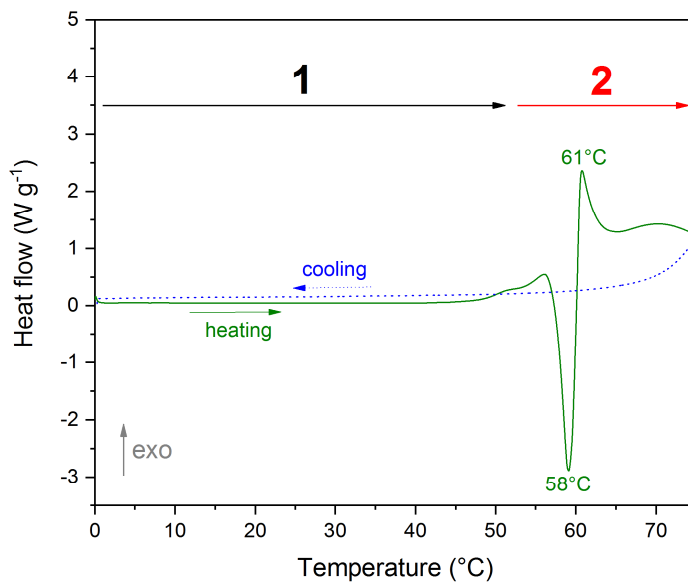

**Figure 2.** DSC analysis of **1** upon heating up to  $75^\circ C$  and then cooling down to  $0^\circ C$  (heating rate of  $1^\circ C min^{-1}$ ). The temperature ranges of the samples **1** and **2** are shown.

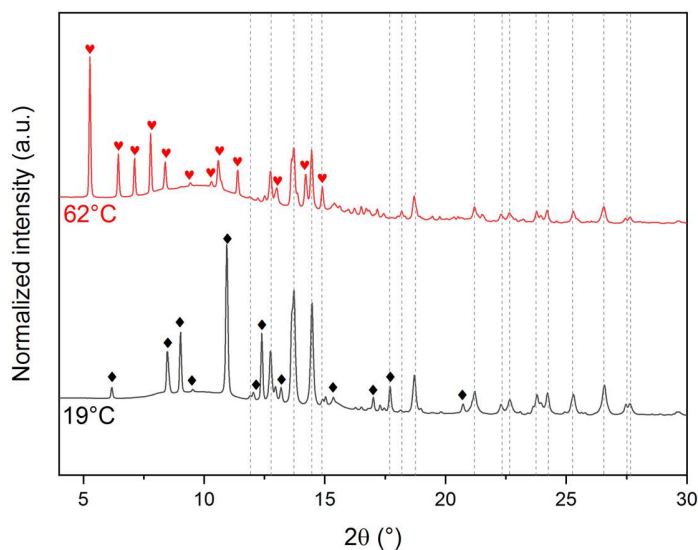

**Figure 3.** X-ray diffraction patterns of **1** collected at 19°C and 62°C. The main peaks belonging to  $\text{CaH}_2$  (vertical dashed grey lines) and HB (symbol ◆) are shown (indexed pattern shown by Figure S2). The main peaks due to the new phase  $\text{Ca}(\text{HB})_2$  are indicated by the symbol ♥ (indexed pattern shown by Figure S3).

Above 55°C, the aforementioned exothermic event is compensated by an endothermic event that is typical of HB melting, but the exothermic signal gets rapidly over the endothermic one. Under cooling from 75°C down to 0°C, neither exothermic signal nor endothermic one is seen, bearing out the formation of the new phase. The key to synthesize  $\text{Ca}(\text{HB})_2$  seems to be the temperature, more precisely it seems to be HB in liquid state (leading to increased entropy factor) that is more likely to react with solid-state  $\text{CaH}_2$ . Peaks due to a small amount of unreacted  $\text{CaH}_2$  can be seen above 55°C, which indicates that **2** would be a mixture of the new solid as the main phase (i.e.  $\text{Ca}(\text{HB})_2$ ) and of some  $\text{CaH}_2$ . Similar phase-rich solids were reported for the amidoborane counterpart  $\text{Ca}(\text{NH}_2\text{BH}_3)_2$  that was prepared by ball-milling [30,31]. An additional experiment using Beyond 97°C, the diffraction peaks of **2** cannot be observed anymore, suggesting decomposition.

### 3.2. Crystal structure of $\text{Ca}(\text{HB})_2$

The XRD pattern corresponding to the maximum intensity of **2** (i.e. that collected at 62°C) was successfully indexed using a mixture of two phases (Figures 3 and S3). The first phase is  $\text{CaH}_2$ , indexed as an orthorhombic *Pnma* (No. 62) unit cell [29]. The second one is  $\text{Ca}(\text{HB})_2$ , indexed as a monoclinic *Ic* (No. 9) unit cell. The relative amounts of these two crystalline phases are 29.0(7)


and 71.0(3) wt%, respectively, as obtained by the refinement of the XRD pattern. The structure parameters corresponding to  $\text{Ca}(\text{HB})_2$  (as well as those of the remaining  $\text{CaH}_2$ ) are summarized in [Table 1](#).

The HB derivatives show the same lattice system, i.e. monoclinic, but  $\text{Ca}(\text{HB})_2$  shows a different cell (s.g.  $Ic$  versus  $P2_1/n$  for NaHB [20]). As a derivative of AB,  $\text{Ca}(\text{NH}_2\text{BH}_3)_2$  shows a different monoclinic cell (s.g.  $C2$  (No. 5)) [30]. Besides it shows a smaller cell volume per formula unit ( $138.5 \text{ \AA}^3$ ) compared to that of  $\text{Ca}(\text{HB})_2$  ( $244.8 \text{ \AA}^3$ ); this is consistent with the larger size of the anion  $[\text{N}_2\text{H}_3\text{BH}_3]^-$ . The volume per formula unit of HB is also smaller with  $80.2 \text{ \AA}^3$  [13]; this is consistent with the presence of the bulkier cation  $\text{Ca}^{2+}$  in  $\text{Ca}(\text{HB})_2$ .

According to the derived crystal structure of  $\text{Ca}(\text{HB})_2$  ([Figures 4 and 5](#)), the intermolecular interactions form chains (layers) along the  $a$  axis. The  $\text{Ca}\cdots\text{Ca}$  distance along the  $a$  axis (intra-chain) is the shortest one, with  $4.39 \text{ \AA}$ , whereas the inter-chain  $\text{Ca}\cdots\text{Ca}$  distance is  $7.04 \text{ \AA}$ . The shortest  $\text{Ca}\cdots\text{N}$  distance is  $2.53 \text{ \AA}$ , which is comparable to that in  $\text{Ca}(\text{NH}_2)_2$  ( $2.44\text{-}2.57 \text{ \AA}$ ) [32] and is slightly longer than the shortest distance in  $\text{Ca}(\text{NH}_2\text{BH}_3)_2$  ( $2.47 \text{ \AA}$ ) [30]. The shortest  $\text{Ca}\cdots\text{B}$  distance is  $3.38 \text{ \AA}$ , whereas distances of  $2.87\text{-}3.03$  and  $2.89\text{-}2.96 \text{ \AA}$  were reported for  $\text{Ca}(\text{NH}_2\text{BH}_3)_2$  [30] and  $\text{Ca}(\text{BH}_4)_2$  [33] respectively. The  $\text{Ca}\cdots\text{H}\text{-B}$  and  $\text{Ca}\cdots\text{H}\text{-N}$  distances resulting from the geometry optimization are between  $2.33$  and  $2.43 \text{ \AA}$ . With respect to the two directly binding anions, the distances of the N–N bonds from the Rietveld refinement are  $1.38$  and  $1.40 \text{ \AA}$ . They are comparable to the distance observed for HB ( $1.41 \text{ \AA}$ ) [13], but shorter compared to the MHBs ( $\alpha\text{-LiHB}$   $1.47 \text{ \AA}$  [17];  $\beta\text{-LiHB}$   $1.50 \text{ \AA}$  [18]; NaHB  $1.46 \text{ \AA}$  [19]; KHB  $1.47 \text{ \AA}$  [22]; RbHB  $1.43 \text{ \AA}$  [23]). The B–N bonds have lengths of  $1.53$  and  $1.57 \text{ \AA}$ . This is consistent with the bond lengths in  $\text{Ca}(\text{NH}_2\text{BH}_3)_2$  ( $1.55 \text{ \AA}$ ) [30] and in the MHBs ( $1.54\text{-}1.55 \text{ \AA}$ ) [17,18,19,22,23]. They are all slightly shorter than the B–N bond of HB ( $1.59 \text{ \AA}$ ) [13]; this is typical of the bond strengthening/shortening due to  $\text{M}^+$  or  $\text{M}^{2+}$  insertion. With regard to the interactions between the  $[\text{N}_2\text{H}_3\text{BH}_3]^-$  anions, the average intermolecular  $\text{H}^{\delta+}\cdots\text{H}^{\delta-}$  distance is about  $2.16 \text{ \AA}$ , which is longer than the distance in HB ( $2.01 \text{ \AA}$ ) and shorter than the sum of the van der Waals radii for two H atoms ( $2.4 \text{ \AA}$ ) [13]. These interactions, together with the van der Waals interactions between the cation and the anionic entities, take part to the stabilization of the solid state of  $\text{Ca}(\text{HB})_2$  [34].


**Table 1.** Space groups (*s.g.*), unit cell parameters, goodness of fit (GoF), R values, and structural parameters for the refined structures Ca(HB)<sub>2</sub> and CaH<sub>2</sub> in **2**.

<b>Formula</b>	<b>Ca(NH<sub>2</sub>NHBH<sub>3</sub>)<sub>2</sub></b>					
<i>s.g.</i>	<i>Ic</i> (No. 9)					
<b>Z</b>	4					
<i>a</i> (Å)	8.2597(12)					
<i>b</i> (Å)	10.4118(15)					
<i>c</i> (Å)	11.9367(17)					
$\beta$ (°)	107.515(10)					
<i>V</i> (Å <sup>3</sup> )	979.0(3)					
<b>Temperature</b>	62°C					
<b>R<sub>(obs)</sub> / wR<sub>(obs)</sub></b>	16.39 / 20.88					
<b>R<sub>(all)</sub>/wR<sub>(all)</sub></b>	16.42 / 20.89					
<b>Atom</b>	<b>Site</b>	<b>Occupancy</b>	<b>x</b>	<b>y</b>	<b>z</b>	<b>Biso (Å<sup>2</sup>)</b>
Ca1_1	4e	1	0.3524(11)	0.4290(14)	0.8726(6)	0.072(5)
B1_1			0.599(6)	1.112(4)	0.195(4)	0.015(12)
N2_1			0.559(4)	0.894(3)	0.230(3)	0.036(8)
N3_1			0.471(4)	1.008(3)	0.201(3)	0.036(8)
H1_1			0.70568	0.12429	0.28649	1.2
H2_1			0.52889	0.21314	0.17802	1.2
H3_1			0.65159	0.09379	0.11456	1.2
H4_1			0.48451	0.66868	0.76230	1.2
H5_1			0.57346	0.64977	0.65428	1.2
H6_1			0.38265	0.50134	0.61936	1.2
B2_1			0.341(8)	-0.062(4)	0.901(4)	0.015(12)
N4_1			0.439(4)	0.173(3)	0.915(3)	0.036(8)
N5_1			0.311(4)	0.085(3)	0.915(3)	0.036(8)
H7_1			0.32078	0.58609	0.30016	1.2
H8_1			0.48034	0.58979	0.45625	1.2
H9_1			0.24546	0.62381	0.43558	1.2
H10_1	0.91255	0.70923	0.32978	1.2		
H11_1	0.94848	0.74196	0.47977	1.2		
H12_1	0.74850	0.60788	0.47658	1.2		
<b>Formula</b>	<b>CaH<sub>2</sub></b>					
<i>s.g.</i>	<i>Pnma</i> (No. 62)					
<b>Z</b>	4					
<i>a</i> (Å)	5.9663(5)					
<i>b</i> (Å)	3.6053(3)					
<i>c</i> (Å)	6.8233(6)					
<i>V</i> (Å <sup>3</sup> )	146.77(2)					
<b>Temperature</b>	62°C					
<b>R<sub>(obs)</sub> / wR<sub>(obs)</sub></b>	8.44 / 16.95					
<b>R<sub>(all)</sub>/wR<sub>(all)</sub></b>	8.44 / 16.95					
<b>Atom</b>	<b>Site</b>	<b>Occupancy</b>	<b>x</b>	<b>y</b>	<b>z</b>	<b>Biso (Å<sup>2</sup>)</b>
Ca1_2	4e	1	0.2626(11)	0.75	0.1104(4)	0.0104(9)
<b>GoF</b>	25.79					
<b>Rp</b>	2.25					
<b>wRp</b>	2.78					

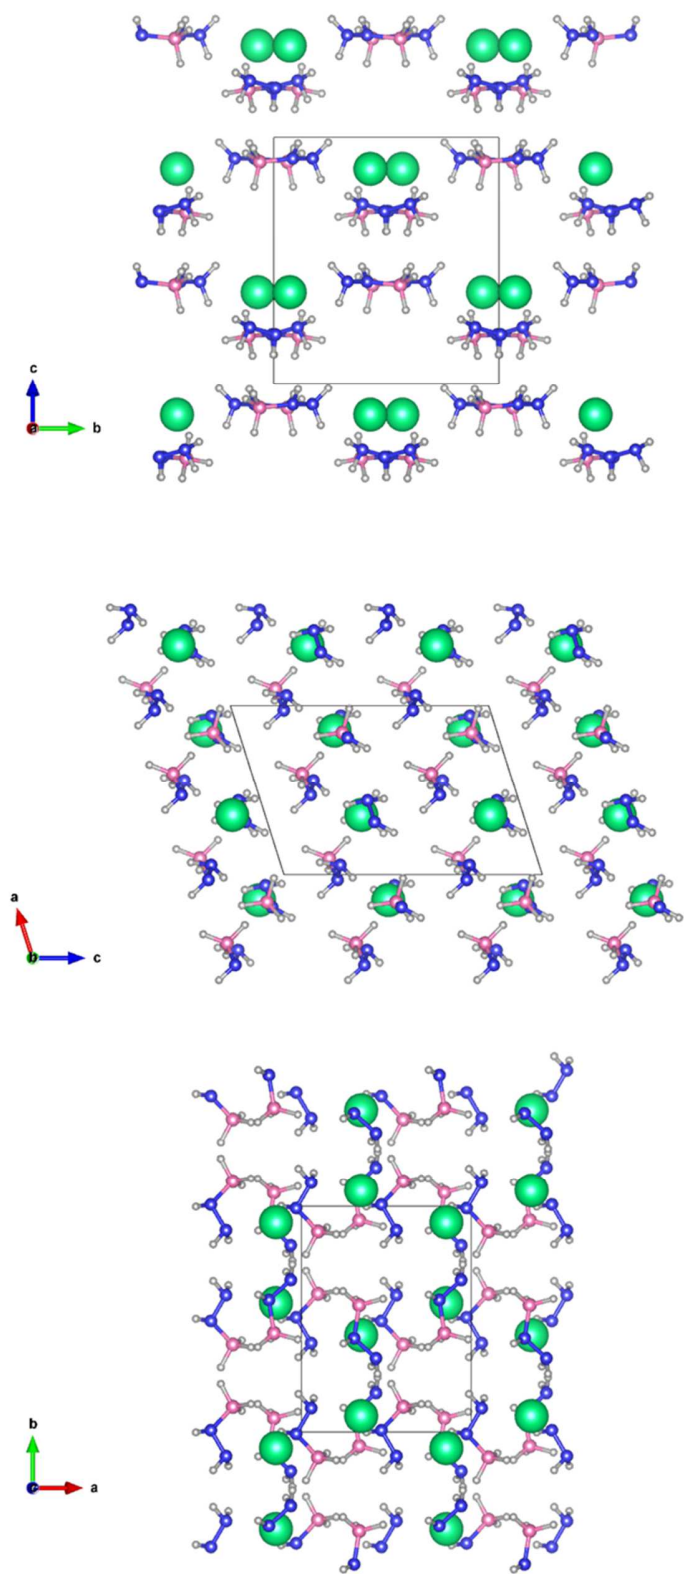

**Figure 4.** Crystal structure of  $\text{Ca}(\text{HB})_2$  along the  $a$ ,  $b$  and  $c$  crystallographic axes. The white, pink, blue and green spheres correspond to the H, B, N and Ca atoms respectively.

As mentioned in the introduction, Wu et al. [17] attempted a synthesis of  $\text{Ca}(\text{HB})_2$  by ball-milling  $\text{CaH}_2$  and HB (mol ratio 1:2) at 200 rpm for 3h. They reported a partial XRD pattern without further exploitation. We compared it to the pattern we collected here: some of the peaks are comparable to ours for a  $2\theta$  range likely between 5 and  $15^\circ$ , and the others look like belonging to unreacted HB. In other words, Wu et al. were able to recover a  $\text{Ca}(\text{HB})_2$ -containing solid by using a planetary mill (Fritsch Pulverisette 7), whereas we failed to synthesize it by using a different planetary mill (Retsch PM 100) [21]. Interestingly, with respect to the polymorphic LiHB, Wu et al. [17] synthesized the high-temperature phase with their planetary mill, whereas we synthesized the low-temperature phase with ours. These two different achievements indicate first that the device used by Wu et al. is more energetic in comparable milling conditions, and second that synthesis of a HB derivative is also sensitive to the apparatus used.

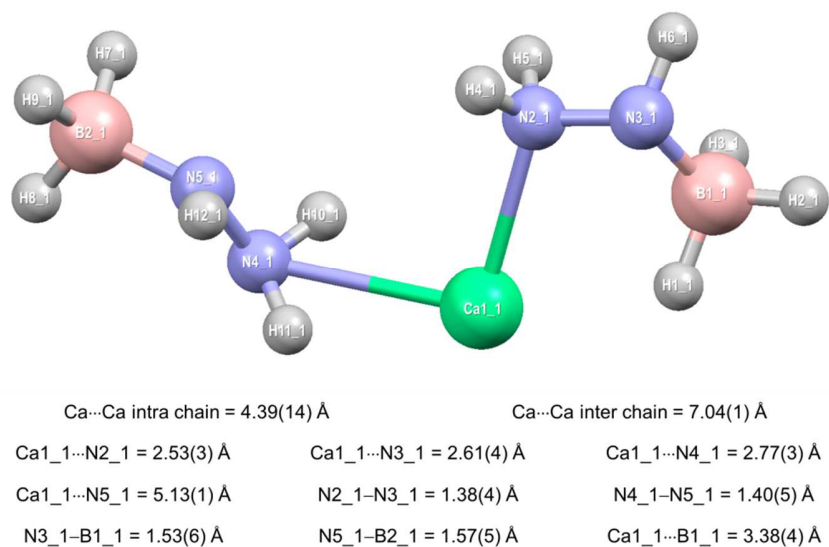


**Figure 5.** Asymmetric unit showing the coordination around the cation  $\text{Ca}^{2+}$ , and inter- and intra-atomic distances obtained for  $\text{Ca}(\text{HB})_2$  in **2**.

### 3.3. Molecular analysis of $\text{Ca}(\text{HB})_2$


**2** was analyzed by  $^{11}\text{B}$  MAS NMR spectroscopy (Figure 6). The spectrum shows a single split signal centered at  $-24$  ppm, typical of a quadrupolar coupling for an  $\text{NBH}_3$  environment. The electron repartition around the B element is anisotropic. This is different from the isotropy and the single Gaussian-like signal reported for the alkali derivatives, where the strong interaction

between  $M^+$  ( $M = \text{Li}, \text{Na}, \text{K}$ ) and  $\text{BH}_3$  substantially smooths the electronic repartition around B [17,18,20,22]. With **2**, the larger atomic size and lower electropositivity of  $\text{Ca}^{2+}$  would make the  $\text{Ca}^{2+}\cdots\text{H}^{\delta-}\text{-B}$  interactions weak enough not to modify the anisotropic repartition of electrons around B [9,10]. Our observation is in fact consistent with the signature reported for  $\text{Ca}(\text{NH}_2\text{BH}_3)_2$  [35]. The spectrum of **2** shows a small deviation of the baseline between 0 and  $-15$  ppm ascribed to  $\text{N}_2\text{BH}_2$  and  $\text{N}_3\text{BH}$  environments that we usually see because of the high-speed rotation of the spectrometer rotor. However, we cannot discard dehydrocoupling in small extent of HB molecules when **1** was heated.

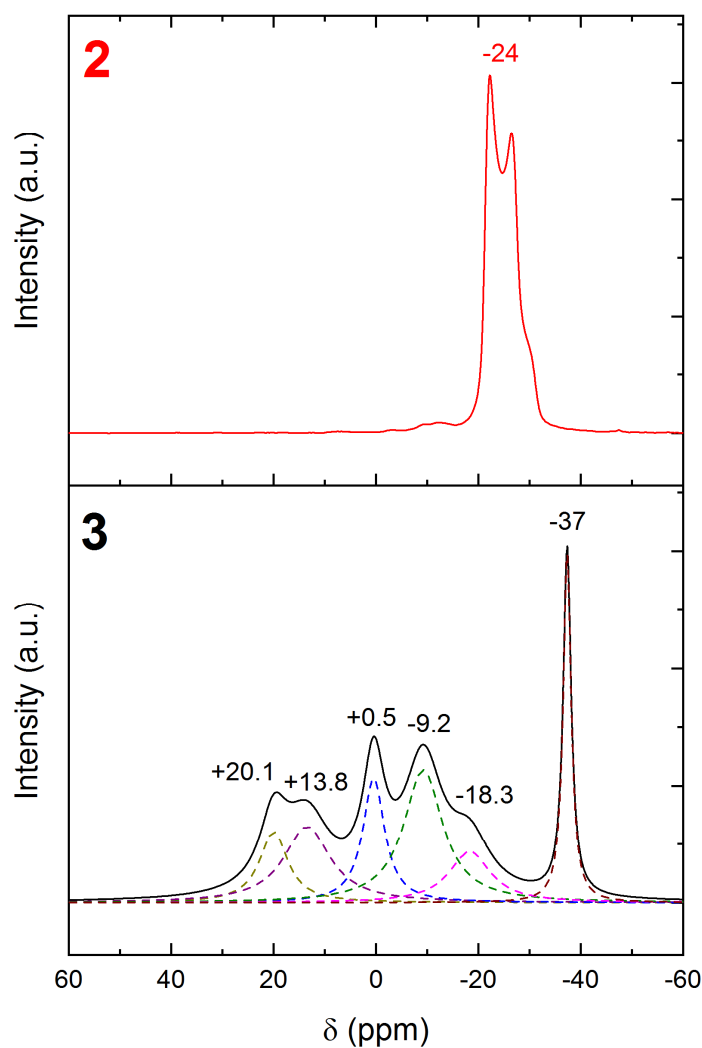

**Figure 6.**  $^{11}\text{B}$  MAS NMR spectra of **2** and **3**. The chemical shifts (in ppm) of the signals are given. For **3**, the deconvoluted signals are shown in dashed lines.

**2** was also analyzed by  $^{43}\text{Ca}$  MAS NMR spectroscopy (Figure 7). The spectrum shows one broad and asymmetric signal which maximum is at 58.1 ppm. It cannot be ascribed to  $\text{CaH}_2$  (+94.4 ppm) [36]. The chemical shift of the nucleus  $^{43}\text{Ca}$  is sensitive to the (Pauling) electronegativity of the element with which  $\text{Ca}^{2+}$  interacts. As  $\text{Ca}^{2+}$  interacts with N ( $\chi_{\text{N}} = 3.04$ ) of the anion  $[\text{N}_2\text{H}_3\text{BH}_3]^-$ , the signal belonging to **2** is expected to appear at lower chemical shift (+58.1 ppm) than the signal due to  $\text{CaH}_2$  (+94.4 ppm;  $\chi_{\text{H}} = 2.2$ ) and at higher chemical shift than that for e.g.  $\text{CaF}_2$  (-1.4 ppm;  $\chi_{\text{F}} = 3.98$ ) [37]. These observations support the formation of **2**. The presence of an additional signal of low intensity at +71.4 ppm, i.e. between the signal ascribed to **2** and that of  $\text{CaH}_2$ , cannot be discarded. It may belong to an intermediate species such as  $\text{HCa}(\text{N}_2\text{H}_3\text{BH}_3)$  (Eq. 2).

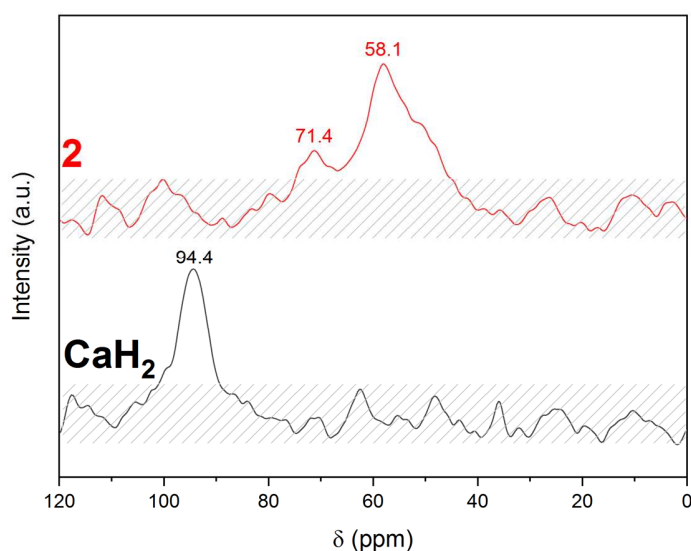


**Figure 7.**  $^{43}\text{Ca}$  MAS NMR spectra of **2** and of  $\text{CaH}_2$ . The chemical shifts of the prominent signals are given. The hatched area aims at distinguishing the possible signal at +58.1 ppm in the background noise.

**2** was analyzed by FTIR spectroscopy (Figure 8). The spectrum is typical of a compound containing N–H, B–H, N–N and B–N bonds. The vibrational modes of N–H are represented by the bands at  $3500\text{--}2500\text{ cm}^{-1}$  for symmetric and asymmetric stretching, and  $1650\text{--}1300\text{ cm}^{-1}$  for asymmetric and symmetric wagging. The band at  $1334\text{ cm}^{-1}$  has been assigned to N–N bending and that at  $100\text{--}940\text{ cm}^{-1}$  for twisting and/or rocking. The vibrational modes of B–H can be seen



through the bands at 2500-2100  $\text{cm}^{-1}$  for symmetric and asymmetric stretching, and at 1300–1100  $\text{cm}^{-1}$  for wagging and/or rocking. The N–N bond is mainly characterized by the band present at 1000  $\text{cm}^{-1}$  (stretching). The B–N bond can be seen *via* the symmetric stretching mode at 746  $\text{cm}^{-1}$ . Compared to the spectrum of HB [13], the B–H stretching bands of **2** show red shifts, indicating weakened B–H bonds. The N–H stretching region is as complex, with bands showing blue (2950  $\text{cm}^{-1}$ ), red (3210 and 3033  $\text{cm}^{-1}$ ), or negligible (3330, 3268 and 2661  $\text{cm}^{-1}$ ) shifts. This is consistent with cation-induced changes in the electronic densities of the anion  $[\text{N}_2\text{H}_3\text{BH}_3]^-$  [15,38].

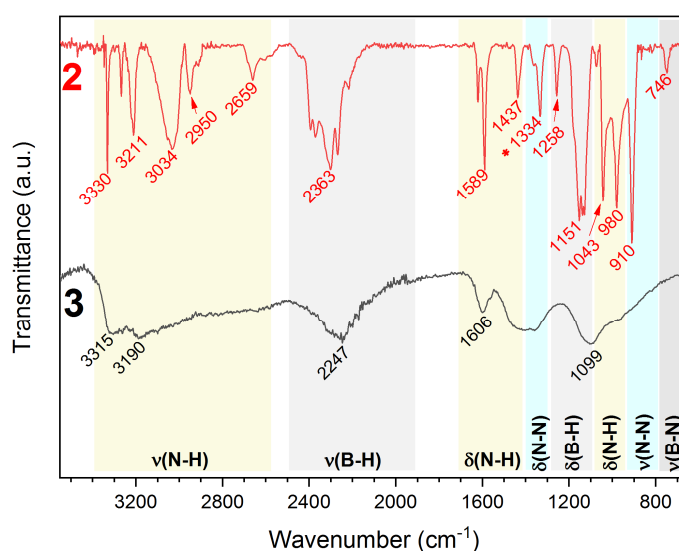

**Figure 8.** FTIR spectra of **2** and **3**. The vibration bands have been assigned and the wavenumbers ( $\text{cm}^{-1}$ ) are shown.

### 3.4. Thermal analysis and dehydrogenation properties of **2**

The gravimetric hydrogen density of pure  $\text{Ca}(\text{HB})_2$  is 9.3 wt% H. The figure is high enough to consider the compound as a possible solid-state hydrogen carrier, provided it is able to release  $\text{H}_2$  in mild conditions. Such a potential can be easily assessed by thermal analysis.

**2** was analyzed by TG-MS and DSC over the temperature range 50-300°C at which  $\text{CaH}_2$  is thermally stable (Figure 9). The curves can be divided into three distinct parts. (i) The part between 50 and about 90°C shows a weight gain of about 1.5 wt%. This is due to a “buoyancy” effect associated to the slow evolution of  $\text{H}_2$  in an argon-filled semi-closed crucible (i.e. an


aluminum crucible sealed with a cap having a small hole); this happens when argon (heavier than H<sub>2</sub>) is slowly expelled from the crucible while lighter H<sub>2</sub> forms. The H<sub>2</sub> release is slightly exothermic as evidenced by the very small hump on the DSC curve over the aforementioned temperature range. (ii) The second part of the curves starts from about 90°C and ends at about 170°C. **2** mainly dehydrogenates. The H<sub>2</sub> evolution followed by MS shows a maximum of intensity at 133°C. There is a concomitant release of N<sub>2</sub>. This is in fact typical of MABs [17-22]. Volatile (unwanted) by-products like NH<sub>3</sub> and N<sub>2</sub>H<sub>4</sub> are also generated. This indicates decomposition of **2** to some extent. The DSC curve shows a large exothermic wave, suggesting that the overall process is rather complex. (iii) The third part of the curves, starting from about 170 °C, is characterized by the evolution of H<sub>2</sub> only. At 300°C, the weight loss of **2** is 12 wt%, which is higher than the gravimetric hydrogen density of Ca(HB)<sub>2</sub> by 2.7 wt%, thus consistent with the release of N<sub>2</sub>, NH<sub>3</sub> and N<sub>2</sub>H<sub>4</sub> together with H<sub>2</sub>.

It is interesting to compare the DSC curves of **2** and **1** (Figures 2 and 9). Between about 50 and 90°C, **1** shows melting (endothermic signal) and evolution (subsequent exothermic signal); **2** does not evolve (fairly stable over the temperature range). The fact remains that **1** transforms into **2**. Above 90°C, the DSC profiles of **1** and **2** are superimposable, confirming that **1** transformed into **2**.

**2** does not melt. The DSC curve (Figure 9) does not show any endothermic process. We visually inspected the sample when heated up to 100°C and it did not show a change of physical state.

Dehydrogenation of B-N-H materials is generally compared at e.g. 200 °C. At such a temperature, the weight loss for **2** is 5.3 wt%. By ignoring the release of by-products, one may assume the evolution of roughly 3 equiv H<sub>2</sub> (out of a maximum of 6). The dehydrogenation extent of **2** is lower than that of amidoboranes [11,30,39-41] and hydrazinidoboranes [17,20,22] (Table 2). The destabilization effect of Ca<sup>2+</sup> is less important than for Li<sup>+</sup>, Na<sup>+</sup> and K<sup>+</sup>. This is confirmed by the FTIR spectrum of the thermolytic residue, denoted **3**, forming upon heating **2** up to 200°C (Figure 8): the B–H and N–H vibration bands are weakened and broadened in comparison to those of **2**, but they are still relatively high in comparison to those observed for polymeric residues formed by extensive dehydrogenation of e.g. AB, like cross-linked

polyiminoborane and polyborazylene [42]. Interestingly, comparable thermolytic properties were reported for  $\text{Ca}(\text{NH}_2\text{BH}_3)_2$ , which liberated about 3.4 equiv  $\text{H}_2$  up to  $200^\circ\text{C}$  [30].

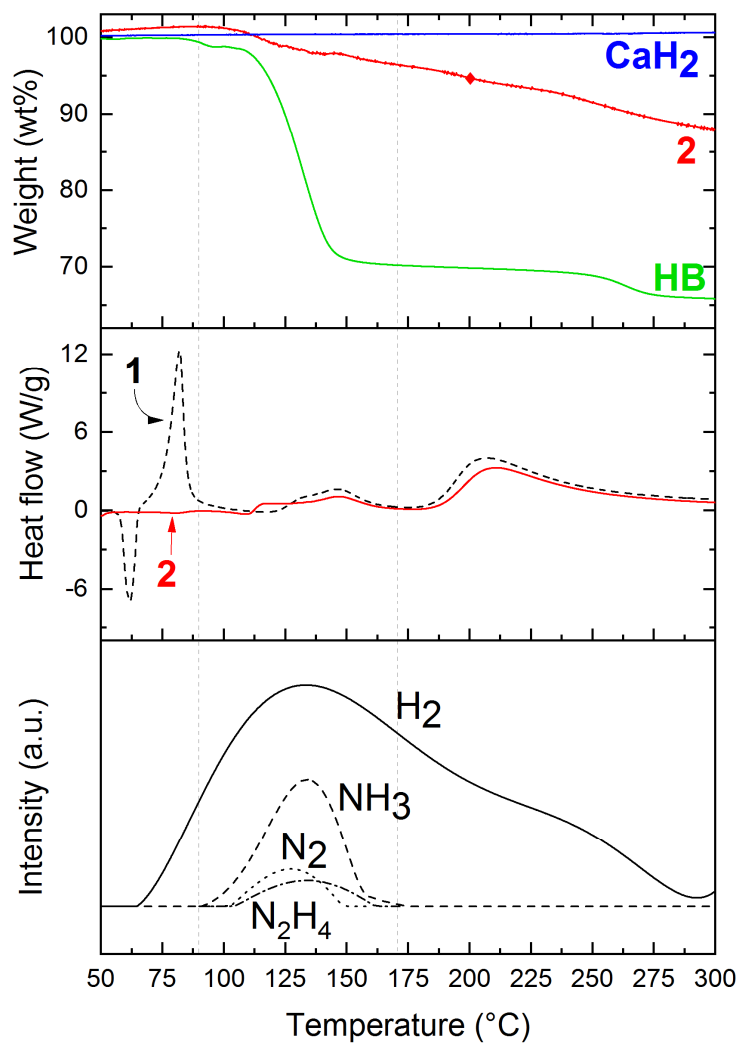

**Figure 9.** (top) Thermogravimetric analysis of **2**, compared to the results obtained for  $\text{CaH}_2$  and pristine HB; the three parts mentioned in the manuscript are delimited by the vertical grey dashed lines; the symbol  $\blacklozenge$  in red placed on the TG curve of **2** indicates the weight loss at  $200^\circ\text{C}$ . (middle) Differential scanning calorimetry analysis of **2**, compared to that of **1**. (bottom) Mass spectrometry analysis of the gas liberated by **2** (with  $\text{H}_2$   $m/z = 2$ ;  $\text{NH}_3$   $m/z = 17$ ;  $\text{N}_2$   $m/z = 28$ ;  $\text{N}_2\text{H}_4$   $m/z = 32$ ).

**Table 2.** Comparison of amidoboranes (MAB =  $\text{MNH}_2\text{BH}_3$ , and  $\text{M}(\text{AB})_2 = \text{M}(\text{NH}_2\text{BH}_3)_2$ ) and hydrazinidoboranes (MHB =  $\text{MN}_2\text{H}_3\text{BH}_3$ , and  $\text{M}(\text{HB})_2 = \text{M}(\text{N}_2\text{H}_3\text{BH}_3)_2$ ), based on their gravimetric H density ( $\rho_{\text{H}}$  in wt%), onset temperature of dehydrogenation ( $T_{\text{onset}}$  in °C) observed by thermogravimetric analysis, dehydrogenation extent at 200°C ( $n_{\text{H}_2}$  per mol of anion  $[\text{NH}_2\text{BH}_3]^-$  or  $\text{N}_2\text{H}_3\text{BH}_3^-$ ), and, in any, the list of the by-products found together with  $\text{H}_2$ .


Family	Compound	$\rho_{\text{H}}$ (wt%)	$T_{\text{onset}}$ (°C)	$n_{\text{H}_2}/n_{\text{anion}}$	By-products	Ref.
MAB	LiAB	13.7	ca. 70	1.9	none	[39]
	NaAB	9.5	ca. 57	2	none or $\text{NH}_3$ <sup>a</sup>	[11,40]
	KAB	7.3	ca. 66	2	none	[41]
$\text{M}(\text{AB})_2$	$\text{Ca}(\text{AB})_2$	10.1	ca. 75	1.7 <sup>b</sup>		[30]
MHB	LiHB	11.7	ca. 70	2.4	$\text{N}_2$ , $\text{NH}_3$	[17]
	NaHB	8.9	ca. 60	2.6	$\text{N}_2$ , $\text{NH}_3$ , $\text{N}_2\text{H}_4$	[20]
	KHB	7.2	ca. 50	3	$\text{N}_2$ , $\text{NH}_3$	[22]
$\text{M}(\text{HB})_2$	$\text{Ca}(\text{HB})_2$	9.3	ca. 64	1.5 <sup>c</sup>	$\text{N}_2$ , $\text{NH}_3$ , $\text{N}_2\text{H}_4$	Present work

<sup>a</sup> There is a contradiction about the purity of  $\text{H}_2$  in ref. [11] vs. ref. [40].  
<sup>b</sup> i.e. 3.4 equiv  $\text{H}_2$  for 1 equiv  $\text{Ca}(\text{AB})_2$ .  
<sup>c</sup> i.e. 3 equiv  $\text{H}_2$  for 1 equiv  $\text{Ca}(\text{HB})_2$ .


The thermolytic residue **3** mentioned above is mostly amorphous (Figure S4). This is typical of any dehydrogenated B-N-H materials. Few diffractions peaks of very low intensity can however be seen. They are possibly attributed to  $\text{CaH}_2$ . Given that  $\text{CaH}_2$  in pristine state is stable up to 300°C (Figure 9), the significant decreases of the  $\text{CaH}_2$  diffraction peaks from **2** to **3** suggests that, between 100 and 200°C,  $\text{CaH}_2$  would have reacted with the  $[\text{NH}_2\text{BH}_3]^-$  anions. The few diffraction peaks may also be interpreted as the occurrence of another minor phase like calcium borohydride  $\text{Ca}(\text{BH}_4)_2$  [43]. **3** is of complex composition as evidenced by the presence of several boron resonances in the  $^{11}\text{B}$  MAS NMR spectrum (Figure 6). One highly hydrogenated environment with  $\text{BH}_4$  (−37 ppm) is attributed to in situ formed  $\text{BH}_4^-$ ; it may belong to  $\text{Ca}(\text{BH}_4)_2$ , which is known to be stable up to ca. 350 °C. Its formation could rationalize the low dehydrogenation extent discussed above. The spectrum also shows  $\text{NBH}_3$ ,  $\text{N}_2\text{BH}_2$ , and/or  $\text{N}_2\text{BH}$  environments (−18.3 and −9.2 ppm). They are typical of oligomeric/polymeric molecules with the structural units  $[-\text{NH}_2\text{BH}_2-]$  and  $[-\text{NHBH}-]$ , and for which the terminal group is  $\text{NBH}_3$  [6]. At positive chemical shift, there is a first signal at +0.5 ppm. It is ascribed to a  $\text{BN}_4$  environment [44]. Tri-coordinated boron elements with  $\text{BN}_3$  (+13.8 ppm) and  $\text{BN}_2\text{H}$  (+20.1 ppm) environments are also distinguished. They are typical of polyborazylene-like compounds [45]. Such a complex composition is problematic for the development of an efficient regeneration path.

Little is known about the dehydrogenation and/or decomposition paths of MHB leading to the aforementioned polymeric residues. The overall path of dehydrocoupling is complex. For example, it has been demonstrated that heteropolar  $\text{H}^{\delta+}\dots\text{H}^{\delta-}$  and homopolar  $\text{H}^{\delta-}\dots\text{H}^{\delta-}/\text{H}^{\delta+}\dots\text{H}^{\delta+}$


reactions competitively occur [46,47] resulting in  $NBH_3$ ,  $N_2BH_2$ ,  $N_2BH$ ,  $BN_3$ ,  $BN_2H$ , and  $BN_4$  environments. Otherwise, we may try to clarify the likely presence of  $Ca(BH_4)_2$  as by-product. We hypothesize the formation of  $[Ca(N_2H_3)_2BH_2]^+[BH_4]^-$  as intermediate by  $Ca^{2+}$ -mediated hydride transfer from  $BH_3$  of one  $[N_2H_3BH_3]^-$  anion to  $BH_3$  of the other anion, the transfer being accompanied by a scission of the N–B bond of the latter anion:



The formation of such transient Ca–H is based on the metal ion assisted hydride transfer mechanism reported for e.g. LiHB [35,48] and  $Ca(NH_2BH_3)_2$  [49]. Dehydrocoupling is suggested to take place via a major path and a minor path (where the participation of the remaining  $CaH_2$  is ignored). For the major path, all of the hydrogens would be likely to participate to  $H_2$  evolution, such as:



With respect to the minor path, only the  $(N_2H_3)_2BH_2$  ligands would be involved:



The entities  $N_2H_3$ , that are twice more concentrated than the  $BH_2$  groups, could then explain the evolution of  $N_2H_4$ ,  $NH_3$  and  $N_2$  as volatile by-products:



To support these mechanisms, further works, implemented by theoretical calculations, are required. Beforehand, it would be preferable to succeed in synthesizing a pure phase of  $Ca(HB)_2$ .

Hügler et al. [12] demonstrated that the binary mixture LiH-HB is preferable to pristine HB owing to faster dehydrogenation kinetics. It is even more attractive than LiHB on the basis of the gravimetric hydrogen density (15 and 11.7 wt% H respectively). A similar comparison can be made for **1**, our binary mixture  $CaH_2$ -2HB, and pure  $Ca(HB)_2$ . (i) They respectively have a gravimetric hydrogen density of 12.05 and 9.3 wt% H. (ii) **1** is able to release  $H_2$  from about 40°C [21]: 2 equiv  $H_2$  are formed by reaction of the two  $H^{\delta-}$  of  $CaH_2$  with one  $H^{\delta+}$  of each HB molecule. Assuming that both **1** and  $Ca(HB)_2$  liberate 3 equiv  $H_2$  from about 100 to 200°C, the  $H_2$  release capacity of **1** is then higher, with 5 equiv  $H_2$  (i.e. 7.5 wt% H released). (iii) The weight loss at 200°C determined by TG analysis is 15.5 wt% for **1**, which supposes an important amount of  $N_2H_4$  probably due to

some unreacted HB. Superior H<sub>2</sub> purity could be expected provided that improvements in the sample preparation (further optimization of the milling, mixing using an anhydrous solvent, etc.) are made. What is clear from this short comparative analysis is that any further work should focus on a pure phase of Ca(HB)<sub>2</sub> as well as on the binary mixture CaH<sub>2</sub>-2HB.

## 4. Conclusion

In situ synchrotron thermodiffraction experiments, coupled with DSC analyses, allowed us to synthesize the hitherto elusive calcium hydrazinidoborane Ca(N<sub>2</sub>H<sub>3</sub>BH<sub>3</sub>)<sub>2</sub>. From a binary mixture of calcium hydride CaH<sub>2</sub> and two equivalents of hydrazine borane N<sub>2</sub>H<sub>4</sub>BH<sub>3</sub>, calcium hydrazinidoborane (monoclinic, s.g. *Ic*) forms above 45°C, especially at around 60°C, the temperature at which HB has melted and is liquid. The as-obtained sample is actually a mixture of Ca(N<sub>2</sub>H<sub>3</sub>BH<sub>3</sub>)<sub>2</sub> as the main phase and some unreacted CaH<sub>2</sub>. Beyond 70°C, the diffraction peaks of Ca(N<sub>2</sub>H<sub>3</sub>BH<sub>3</sub>)<sub>2</sub> decay and they cannot be seen above 97°C anymore. This suggests the decomposition of the new phase, which was confirmed by thermal analyses. The calcium hydrazinidoborane-rich solid dehydrogenates within the temperature range 90-170°C, and some decomposition into volatile by-products (N<sub>2</sub>, NH<sub>3</sub> and N<sub>2</sub>H<sub>4</sub>) also takes place. In any event, Ca(N<sub>2</sub>H<sub>3</sub>BH<sub>3</sub>)<sub>2</sub> shows better dehydrogenation properties than the parent N<sub>2</sub>H<sub>4</sub>BH<sub>3</sub>. The thermolytic residue obtained at 200°C is typical of any dehydrogenated B-N-H materials: it is amorphous and of complex composition. As it stands, Ca(N<sub>2</sub>H<sub>3</sub>BH<sub>3</sub>)<sub>2</sub> may be regarded as having a potential for hydrogen storage but additional works, notably targeting a pure phase, are required. This is all the more important as further efforts might open other opportunities (e.g. boron nitride ceramics).

## Acknowledgments

The authors thank: the French State *via* the ANR (Agence Nationale de la Recherche) and the program “Investissements d’Avenir” with the reference ANR-10-LABX-05-01; the Région Languedoc-Roussillon and the program “Chercheur(se)s d’Avenir 2013” (project C3 / 2013 008555); and the Institut Carnot Chimie Balard Cirimat (project 408-15AC1). The authors also thank Dr. Jean-Fabien Petit (Univ Montpellier) who contributed to the first experiments towards

the synthesis of **2**, Dr. Fabrice Salles (CNRS) who was of help during the synchrotron X-ray thermodiffraction experiments, and Dr. Danielle Laurencin (CNRS) for her help in the  $^{43}\text{Ca}$  MAS NMR analyses.

## References

- [1] Umegaki T, Yan JM, Zhang XB, Shioyama H, Kuriyama N, Xu Q. Boron- and nitrogen-based chemical hydrogen storage materials. *Int J Hydrogen Energy* 2009;34:2303-11.
- [2] Li H, Tang Q, Chen X, Shore SG. Ammonia borane, past as prolog. *J Organomet Chem* 2014;751:60-6.
- [3] Demirci UB. Ammonia borane, a material with exceptional properties for chemical hydrogen storage. *Int J Hydrogen Energy* 2017;42:9978-10013.
- [4] Akbayrak S, Özkar S. Ammonia borane as hydrogen storage materials. *Int J Hydrogen Energy* 2018;43:18592-606.
- [5] Chiriac R, Toche F, Demirci UB, Krol O, Miele P. Ammonia borane decomposition in the presence of cobalt halides. *Int J Hydrogen Energy* 2011;36:12955-64.
- [6] Al-Kukhun, Hwang HT, Varma A. Mechanistic studies of ammonia borane dehydrogenation. *Int J Hydrogen Energy* 2013;38:169-79.
- [7] Roy B, Hajari A, Kumar V, Manna J, Sharma P. Kinetic model analysis and mechanistic correlation of ammonia borane thermolysis under dynamic heating conditions. *Int J Hydrogen Energy* 2018;43:10386-95.
- [8] Petit JF, Demirci UB. Discrepancy in the thermal decomposition/dehydrogenation of ammonia borane screened by thermogravimetric analysis. *Int J Hydrogen Energy* 2019;44:14201-6.
- [9] Chua YS, Chen P, Wu G, Xiong Z. Development of amidoboranes for hydrogen storage. *Chem Commun* 2011;47:5116-29.
- [10] Owarzany R, Leszczyński PJ, Fijalkowski KJ, Grochala W. Mono- and bimetallic amidoboranes. *Crystals* 2016;6:88.
- [11] Xiong Z, Wu G, Chua YS, Hu J, He T, Xu W, Chen P. Synthesis of sodium amidoborane ( $\text{NaNH}_2\text{BH}_3$ ) for hydrogen production. *Energy Environ Sci* 2008;1:360-3.
- [12] Hügle T, Kühnel MF, Lentz D. Hydrazine borane: a promising hydrogen storage material. *J Am Chem Soc* 2009;131:7444-6.
- [13] Moury R, Moussa G, Demirci UB, Hannauer J, Bernard S, Petit E, van der Lee A, Miele P. Hydrazine borane: synthesis, characterization, and application prospects in chemical hydrogen storage. *Phys Chem Chem Phys* 2012;14:1768-77.
- [14] Moury R, Demirci UB. Hydrazine borane and hydrazinidoboranes as chemical hydrogen storage materials. *Energies* 2015;8:3118-41.



- [15] Aichouche A, Bouhadda Y, Bououdina M, Benyelloul K, Bentría B. The destabilising effect of alkali metal (Na and K) of hydrazine-borane  $N_2H_4BH_3$  for hydrogen storage: Ab-initio study. *Int J Hydrogen Energy* 2018;43:14520-31.
- [16] Qian Z, Pathak B, Ahuja R. Energetic and structural analysis of  $N_2H_4BH_3$  inorganic solid and its modified material for hydrogen storage. *Int J Hydrogen Energy* 2013;38:6718-25.
- [17] Wu H, Zhou W, Pinkerton FE, Udovic TJ, Yildirim T, Rush JJ. Metal hydrazinoborane  $LiN_2H_3BH_3$  and  $LiN_2H_3BH_3 \cdot 2N_2H_4BH_3$ : crystal structures and high-extent dehydrogenation. *Energy Environ Sci* 2012;5:7531-5.
- [18] Moury R, Demirci UB, Ban V, Filinchuk Y, Ichikawa T, Zeng L, Goshome K, Miele P. Lithium hydrazinidoborane: a polymorphic material with potential for chemical hydrogen storage. *Chem Mater* 2014;26:3249-55.
- [19] Moury R, Robeyns K, Filinchuk Y, Miele P, Demirci UB. *In situ* thermodiffraction to monitor synthesis and thermolysis of hydrazine borane-based materials. *J Alloys Compd* 2016;659:210-6.
- [20] Moury R, Demirci UB, Ichikawa T, Filinchuk Y, Chiriac R, van der Lee A, Miele P. Sodium hydrazinidoborane: a chemical hydrogen-storage material. *Chem Sus Chem* 2013;6:667-73.
- [21] Pylypko S, Petit JF, Ould-Amara S, Hdhili N, Taihei A, Chiriac R, Ichikawa T, Cretin M, Miele P, Demirci UB. Metal hydride-hydrazine borane: towards hydrazinidoboranes or composites as hydrogen carriers. *Int J Hydrogen Energy* 2015;40:14975-14884.
- [22] Chua YS, Pei Q, Ju X, Zhou W, Udovic TJ, Wu G, Xiong Z, Chen P, Wu H. Alkali metal hydride modification on hydrazine borane for improved dehydrogenation. *J Phys Chem C* 2014;118:11244-51.
- [23] Castilla-Martinez CA, Granier D, Charmette C, Maurin G, Yot PG, Demirci UB. Rubidium hydrazinidoborane: synthesis, characterization and hydrogen release properties. *Int J Hydrogen Energy*, under revision.
- [24] Boultif A, Louër D. Indexing of powder diffraction patterns for low-symmetry lattices by the successive dichotomy method. *J Appl Cryst* 1991;24:987-93.
- [25] Favre-Nicolin V, Černý R. *FOX*, 'free objects for crystallography': a modular approach to ab initio structure determination from powder diffraction. *J Appl Cryst* 2002;35:734-43.
- [26] Petříček V, Dušek M, Palatinus L. Crystallographic computing system JANA2006: general features. *Z Kristallogr* 2014;229:345-52.

- [27] Rappe AK, Casewit CJ, Colwell KS, Goddard WA, Skiff WM. UFF, a full periodic table force field for molecular mechanics and molecular dynamics simulations. *J Am Chem Soc* 1992;114:10024-35.
- [28] Rappe AK, Goddard III WA. Charge equilibration for molecular dynamics simulations. *J Phys Chem* 1991;95:3358-63.
- [29] Takeshita HT, Oishi T, Kuriyama N. Disproportionation of  $\text{CaNi}_3$  hydride: formation of new hydride,  $\text{CaNiH}_3$ . *J Alloys Compd* 2002;333:266-73.
- [30] Wu H, Zhou W, Yildirim T. Alkali and alkaline-earth metal amidoboranes: structure, crystal chemistry, and hydrogen storage properties. *J Am Chem Soc* 2008;130:14834-9.
- [31] Leardini F, Ares JR, Bodega J, Valero-Pedraza MJ, Banares M, Fernandez JF, Sanchez C. Hydrogen desorption behavior of calcium amidoborane obtained by reactive milling of calcium hydride and ammonia borane. *J Phys Chem C* 2012;116:24430-5.
- [32] Senker J, Muller M, Press W, Muller P, Mayer HM, Ibberson RM. Reorientational dynamics of amide ions in isotopic phases of strontium and calcium amide. 1. Neutron diffraction experiments. *J Phys Chem B* 1998;102:931-40.
- [33] Miwa K, Aoki M, Noritake T, Ohba N, Nakamori Y, Towata SI, Züttel A, Orimo SI. Thermodynamical stability of calcium borohydride  $\text{Ca}(\text{BH}_4)_2$ . *Phys Rev B* 2006;74:155122.
- [34] Luedtke AT, Autrey T. Hydrogen release studies of alkali amidoboranes. *Inorg Chem* 2010;49:3905-10.
- [35] Li Z, He T, Wu G, Chen W, Chua YS, Guo J, Xie D, et al. Synthesis, structure and the dehydrogenation mechanism of calcium amidoborane hydrazinates. *Phys Chem Chem Phys* 2016;18:244-51.
- [36] Dupree R, Howes AP, Kohn SC. Natural abundance solid state  $^{43}\text{Ca}$  NMR. *Chem Phys Lett* 1997;276:399-404.
- [37] Laurencin D, Smith ME. Development of  $^{43}\text{Ca}$  solid state NMR spectroscopy as a probe of local structure in inorganic and molecular materials. *Prog Nucl Magn Reson Spectrosc* 2013;68:1-40.
- [38] Li T, Zhang JG. Theoretical study of the metal-controlled dehydrogenation mechanism of  $\text{MN}_2\text{H}_3\text{BH}_3$  ( $\text{M} = \text{Li}, \text{Na}, \text{K}$ ): a new family of hydrogen storage material. *J Phys Chem A* 2018;122:1344-9.

- [39] Xia G, Chen J, Sun W, Tan Y, Guo Z, Liu H, Yu X. Well-dispersed lithium amidoborane nanoparticles through nanoreactor engineering for improved hydrogen release. *Nanoscale* 2014;6:12333-9.
- [40] Fijalkowski KJ, Grochala W. Substantial emission of NH<sub>3</sub> during thermal decomposition of sodium amidoborane, NaNH<sub>2</sub>BH<sub>3</sub>. *J. Mater. Chem.* 2009;19:2043-50.
- [41] Diyabalanage HVK, Nakagawa T, Shrestha RP, Semelsberger TA, Davis BL, Scott BL, Burrell AK, et al. Potassium(I) amidotrihydroborate: structure and hydrogen release. *J. Am. Chem. Soc.* 2010;132:11836-7.
- [42] Fazen PJ, Remsen EE, Beck JS, Carroll PJ, McGhie AR, Sneddon LG. Synthesis, properties, and ceramic conversion reactions of polyborazylene. A high-yield polymeric precursor to boron nitride. *Chem Mater* 1995;7:1942-56.
- [43] Kim JH, Jin SA, Shim JH, Cho Y W. Thermal decomposition behavior of calcium borohydride Ca(BH<sub>4</sub>)<sub>2</sub>. *J Alloys Compd* 2008;461:L20-2.
- [44] Kobayashi T, Gupta S, Caporini MA, Pecharsky VK, Pruski M. Mechanism of solid-state thermolysis of ammonia borane: a <sup>15</sup>N NMR study using fast magic-angle spinning and dynamic nuclear polarization. *J Phys Chem C* 2014;118:19548-55.
- [45] Roy B, Hajari A, Manna J, Sharma P. Supported ammonia borane decomposition through enhanced homopolar B–B coupling. *Dalton Trans* 2018;47:6570-9.
- [46] Wolstenholme DJ, Traboulsee KT, Hua, Y, Calhoun LA, McGrady GS. Thermal desorption of hydrogen from ammonia borane: unexpected role of homopolar B–H···H–B interactions. *Chem Commun* 2012;48:2597-9.
- [47] Tan Y, Chen X, Chen J, Gu G, Yu X. The decomposition of α-LiN<sub>2</sub>H<sub>3</sub>BH<sub>3</sub>: an unexpected hydrogen release from a homopolar proton–proton pathway. *J Mater Chem A* 2014;2:15627-32.
- [48] Banu T, Sen K, Ash T, Das AK. Dehydrogenation of lithium hydrazinidoborane: insight from computational analysis. *Int J Hydrogen Energy* 2016;41:18953-162.
- [49] Kim DY, Lee HM, Seo J, Shin SK, Kim KS. Rules and trends of metal cation driven hydride-transfer mechanisms in metal amidoboranes. *Phys Chem Chem Phys* 2010, 12, 5446-53.

