



Closing the hydrogen cycle with the couple sodium borohydride-methanol, via the formation of sodium tetramethoxyborate and sodium metaborate

Kübra Aydın, Büşra Kulakli, Bilge Coşkuner Filiz, Damien Alligier, Umit Demirci, Aysel Kantürk Figen

► To cite this version:

Kübra Aydın, Büşra Kulakli, Bilge Coşkuner Filiz, Damien Alligier, Umit Demirci, et al.. Closing the hydrogen cycle with the couple sodium borohydride-methanol, via the formation of sodium tetramethoxyborate and sodium metaborate. International Journal of Energy Research, 2020, 44 (14), pp.11405-11416. 10.1002/er.5761 . hal-03544935

HAL Id: hal-03544935

<https://hal.umontpellier.fr/hal-03544935>

Submitted on 3 Oct 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Closing the hydrogen cycle with the couple sodium borohydride-methanol, via the formation of sodium tetramethoxyborate and sodium metaborate

Running title: **Closing the hydrogen cycle with sodium borohydride-methanol**

Kübra Aydın¹, Büşra N. Kulaklı¹, Bilge Coşkuner Filiz², Damien Alligier³, Umit B. Demirci³, Aysel Kantürk Figen^{1*}

¹Department of Chemical Engineering, Yildiz Technical University, İstanbul, Turkey

²Science and Technology Application and Research Center, Yildiz Technical University, İstanbul, Turkey

³Institut Européen des Membranes, IEM – UMR 5635, ENSCM, CNRS, Univ Montpellier, Montpellier, France

* Corresponding author: akanturk@yildiz.edu.tr; ayselkanturk@gmail.com; +90 212 383 47 28

Abstract

Methanolysis of sodium borohydride (NaBH_4) is one of the methods efficient enough to release, on demand, the hydrogen stored in the hydride as well as in 4 equivalents of methanol (CH_3OH). It is generally reported that, in methanolysis, sodium tetramethoxyborate ($\text{NaB}(\text{OCH}_3)_4$) forms as single component of the spent fuel. It is however necessary to clearly investigate some critical aspects related to it. We first focused on the methanolysis reaction where NaBH_4 was reacted with 2, 4, 8, 16 or 32 equivalents of CH_3OH . With 2 equivalents of CH_3OH , the conversion of NaBH_4 is not complete. With 4 to 32 equivalents of CH_3OH , NaBH_4 is totally methanolized (conversion of 100%). The best conditions are those involving 4 equivalents of CH_3OH as they offer the highest effective gravimetric hydrogen storage capacity with 4.8 wt%, an attractive H_2 generation rate with $331 \text{ mL}(\text{H}_2) \text{ min}^{-1}$ – a performance achieved without any catalyst –, and the formation of $\text{NaB}(\text{OCH}_3)_4$ as single product as identified by XRD, FTIR and NMR. We then focused on the transformation of this product $\text{NaB}(\text{OCH}_3)_4$ into sodium metaborate (NaBO_2), via the formation of sodium tetrahydroxyborate ($\text{NaB}(\text{OH})_4$). $\text{NaB}(\text{OCH}_3)_4$ is easily transformed in water, by hydrolysis, at 80°C and for 90 min, into $\text{NaB}(\text{OH})_4$ and 4 equivalents of CH_3OH . In doing so, the cycle with

CH₃OH is closed. Subsequently, NaB(OH)₄ is recovered and converted into NaBO₂ under heating at 500 °C. This reaction liberates 4 equivalents of H₂O, which allows to close the cycle with water. Based on these achievements, we have finally proposed a triangular recycling scheme aiming at closing the cycle with the protic reactants of the aforementioned reactions. This scheme may be used as base for implementing a closed cycle with the couple NaBH₄-CH₃OH.


Keywords

Methanolysis; Recycling; Sodium borohydride; Sodium metaborate; Sodium tetramethoxyborate; Spent fuel

1. Introduction

Hydrogen, owing to its clean nature and high energy density, is clearly one of the most attractive sustainable energy technologies [1]. Hydrogen has grown up very quickly. However, its deployment is confronted with a number of issues touching the whole chain of the so-called “hydrogen economy”. One of the main roadblocks concerns its storage [2]. Various solutions (physical and chemical) have been explored within the past decades [3,4] and chemical hydrogen storage has shown to face a very positive outlook going forward [5–7].

As chemical hydrogen storage material, sodium borohydride (NaBH_4) has been widely investigated as it is considered as a reliable candidate for mobile applications [2], especially because it carries 10.8 wt% of (atomic) hydrogen (in hydridic form) and is able to readily release (molecular) hydrogen by reaction with water (by hydrolysis [8]) or methanol (by methanolysis [9]) at ambient conditions:



The reaction, e.g. the hydrolysis one, is spontaneous ($\Delta H = -217 \text{ kJ mol}^{-1}$ at 25°C) [10] and the solution is generally stabilized by increasing the pH beyond 11 (alkaline conditions) [11]. The use of a heterogeneous (metallic) catalyst is required to catalyze the release of hydrogen by hydrolysis [12]. The research field dedicated to NaBH_4 has mainly focused on finding the best catalyst whereas other crucial aspects (by-products, scaling up, among others) have been clearly under-investigated [13].

One of the main challenges with NaBH_4 is related to the by-product, i.e. sodium tetrahydroxyborate (NaB(OH)_4) in hydrolysis or sodium tetramethoxyborate ($\text{NaB(OCH}_3)_4$) in methanolysis. Recycling it to regenerate NaBH_4 is of importance for closing the hydrogen cycle and for the implementation of the technology. In the field of hydrolysis, a number of studies have focused on identification of the hydrolytic (intermediate and final) by-products [14–16] as well as on regeneration options [17–20], and it may be concluded that the challenge is

enormous. Using methanol for dehydrogenating NaBH_4 has advantages over the use of water. One of them is related to the nature of the by-product. In methanolysis (Eq. 2), $\text{NaB}(\text{OCH}_3)_4$ forms [21]. Unlike $\text{NaB}(\text{OH})_4$ [22], $\text{NaB}(\text{OCH}_3)_4$ does not have the propensity to readily polymerize into polyborates [23,24], avoiding then their precipitation that are known to cause blocking of pipes and catalyst poisoning [25]. Another attractive feature with $\text{NaB}(\text{OCH}_3)_4$ is that it is one of the intermediate products of the $\text{NaB}(\text{OH})_4$ regeneration process developed by Kemmitt et al. [26]. According to this process, $\text{NaB}(\text{OH})_4$ is first dehydrated into NaBO_2 , then NaBO_2 is reacted with methanol to form $\text{NaB}(\text{OCH}_3)_4$, and finally $\text{NaB}(\text{OCH}_3)_4$ is reduced into NaBH_4 in the presence of sodium alanate NaAlH_4 in refluxing diglyme. Yet, in methanolysis, $\text{NaB}(\text{OCH}_3)_4$ forms directly (Eq. 2), which then allows getting a cheaper process (free of the two steps of dehydration and methoxylation). To our knowledge, the open literature dedicated to methanolysis of NaBH_4 mainly deals with reaction parameters [27–30], catalysts [27,31–33], and kinetics [23,29,30]. The catalysis topic has been disproportionately investigated with a large number of possible catalysts reported so far [34]. Examples of recent catalysts are as follows: supported cobalt [35–37] and nickel [38] and bimetallics [39,40], TiO_2 [41], metallurgic sludge [42], polymer-based systems (e.g. microgels) [43–46], treated microalgae [47,48] and other natural materials like spent coffee [49,50]. With respect to the by-products like $\text{NaB}(\text{OCH}_3)_4$, very few reports focused on their identification and their solid-state structure. Fernandes et al., who primarily investigated the effect of methanol on the kinetics of hydrolysis of NaBH_4 for methanol-water mixtures, showed that $\text{NaB}(\text{OCH}_3)_4$ is only obtained in the absence of water [21]. Huynh et al. isolated and characterized a solid-state methanolysis by-product [51]. By XRD analyses, a derivative of $\text{NaB}(\text{OCH}_3)_4$ was found; the following structure was suggested: $[\text{Na}_2(\text{B}(\text{OCH}_3)_4)_2(\text{CH}_3\text{OH})_2]_4$. Its stability in water was scrutinized; it was observed that hydrolysis takes place resulting in the formation of a hydrated sodium tetraborate salt with the structure $\text{Na}_2[\text{B}_4\text{O}_5(\text{OH})_4] \cdot 8/3\text{H}_2\text{O}$. In this way, methanol (CH_3OH) was recovered.

In such a context, our efforts have focused on methanolysis of NaBH_4 , specifically on the by-products stemming from this reaction. For a technology that has commercial objectives, implying then large volumes of spent fuel, it is necessary to better understand the by-products as well as to think about economically viable recycling processes. We performed a systematic work on spent fuel stemming from the methanolysis of NaBH_4 . The reaction was performed

at the scale of few grams, unlike what is generally reported in the literature, in order to be closer to the technological application. In addition, the reaction was proceeded at different $\text{NaBH}_4/\text{CH}_3\text{OH}$ ratios to check the nature of the spent fuel depending on the amount of CH_3OH and to find the suitable conditions for implementation. Our results have shown the formation of $\text{NaB}(\text{OCH}_3)_4$ only for the ratio 4, which corresponds to the stoichiometric conditions and is the optimal one for a conversion of 100% of NaBH_4 with attractive H_2 generation rates ($331 \text{ mL}(\text{H}_2) \text{ min}^{-1}$). Otherwise, the methanolysis products obtained for the other ratios, namely 2, 8, 16 and 32, were recovered to be analyzed and identified. In a second part of the work, we analyzed the hydrolytic evolution of $\text{NaB}(\text{OCH}_3)_4$ at ambient conditions. It was found to evolve into 4 equivalents of CH_3OH , for which the close is thus closed, and into $\text{NaB}(\text{OH})_4$. The latter product was separated and used to highlight the experimental conditions of its transformation into NaBO_2 . In that respect, the appropriate conditions to transform $\text{NaB}(\text{OCH}_3)_4$ into NaBO_2 while recovering CH_3OH have been defined and are discussed in the form of a triangle recycling scheme. This is reported herein.

2. Experimental procedure

Sodium borohydride (NaBH_4 ; $\geq 98\%$ purity Merck) and anhydrous methanol (CH_3OH ; $\geq 99.9\%$ Sigma Aldrich) were used as received. They were stored under inert atmosphere.


Methanolysis by-products were prepared as follows. NaBH_4 (3 g) was transferred in a three-neck flask (100 mL). Hydrogen evolution (Eq. 2) was started by adding a volume of methanol. The amount of the alcohol was varied such as $x = 2, 4, 8, 16, 32$, where x is the mole number of CH_3OH per mole of NaBH_4 . In other words, the reaction was stoichiometric for $x = 4$ (Eq. 2); we performed one experiment at sub-stoichiometry ($x = 2$), and three other ones at over-stoichiometry ($x = 8, 16, 32$). The reaction temperature was set at $20 \pm 2^\circ\text{C}$. The three-neck flask was connected to an inverted burette (to measure the volume of the evolving H_2), via a cold trap used to condensate any vapor.

After the H_2 evolution experiment, the methanolysis spent fuel was recovered. A white solid was obtained for $x = 2, 4$ and 8. For $x = 16$, a white viscous liquid was found to form, and the

excess of CH₃OH was removed as follows. The liquid was held at room temperature (under a hood) for 72 h, leading to the formation of white solid powder. For $x = 32$, a colorless liquid was obtained. After extraction of CH₃OH in excess in a similar way, a white solid powder was recovered. The powders were put under vacuum at 40 °C before they were stored in a desiccator. Their morphology was scrutinized by scanning electron microscope (SEM, Zeiss EVO® LS 10).

The crystal structure of the white solid powders was analyzed by powder X-ray diffraction (XRD; Philips Panalytical X'Pert-Pro, CuK α). Pattern matching was performed using the database available proposed by the PANalytical X'Pert HighScore Plus (PDF-4 2018 RDB) software. The molecular structure was investigated by Fourier transform infrared spectroscopy (FTIR, ATR equipped Perkin Elmer Spectrum One, 4 cm⁻¹). The samples were analyzed by ¹¹B nuclear magnetic resonance (NMR) spectroscopy (Bruker AVANCE-300; probe head BBO10, 96.29 MHz, D₂O or CD₃CN in a capillary tube). Anhydrous N,N-dimethylformamide (HCON(CH₃)₂, Merck) was used to dissolve the solids. Some of the samples were further analyzed by Raman spectroscopy (Horiba Jobin Yvon LabRAM 1B; laser Ar/Kr 100 mW 647.1 nm).

Solid NaB(OCH₃)₄ (recovered for the experiment such as $x = 4$) were then put in water to investigate their possible evolution into e.g. NaB(OH)₄ by hydrolysis:



Typically, NaB(OCH₃)₄ (2.46 g) and H₂O (1.25 g) were loaded in a glass batch reactor. The reaction mixture was heated at 80 ± 2 °C, under stirring (500 rpm), and for 90 min. Upon hydrolysis, the slurry was isolated and dried at 60 °C under vacuum atmosphere for 4 h. The as-obtained white solid was analyzed by XRD. Its thermal stability was analyzed by thermogravimetric (TG) analysis and differential thermal (DT) analysis (SII Nanotechnology – SII6000 Exstar TG/DTA 6300; aluminum crucible; temperature range of 50-700°C; heating rate of 10°C min⁻¹) under either oxidative (O₂) or inert (N₂) atmosphere. These TG and DT analyses allowed us choosing the temperatures 300 and 500 °C for calcination of the hydrolysis white

solids; alumina high temperature crucibles were used. The as-calcined solids were analyzed by XRD. The formation of NaBO₂ was actually targeted:



Based on Eq. 3, CH₃OH was predicted to form. It was identified by analyzing the slurry using gas chromatography (Perkin Elmer Clarus 580 GC apparatus with split injector and FID detector; 30 m column ID BPX5 with i.d. and film thickness of 0.25 mm and 0.25 μm respectively). The oven temperature program was as follows: initial temperature of 40 °C; heating rate of 15 °C min⁻¹ until 70°C; 3 min at 70 °C; heating rate of 45 °C min⁻¹ until 250 °C; 5 min at 250 °C. The injector and detector temperatures were, respectively, 100 and 300 °C. The flow rate of the carrier gas (H₂) was set at 0.5 mL min⁻¹.

3. Result and Discussion

3.1. Towards sodium tetramethoxyborate NaB(OCH₃)₄

At sub-stoichiometric and stoichiometric conditions, i.e. for $x = 2$ and $x = 4$ (Eq. 2), a solid formed by methanolysis of NaBH₄. In the former case, the presence of some unreacted NaBH₄ is likely. A repeated experiment where the volume of H₂ was collected showed a partial conversion of NaBH₄, calculated to be as low as about 40% (Figure S1). This is also consistent with the NMR, XRD and FTIR results reported hereafter. In the case of $x = 4$, all of the NaBH₄ are ideally supposed to react with 4 equiv CH₃OH to form NaB(OCH₃)₄. This was verified by measuring the volume of the generated H₂ (Figure S1); the H₂ generation rate was calculated (for a conversion ≤ 50%) to be 331 mL(H₂) min⁻¹. A solid was also recovered upon the completion of the reaction involving $x = 8$. The three solids were observed by SEM (Figures S2 to S4). They consist of an irregularly-shaped matrix. The surface of the solids obtained for $x = 2$ is rougher, likely because of the presence of some unreacted NaBH₄. The surface of the solids obtained for $x = 4$ and $x = 8$ are smoother and comparable, and they may indicate similar products. A white viscous liquid was obtained for $x = 16$, and for the higher ratio, $x = 32$, a colorless liquid was recovered. Actually, at over-stoichiometric conditions, the excess of methanol, that is, the fraction that did not react with NaBH₄, acts as solvent. This excess of methanol was then extracted and white solids were recovered. By SEM (Figures S5 and S6),

smaller structures (about 400-600 nm) were observed. They are irregularly-shaped and agglomerated. The smaller size may be a result of the solvent extraction and the related crystallization of the methanolysis product.

The methanolysis solid by-products were first considered for analysis by ^{11}B NMR spectroscopy. D_2O as deuterated solvent was found to be inappropriate because of e.g. bubbling of the solid obtained for $x = 2$. Note that this confirmed the presence of some unreacted NaBH_4 (quintet at -39.2 ppm) upon hydrolysis in sub-stoichiometric conditions. N,N -Dimethylformamide is a good solvent for NaBH_4 , and the borates are also slightly soluble in it. It was therefore used to dissolve the methanolysis solid by-products. The ^{11}B NMR analyses were performed using CD_3CN as deuterated solvent (Figure 1). The presence of some unreacted NaBH_4 for the reaction at $x = 2$ (i.e. sub-stoichiometry) is confirmed. Borates ($\delta = 3$ ppm) formed when methanolysis was performed in stoichiometric and over-stoichiometric conditions (total conversion of NaBH_4). According to Huynh et al. [51], the signal may be ascribed to methanolated methoxyborate like $[\text{Na}_2(\text{B}(\text{OCH}_3)_4)_2(\text{CH}_3\text{OH})_2]_4$.

The solids were analyzed by XRD (Figure 2). The presence of unreacted NaBH_4 (ref. 00-009-0386) for the reaction performed at $x = 2$ is confirmed. No trace of a crystalline phase of $\text{NaB}(\text{OCH}_3)_4$ was detected, suggesting the formation of an amorphous by-product. There are few peaks, of very low intensity, that have not been identified and indexed. Pattern matching has not given any relevant result. They are likely to belong to one or more unidentified intermediate species or to an unidentified product; compounds with one to four B–O bonds (for example $\text{NaBH}_3(\text{OCH}_3)$ and $\text{NaBH}_2(\text{OCH}_3)_2$), including oligomeric borates made of 2 to 5 boron atoms, are possible species. The pattern of the by-product obtained at $x = 4$ well matches that of the referenced structure (ref. 00-012-0863) belonging to $\text{NaB}(\text{OCH}_3)_4$. This is in agreement with the results reported by Fernandes et al. [21]. The XRD patterns of the other by-products (i.e. obtained at $x = 8, 16$ and 32) are different. There are similar to the pattern reported by Huynh et al. [51] found for $[\text{Na}_2(\text{B}(\text{OCH}_3)_4)_2(\text{CH}_3\text{OH})_2]_4$ (tetragonal, s.g. I_4), synthesized by reacting NaBH_4 in an excess of methanol (anhydrous). To sum up our observations, a minimum of 4 equiv CH_3OH is required for methanolysis completion and the reaction results in the formation of $\text{NaB}(\text{OCH}_3)_4$. In an excess of CH_3OH , the by-product is a complex of both $[\text{B}(\text{OCH}_3)_4]^-$ and CH_3OH , like the species $[\text{Na}_2(\text{B}(\text{OCH}_3)_4)_2(\text{CH}_3\text{OH})_2]_4$.

The solids were analyzed by FTIR (Figure 3). The observed bands have been indexed with database available in the literature [52–54]. The spectrum of the solid obtained at $x = 2$ shows well-defined sharp bands at e.g. 2500-2100 cm^{-1} (B–H stretching), ascribed to unreacted NaBH_4 [55]. There are also bands at wavenumbers typical of O–H stretching (3600-3000 cm^{-1}) and B–O stretching (1000-750 cm^{-1}) modes, indicating some conversion of NaBH_4 into a borate intermediate (amorphous to X-ray). The spectrum of the solid obtained at $x = 4$ is comparable to the fingerprint of $\text{NaB}(\text{OCH}_3)_4$ [56]. All of the bands can be ascribed to B–O stretching/deformation, C–O stretching and C–H stretching/deformation modes. The spectra of the solids obtained at $x = 8, 16$ and 32 (Figures 3, and S7 to S9) look like that of a methoxyborate by-product like $\text{NaB}(\text{OCH}_3)_4$. The O–H deformation mode at around 1600 cm^{-1} (as well as the bands due to O–H stretching) indicates the presence of CH_3OH [51], in agreement with the conclusions made from the analysis of the XRD patterns.

The sample obtained at $x = 4$, i.e. $\text{NaB}(\text{OCH}_3)_4$, was selected for further analyses. Its thermal stability was analyzed under oxidative and inert atmospheres (Figure S10). A comparable behavior was found. The sample decomposes starting from 30 °C. It undergoes four successive weight losses up to 700 °C, with a main one between 60 and 300 °C. The total weight loss is slightly higher than 45 wt%. In other words, $\text{NaB}(\text{OCH}_3)_4$ is not thermally stable.

3.2. Towards sodium metaborate NaBO_2

$\text{NaB}(\text{OCH}_3)_4$ (i.e. the solid obtained at $x = 4$) readily reacts with water. Total conversion was found to occur for a $\text{H}_2\text{O}/\text{NaB}(\text{OCH}_3)_4$ molar ratio $n \geq 4$. The formation of CH_3OH was verified by GC–FID (Figure S11). The hydrolytic boron product was heated at 60°C, under vacuum, to remove water. A white solid was recovered.

The hydrolysis solid was analyzed by XRD (Figure 4). Monoclinic $\text{NaB}(\text{OH})_4$ (ref. 04-011-2875) was found to be the main crystallographic phase. The presence of another hydrated borate (e.g. $\text{Na}_2\text{B}_4\text{O}_7 \cdot 5\text{H}_2\text{O}$, ref. 00-007-0277) is likely. The FTIR spectrum (Figure 5) is consistent with the formation of such hydrated borates [57–59]. The ^{11}B NMR spectrum (Figure 6) of the solid dissolved in deuterated water shows two signals at positive chemical shifts suggesting two

borate species [60], which might be due to equilibrium between the BO_3 (due to e.g. H_3BO_3) and BO_4 environments (i.e. $B(OH)_4^-$) [61].

The hydrolysis solid was heated, up to 300°C. The XRD pattern (Figure 4) indicates a lightly crystalline solid. The few peaks of small intensity were found to indicate the formation of $NaBO_2$ (ref. 00-037-0115). However, the presence of crystalline $Na_2B_4O_{10}$ (ref. 00-022-1347) cannot be discarded as suggested by the pattern matching. The FTIR spectrum (Figure 5) shows an evolution towards dehydration, which is featured by O–H bands with decreased intensity. The ^{11}B NMR spectrum (Figure 6) is comparable to that of the sample heated at 60 °C.

A last heat-treatment was performed at 500°C. Only the rhombohedral $NaBO_2$ phase (ref. 01-076-0750) was identified (Figure 4), consistently with ref. [62]. $NaB(OH)_4$ is known to lose structural water from about 150 °C [57], resulting in the formation of $NaBO_2$. Temperatures of $NaBO_2$ formation of 300 and 400 °C were reported [57,62]. This is quite consistent with our XRD observations. The FTIR spectrum is also consistent with this observation (Figure 5). The ^{11}B NMR spectrum (Figure 6) of $NaBO_2$ dissolved in deuterated water shows one signal at 4.5 ppm, ascribed to a BO_4 environments such as for $B(OD)_4^-$.

The solids heated at 60, 300 and 500 °C were analyzed by Raman spectroscopy (Figure 7). The first two solids show bands due to symmetric (700-950 cm^{-1}) and asymmetric (350-1100 cm^{-1}) stretching of B–O bonds. The bands at about 750 cm^{-1} may be attributed to $B(OH)_3$ species, and that at 942 cm^{-1} to $B(OH)_4^-$ [63]. The band peaking at 1076 cm^{-1} , which is the only one observed for the sample heated at 500 °C, is assigned to $NaBO_2$. These results confirm the XRD, FTIR, and NMR data discussed above, that is, the complete transformation of $NaB(OCH_3)_4$ into $NaBO_2$ via $NaB(OH)_4$.

3.3. Towards a neutral cycle with $NaBH_4$

What emerges from the patterns and spectra reported above is that the hydrogen cycle with $NaBH_4$ can be neutral. In other words, the methanolysis by-product could be recycled through a stepwise process to form $NaBH_4$ back. This is illustrated in Figure 8.

Methanolysis of NaBH_4 is an efficient process for H_2 release, resulting in formation of $\text{NaB}(\text{OCH}_3)_4$ as main by-product when the reaction is realized in stoichiometric conditions (Eq. 2). Typically, 1 equiv NaBH_4 reacts with 4 equiv CH_3OH and transforms into 1 equiv $\text{NaB}(\text{OCH}_3)_4$ while liberating 4 equiv H_2 . Such a reaction is very interesting for two reasons. First, all of the atoms are effectively used resulting in an “atom economy” in good agreement with one of the green chemistry principles. Second, the aforementioned stoichiometry implies an effective gravimetric hydrogen capacity of 4.8 wt% for the couple $\text{NaBH}_4\text{-CH}_3\text{OH}$, and this is a clearly promising capacity. In addition, the H_2 generation rate was calculated to be $331 \text{ mL}(\text{H}_2) \text{ min}^{-1}$ (without catalyst), which is one of the best performance for an uncatalyzed solvolysis reaction involving a hydride and a protonic solvent; some examples are shown in Table 1 [21,22,30,64–74].

The as-formed $\text{NaB}(\text{OCH}_3)_4$ can be readily hydrolyzed into $\text{NaB}(\text{OH})_4$, and 4 equiv CH_3OH are generated. The cycle is then neutral in CH_3OH . With respect to $\text{NaB}(\text{OH})_4$, it is easily converted, under heating up to 500°C in our conditions, into NaBO_2 while releasing 2 equiv H_2O . The other 2 equiv H_2O are generated during reduction of NaBO_2 into NaBH_4 . Hence, the cycle is neutral in H_2O .

As mentioned just above, NaBO_2 has to be reduced into NaBH_4 . This may be done by using 4 equiv H_2 or a reducing agent carrying H^- such as MgH_2 [18,75,76]. Another original procedure, recently reported [77], could be to make react NaBO_2 with CO_2 in aqueous solution, the as-forming $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$ and Na_2CO_3 being afterwards ball-milled with Mg under ambient conditions to form NaBH_4 in a yield close to 80 %. In any case, the cycle is then neutral in H_2 . It is worth mentioning that regeneration of NaBH_4 starting from NaBO_2 has been demonstrated, but the processes developed so far need to be further improved to make one/few of them cost-effective [78]. Another challenge, with these processes, will be to develop them while the cycle of each reactant and product is neutral. Otherwise, the scheme of the recycling process could be considered differently for the third part, namely transformation of $\text{NaB}(\text{OH})_4$ into NaBH_4 via NaBO_2 . In the recent years, Ouyang and co-workers reported few regeneration routes using $\text{NaBO}_2 \cdot x\text{H}_2\text{O}$ (with $x = 2$ or 4) as starting borate. Ball-milling $\text{NaBO}_2 \cdot x\text{H}_2\text{O}$ with MgH_2 at room temperature and atmospheric pressure was found to

lead to NaBH_4 back with a yield as high as 90% [79]. In another work, Mg was used instead of MgH_2 and NaBH_4 was regenerated with yields of 64-68% [80]. The formation of NaBH_4 was explained by the involvement of reaction intermediates like MgH_2 and $\text{NaBH}_3(\text{OH})$.

4. Conclusion

In the present work, we have proposed a neutral cycle for the hydrogen storage system based on the couple NaBH_4 - $4\text{CH}_3\text{OH}$. Upon methanolysis, this couple releases 4 equiv H_2 in such a way that the effective gravimetric hydrogen capacity is as high as 4.8 wt%, which is quite attractive from an implementation point of view. It is worth mentioning the H_2 generation rate that has been achieved without any catalyst, namely, 331 $\text{mL}(\text{H}_2) \text{ min}^{-1}$. The methanolysis by-product is $\text{NaB}(\text{OCH}_3)_4$. By using 4 equiv H_2O , $\text{NaB}(\text{OCH}_3)_4$ can be readily hydrolyzed to $\text{NaB}(\text{OH})_4$. The process generates 4 equiv CH_3OH , making the cycle neutral in CH_3OH . Then, $\text{NaB}(\text{OH})_4$ can be converted, under heating up to 500 °C, into NaBO_2 which is the most common starting material for regenerating NaBH_4 . In a further step, NaBO_2 could be reduced into NaBH_4 while using 4 equiv H_2 or e.g. 4 equiv MgH_2 . The cycle would be neutral in H_2 . Each of the $\text{NaB}(\text{OH})_4$ heating and NaBO_2 reduction processes generates 2 equiv H_2O , making the cycle neutral in H_2O also. The cycle summarized above is thus also neutral in the B element; indeed the starting NaBH_4 is targeted to be regenerated by recovering all of the formed $\text{NaB}(\text{OH})_4$ via its total conversion into $\text{NaB}(\text{OH})_4$ and then NaBO_2 . In that respect, all of the atoms involved in this cycle are used and re-used, resulting in an “atom economy” in good agreement with one of the green chemistry principles. In conclusion, the strategy we propose will help us in building a closed pathway from NaBH_4 to its spent fuel without disturbing the environmental balance.

Acknowledgements

This work was supported by TUBITAK (Project no: 218M181) and CAMPUS FRANCE – PHC BOSPHORUS (Project no: 42161TB). UBD and DA thank the Agence Nationale de la Recherche (Project MOBIDIC; ANR-16-CE05-0009).

References

- [1] Saeedmanesh A, Mac Kinnon MA, Brouwer J. Hydrogen is essential for sustainability. *Curr Opin Electrochem* 2018;12:166–81. <https://doi.org/10.1016/j.coelec.2018.11.009>.
- [2] Abe JO, Popoola API, Ajenifuja E, Popoola OM. Hydrogen energy, economy and storage: review and recommendation. *Int J Hydrogen Energy* 2019;44:15072–86. <https://doi.org/10.1016/j.ijhydene.2019.04.068>.
- [3] Müller K, Arlt W. Status and development in hydrogen transport and storage for energy applications. *Energy Technol* 2013;1:501–11. <https://doi.org/10.1002/ente.201300055>.
- [4] Abdalla AM, Hossain S, Nisfindy OB, Azad AT, Dawood M, Azad AK. Hydrogen production, storage, transportation and key challenges with applications: a review. *Energy Convers Manag* 2018;165:602–27. <https://doi.org/10.1016/j.enconman.2018.03.088>.
- [5] Hirscher M, Yartys VA, Baricco M, Bellosta von Colbe J, Blanchard D, Bowman RC, et al. Materials for hydrogen-based energy storage – past, recent progress and future outlook. *J Alloys Compd* 2020;827:153548. <https://doi.org/10.1016/j.jallcom.2019.153548>.
- [6] Kojima Y. Hydrogen storage materials for hydrogen and energy carriers. *Int J Hydrogen Energy* 2019;44:18179–92. <https://doi.org/10.1016/j.ijhydene.2019.05.119>.
- [7] Wang K, Pan Z, Yu X. Metal B-N-H hydrogen-storage compound: development and perspectives. *J Alloys Compd* 2019;794:303–24. <https://doi.org/10.1016/j.jallcom.2019.04.240>.
- [8] Davis RE, Bromels E, Kibby CL. Boron hydrides III. hydrolysis of sodium borohydride in aqueous solution. *J Am Chem Soc* 1962;84:885–92. <https://doi.org/10.1021/ja00865a001>.
- [9] Davis RE, Gottbrath JA. Boron hydrides V. methanolysis of sodium borohydride. *J Am Chem Soc* 1962;84:895–8. <https://doi.org/10.1021/ja00865a003>.
- [10] Kojima Y, Suzuki K, Fukumoto K, Sasaki M, Yamamoto T, Kawai Y, et al. Hydrogen generation using sodium borohydride solution and metal catalyst coated on metal oxide. *Int J Hydrogen Energy* 2002;27:1029–34. [https://doi.org/10.1016/S0360-3199\(02\)00014-9](https://doi.org/10.1016/S0360-3199(02)00014-9).

- 387 [11] Kim JH, Kim KT, Kang YM, Kim HS, Song MS, Lee YJ, et al. Study on degradation of
388 filamentary Ni catalyst on hydrolysis of sodium borohydride. *J Alloys Compd*
389 2004;379:222–7. <https://doi.org/10.1016/j.jallcom.2004.02.009>.
- 390 [12] Brack P, Dann SE, Wijayantha KGU. Heterogeneous and homogenous catalysts for
391 hydrogen generation by hydrolysis of aqueous sodium borohydride (NaBH₄) solutions.
392 *Energy Sci Eng* 2015;3:174–88. <https://doi.org/10.1002/ese3.67>.
- 393 [13] Lang C, Jia Y, Yao X. Recent advances in liquid-phase chemical hydrogen storage. *Energy*
394 *Storage Mater* 2020;26:290–312. <https://doi.org/10.1016/j.ensm.2020.01.010>.
- 395 [14] Kantürk Figen A, Öztürk A, Pişkin S. Process for the conversion of highly caustic spent
396 sodium borohydride fuel. *Res Chem Intermed* 2012;38:2343–54.
397 <https://doi.org/10.1007/s11164-012-0550-9>.
- 398 [15] Hsueh CL, Liu CH, Chen BH, Chen CY, Kuo YC, Hwang KJ, et al. Regeneration of spent-
399 NaBH₄ back to NaBH₄ by using high-energy ball milling. *Int J Hydrogen Energy*
400 2009;34:1717–25. <https://doi.org/10.1016/j.ijhydene.2008.12.036>.
- 401 [16] Stepanov N, Uvarov V, Popov I, Sasson Y. Study of by-product of NaBH₄ hydrolysis and
402 its behavior at a room temperature. *Int J Hydrogen Energy* 2008;33:7378–84.
403 <https://doi.org/10.1016/j.ijhydene.2008.09.052>.
- 404 [17] Qin C, Ouyang L, Wang H, Liu J, Shao H, Zhu M. Regulation of high-efficient regeneration
405 of sodium borohydride by magnesium-aluminum alloy. *Int J Hydrogen Energy*
406 2019;44:29108–15. <https://doi.org/10.1016/j.ijhydene.2019.05.010>.
- 407 [18] Çakanyıldırım Ç, Gürü M. Processing of NaBH₄ from NaBO₂ with MgH₂ by ball milling
408 and usage as hydrogen carrier. *Renew Energy* 2010;35:1895–9.
409 <https://doi.org/10.1016/j.renene.2010.01.001>.
- 410 [19] Kojima Y, Haga T. Recycling process of sodium metaborate to sodium borohydride. *Int*
411 *J Hydrogen Energy* 2003;28:989–93. [https://doi.org/10.1016/S0360-3199\(02\)00173-8](https://doi.org/10.1016/S0360-3199(02)00173-8).
- 412 [20] Li ZP, Morigazaki N, Liu BH, Suda S. Preparation of sodium borohydride by the reaction
413 of MgH₂ with dehydrated borax through ball milling at room temperature. *J Alloys*
414 *Compd* 2003;349:232–6. [https://doi.org/10.1016/S0925-8388\(02\)00872-1](https://doi.org/10.1016/S0925-8388(02)00872-1).
- 415 [21] Fernandes VR, Pinto AMFR, Rangel CM. Hydrogen production from sodium borohydride
416 in methanol–water mixtures. *Int J Hydrogen Energy* 2010;35:9862–8.
417 <https://doi.org/10.1016/j.ijhydene.2009.11.064>.
- 418 [22] Yu L, Matthews MA. Hydrolysis of sodium borohydride in concentrated aqueous

- solution. Int J Hydrogen Energy 2011;36:7416–22.
<https://doi.org/10.1016/j.ijhydene.2011.03.089>.
- [23] Lo CTF, Karan K, Davis BR. Kinetic assessment of catalysts for the methanolysis of sodium borohydride for hydrogen generation. Ind Eng Chem Res 2009;48:5177–84.
<https://doi.org/10.1021/ie8009186>.
- [24] Ocon JD, Tuan TN, Yi Y, de Leon RL, Lee JK, Lee J. Ultrafast and stable hydrogen generation from sodium borohydride in methanol and water over Fe–B nanoparticles. J Power Sources 2013;243:444–50. <https://doi.org/10.1016/j.jpowsour.2013.06.019>.
- [25] Lapeña-Rey N, Blanco JA, Ferreyra E, Lemus JL, Pereira S, Serrot E. A fuel cell powered unmanned aerial vehicle for low altitude surveillance missions. Int J Hydrogen Energy 2017;42:6926–40. <https://doi.org/10.1016/j.ijhydene.2017.01.137>.
- [26] Kemmitt T, Gainsford GJ. Regeneration of sodium borohydride from sodium metaborate, and isolation of intermediate compounds. Int J Hydrogen Energy 2009;34:5726–31. <https://doi.org/10.1016/j.ijhydene.2009.05.108>.
- [27] Xu D, Lai X, Guo W, Zhang X, Wang C, Dai P. Efficient catalytic properties of $\text{SO}_4^{2-}/\text{MxO}_y$ (M=Cu, Co, Fe) catalysts for hydrogen generation by methanolysis of sodium borohydride. Int J Hydrogen Energy 2018;43:6594–602.
<https://doi.org/10.1016/j.ijhydene.2018.02.074>.
- [28] Su CC, Lu MC, Wang SL, Huang YH. Ruthenium immobilized on Al_2O_3 pellets as a catalyst for hydrogen generation from hydrolysis and methanolysis of sodium borohydride. RSC Adv 2012;2:2073. <https://doi.org/10.1039/c2ra01233b>.
- [29] Lo CTF, Karan K, Davis BR. Kinetic studies of reaction between sodium borohydride and methanol, water, and their mixtures. Ind Eng Chem Res 2007;46:5478–84.
<https://doi.org/10.1021/ie0608861>.
- [30] Ramya K, Dhathathreya KS, Sreenivas J, Kumar S, Narasimhan S. Hydrogen production by alcoholysis of sodium borohydride. Int J Energy Res 2013;37:1889–95.
<https://doi.org/10.1002/er.3006>.
- [31] Ali F, Khan SB, Asiri AM. Enhanced H_2 generation from NaBH_4 hydrolysis and methanolysis by cellulose micro-fibrous cottons as metal templated catalyst. Int J Hydrogen Energy 2018;43:6539–50. <https://doi.org/10.1016/j.ijhydene.2018.02.008>.
- [32] Demirci S, Yildiz M, Inger E, Sahiner N. Porous carbon particles as metal-free superior catalyst for hydrogen release from methanolysis of sodium borohydride. Renew Energy

- 2020;147:69–76. <https://doi.org/10.1016/j.renene.2019.08.131>.
- [33] Xu D, Zhang Y, Cheng F, Zhao L. Enhanced hydrogen generation by methanolysis of sodium borohydride in the presence of phosphorus modified boehmite. *Fuel* 2014;134:257–62. <https://doi.org/10.1016/j.fuel.2014.05.071>.
- [34] Özkar S. Transition metal nanoparticle catalysts in releasing hydrogen from the methanolysis of ammonia borane. *Int J Hydrogen Energy* 2020;45:7881–91. <https://doi.org/10.1016/j.ijhydene.2019.04.125>.
- [35] Xu D, Zhang X, Zhao X, Dai P, Wang C, Gao J, et al. Stability and kinetic studies of MOF-derived carbon-confined ultrafine Co catalyst for sodium borohydride hydrolysis. *Int J Energy Res* 2019;43:3702–10. <https://doi.org/10.1002/er.4524>.
- [36] Kaya M, Bekiroğullari M, Saka C. Highly efficient CoB catalyst using a support material based on *Spirulina* microalgal strain treated with ZnCl_2 for hydrogen generation via sodium borohydride methanolysis. *Int J Energy Res* 2019;43:4243–52. <https://doi.org/10.1002/er.4548>.
- [37] Bekiroğullari M, Kaya M, Saka C. Highly efficient Co-B catalysts with *Chlorella Vulgaris* microalgal strain modified using hydrochloric acid as a new support material for hydrogen production from methanolysis of sodium borohydride. *Int J Hydrogen Energy* 2019;44:7262–75. <https://doi.org/10.1016/j.ijhydene.2019.01.246>.
- [38] Wang F, Luo Y, Wang Y, Zhu H. The preparation and performance of a novel spherical spider web-like structure Ru-Ni/Ni foam catalyst for NaBH_4 methanolysis. *Int J Hydrogen Energy* 2019;44:13185–94. <https://doi.org/10.1016/j.ijhydene.2019.01.123>.
- [39] Zhang Y, Zou J, Luo Y, Wang F. Study on preparation and performance of Ru-Fe/GO catalyst for sodium borohydride alcoholysis to produce hydrogen. *Fullerenes, Nanotub Carbon Nanostructures* 2020;1–8. <https://doi.org/10.1080/1536383X.2020.1760849>.
- [40] Tunç N, Rakap M. Preparation and characterization of Ni-M (M: Ru, Rh, Pd) nanoclusters as efficient catalysts for hydrogen evolution from ammonia borane methanolysis. *Renew Energy* 2020;155:1222–30. <https://doi.org/10.1016/j.renene.2020.04.079>.
- [41] Demirci S, Sunol AK, Sahiner N. Catalytic activity of amine functionalized titanium dioxide nanoparticles in methanolysis of sodium borohydride for hydrogen generation. *Appl Catal B Environ* 2020;261:118242. <https://doi.org/10.1016/j.apcatb.2019.118242>.
- [42] Fangaj E, Ali AA, Güngör F, Bektaş S, Ceyhan AA. The use of metallurgical waste sludge as a catalyst in hydrogen production from sodium borohydride. *Int J Hydrogen Energy*

- 2020;45:13322–9. <https://doi.org/10.1016/j.ijhydene.2020.03.043>.
- [43] Sahiner N, Demirci S. Very fast H₂ production from the methanolysis of NaBH₄ by metal-free poly(ethylene imine) microgel catalysts. *Int J Energy Res* 2017;41:736–46. <https://doi.org/10.1002/er.3679>.
- [44] Ari B, Ay M, Sunol AK, Sahiner N. Surface-modified carbon black derived from used car tires as alternative, reusable, and regenerable catalysts for H₂ release studies from sodium borohydride methanolysis. *Int J Energy Res* 2019;43:7159–72. <https://doi.org/10.1002/er.4742>.
- [45] Inger E, Sunol AK, Sahiner N. Catalytic activity of metal-free amine-modified dextran microgels in hydrogen release through methanolysis of NaBH₄. *Int J Energy Res* 2020. <https://doi.org/10.1002/er.5395>.
- [46] Khan SB, Ali F, Asiri AM. Metal nanoparticles supported on polyacrylamide water beads as catalyst for efficient generation of H₂ from NaBH₄ methanolysis. *Int J Hydrogen Energy* 2020;45:1532–40. <https://doi.org/10.1016/j.ijhydene.2019.11.042>.
- [47] Saka C, Kaya M, Bekiroğullari M. Spirulina microalgal strain as efficient a metal-free catalyst to generate hydrogen via methanolysis of sodium borohydride. *Int J Energy Res* 2020;44:402–10. <https://doi.org/10.1002/er.4936>.
- [48] Kaya M. NiB loaded acetic acid treated microalgae strain (*Spirulina Platensis*) to use as a catalyst for hydrogen generation from sodium borohydride methanolysis. *Energy Sources, Part A Recover Util Environ Eff* 2019;41:2549–60. <https://doi.org/10.1080/15567036.2019.1647312>.
- [49] Kaya M. Production of metal-free catalyst from defatted spent coffee ground for hydrogen generation by sodium borohydride methanolysis. *Int J Hydrogen Energy* 2020;45:12731–42. <https://doi.org/10.1016/j.ijhydene.2019.08.013>.
- [50] Kaya M. Evaluating organic waste sources (spent coffee ground) as metal-free catalyst for hydrogen generation by the methanolysis of sodium borohydride. *Int J Hydrogen Energy* 2020;45:12743–54. <https://doi.org/10.1016/j.ijhydene.2019.10.180>.
- [51] Huynh K, Napolitano K, Wang R, Jessop PG, Davis BR. Indirect hydrolysis of sodium borohydride: Isolation and crystallographic characterization of methanolysis and hydrolysis by-products. *Int J Hydrogen Energy* 2013;38:5775–82. <https://doi.org/10.1016/j.ijhydene.2013.03.011>.
- [52] Concha BM, Chatenet M, Coutanceau C, Hahn F. In situ infrared (FTIR) study of the

- borohydride oxidation reaction. *Electrochem Commun* 2009;11:223–6.
<https://doi.org/10.1016/j.elecom.2008.11.018>.
- [53] Lixia Z, Tao Y, Jiang W, Shiyang G. FT-IR and Raman spectroscopic study of hydrated rubidium (cesium) borates and alkali double borates. *Russ J Inorg Chem* 2007;52:1786–92. <https://doi.org/10.1134/S0036023607110241>.
- [54] Jun L, Shuping X, Shiyang G. FT-IR and Raman spectroscopic study of hydrated borates. *Spectrochim Acta Part A Mol Biomol Spectrosc* 1995;51:519–32. [https://doi.org/10.1016/0584-8539\(94\)00183-C](https://doi.org/10.1016/0584-8539(94)00183-C).
- [55] Sljukic B, Santos DMF, Sequeira CAC, Banks CE. Analytical monitoring of sodium borohydride. *Anal Methods* 2013;5:829. <https://doi.org/10.1039/c2ay26077h>.
- [56] Xu D, Zhao L, Dai P, Ji S. Hydrogen generation from methanolysis of sodium borohydride over Co/Al₂O₃ catalyst. *J Nat Gas Chem* 2012;21:488–94. [https://doi.org/10.1016/S1003-9953\(11\)60395-2](https://doi.org/10.1016/S1003-9953(11)60395-2).
- [57] Kantürk Figen A, Sari M, Pişkin S. Synthesis, crystal structure and dehydration kinetics of NaB(OH)₄·2H₂O. *Korean J Chem Eng* 2008;25:1331–7. <https://doi.org/10.1007/s11814-008-0218-8>.
- [58] Zhong H, Ouyang LZ, Ye JS, Liu JW, Wang H, Yao XD, et al. An one-step approach towards hydrogen production and storage through regeneration of NaBH₄. *Energy Storage Mater* 2017;7:222–8. <https://doi.org/10.1016/j.ensm.2017.03.001>.
- [59] Netskina OV, Komova OV, Simagina VI, Odegova GV, Prosvirin IP, Bulavchenko OA. Aqueous-alkaline NaBH₄ solution: the influence of storage duration of solutions on reduction and activity of cobalt catalysts. *Renew Energy* 2016;99:1073–81. <https://doi.org/10.1016/j.renene.2016.08.005>.
- [60] Chandra M, Xu Q. Dissociation and hydrolysis of ammonia-borane with solid acids and carbon dioxide: an efficient hydrogen generation system. *J Power Sources* 2006;159:855–60. <https://doi.org/10.1016/j.jpowsour.2005.12.033>.
- [61] Salentine CG. High-field boron-11 NMR of alkali borates. Aqueous polyborate equilibria. *Inorg Chem* 1983;22:3920–4. <https://doi.org/10.1021/ic00168a019>.
- [62] Kantürk Figen A, Pişkin S. Parametric investigation on anhydrous sodium metaborate (NaBO₂) synthesis from concentrated tincal. *Adv Powder Technol* 2010;21:513–20. <https://doi.org/10.1016/j.appt.2010.01.012>.
- [63] Applegarth L, Pye CC, Cox JS, Tremaine PR. Raman spectroscopic and ab initio

investigation of aqueous boric acid, borate, and polyborate speciation from 25 to 80 °C. Ind Eng Chem Res 2017;56:13983–96. <https://doi.org/10.1021/acs.iecr.7b03316>.

[64] Weng B, Wu Z, Li Z, Yang H, Leng H. Hydrogen generation from noncatalytic hydrolysis of $\text{LiBH}_4/\text{NH}_3\text{BH}_3$ mixture for fuel cell applications. Int J Hydrogen Energy 2011;36:10870–6. <https://doi.org/10.1016/j.ijhydene.2011.06.009>.

[65] Zhang J, Lin F, Yang L, He Z, Huang X, Zhang D, et al. Ultrasmall Ru nanoparticles supported on chitin nanofibers for hydrogen production from NaBH_4 hydrolysis. Chinese Chem Lett 2019. <https://doi.org/10.1016/j.cclet.2019.11.042>.

[66] Yang L, Huang X, Zhang J, Dong H. Protonated Poly(ethylene imine)-Coated Silica Nanoparticles for Promoting Hydrogen Generation from the Hydrolysis of Sodium Borohydride. Chempluschem 2020;85:399–404. <https://doi.org/10.1002/cplu.201900609>.

[67] Keçeli E, Özkaz S. Ruthenium(III) acetylacetonate: A homogeneous catalyst in the hydrolysis of sodium borohydride. J Mol Catal A Chem 2008;286:87–91. <https://doi.org/10.1016/j.molcata.2008.02.008>.

[68] Arzac GM, Fernández A. Hydrogen production through sodium borohydride ethanolysis. Int J Hydrogen Energy 2015;40:5326–32. <https://doi.org/10.1016/j.ijhydene.2015.01.115>.

[69] Saka C, Balbay A. Fast and effective hydrogen production from ethanolysis and hydrolysis reactions of potassium borohydride using phosphoric acid. Int J Hydrogen Energy 2018;43:19976–83. <https://doi.org/10.1016/j.ijhydene.2018.09.048>.

[70] Chen J, Fu H, Xiong Y, Xu J, Zheng J, Li X. MgCl_2 promoted hydrolysis of MgH_2 nanoparticles for highly efficient H_2 generation. Nano Energy 2014;10:337–43. <https://doi.org/10.1016/j.nanoen.2014.10.002>.

[71] Figen AK, Taşçı K. Hydrolysis characteristics of calcium hydride (CaH_2) powder in the presence of ethylene glycol, methanol, and ethanol for controllable hydrogen production. Energy Sources, Part A Recover Util Environ Eff 2016;38:37–42. <https://doi.org/10.1080/15567036.2015.1043473>.

[72] Ramachandran PV, Gagare PD. Preparation of ammonia borane in high yield and purity, methanolysis, and regeneration. Inorg Chem 2007;46:7810–7. <https://doi.org/10.1021/ic700772a>.

[73] Inoue H, Yamazaki T, Kitamura T, Shimada M, Chiku M, Higuchi E. Electrochemical

- hydrogen production system from ammonia borane in methanol solution. *Electrochim Acta* 2012;82:392–6. <https://doi.org/10.1016/j.electacta.2012.05.091>.
- [74] Weng B, Wu Z, Li Z, Yang H. Hydrogen generation from hydrolysis of MNH_2BH_3 and $\text{NH}_3\text{BH}_3/\text{MH}$ ($\text{M}=\text{Li}, \text{Na}$) for fuel cells based unmanned submarine vehicles application. *Energy* 2012;38:205–11. <https://doi.org/10.1016/j.energy.2011.12.012>.
- [75] Hsueh C-L, Liu C-H, Chen B-H, Chen C-Y, Kuo Y-C, Hwang K-J, et al. Regeneration of spent- NaBH_4 back to NaBH_4 by using high-energy ball milling. *Int J Hydrogen Energy* 2009;34:1717–25. <https://doi.org/10.1016/j.ijhydene.2008.12.036>.
- [76] Lang C, Jia Y, Liu J, Wang H, Ouyang L, Zhu M, et al. NaBH_4 regeneration from NaBO_2 by high-energy ball milling and its plausible mechanism. *Int J Hydrogen Energy* 2017;42:13127–35. <https://doi.org/10.1016/j.ijhydene.2017.04.014>.
- [77] Zhu Y, Ouyang L, Zhong H, Liu J, Wang H, Shao H, et al. Closing the loop for hydrogen storage: facile regeneration of NaBH_4 from its hydrolytic product. *Angew Chemie Int Ed* 2020;59:8623–9. <https://doi.org/10.1002/anie.201915988>.
- [78] Ouyang L, Zhong H, Li H-W, Zhu M. A recycling hydrogen supply system of NaBH_4 based on a facile regeneration process: A review. *Inorganics* 2018;6:10. <https://doi.org/10.3390/inorganics6010010>.
- [79] Chen W, Ouyang LZ, Liu JW, Yao XD, Wang H, Liu ZW, et al. Hydrolysis and regeneration of sodium borohydride (NaBH_4) – A combination of hydrogen production and storage. *J Power Sources* 2017;359:400–7. <https://doi.org/10.1016/j.jpowsour.2017.05.075>.
- [80] Ouyang L, Chen W, Liu J, Felderhoff M, Wang H, Zhu M. Enhancing the regeneration process of consumed NaBH_4 for hydrogen storage. *Adv Energy Mater* 2017;7:1700299. <https://doi.org/10.1002/aenm.201700299>.

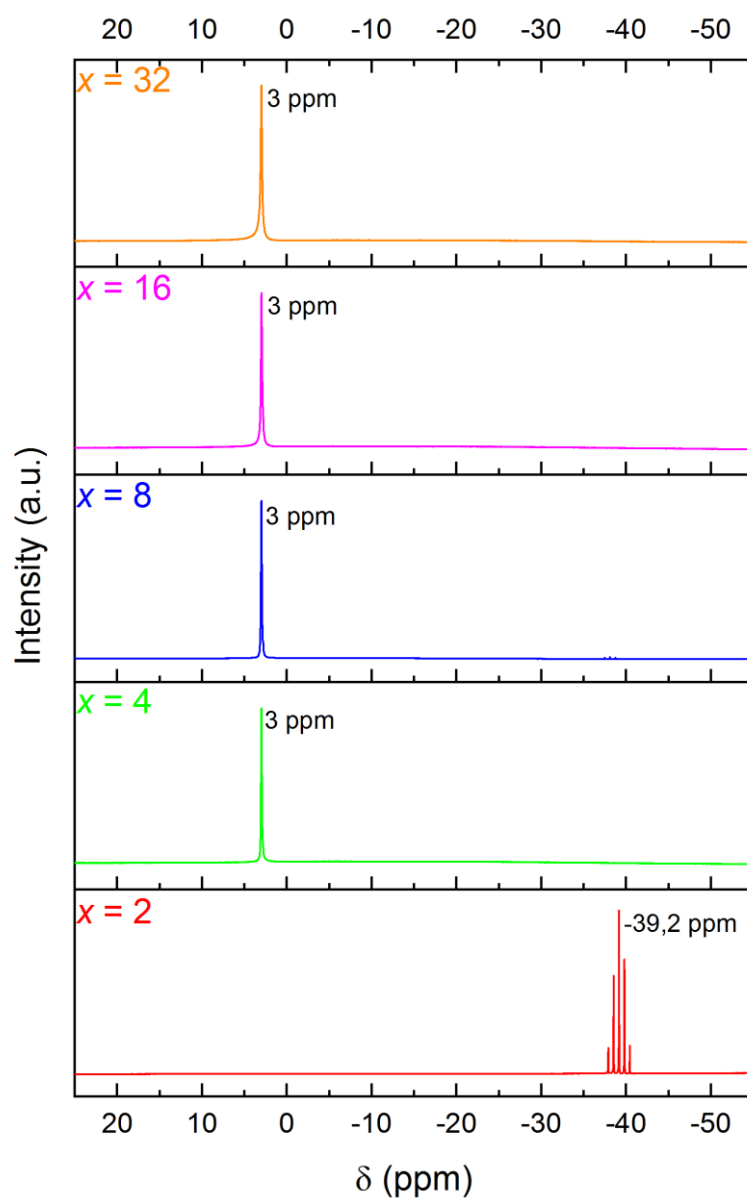


Figure 1. ^{11}B NMR spectra of the solids recovered after methanolysis of NaBH_4 such as $x = 2, 4, 8, 16$ and 32. The solids were dissolved in N,N-dimethylformamide (with CD_3CN).

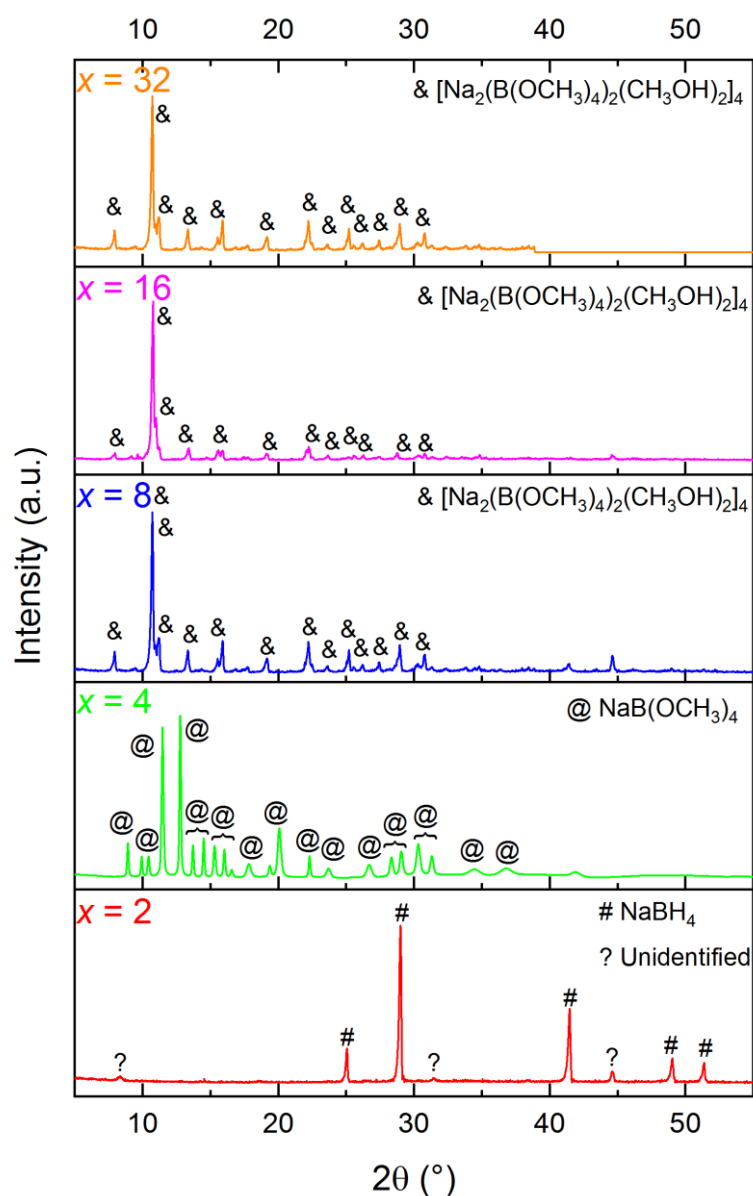


Figure 2. XRD patterns of the solids recovered after methanolysis of NaBH_4 such as $x = 2, 4, 8, 16$ and 32 . The peaks have been indexed as shown. The structures indicated by # and @ were found to match with referenced patterns (respectively: NaBH_4 ref. 00-009-0386, and $\text{NaB}(\text{OCH}_3)_4$ ref. 00-012-0863). The structure indicated by & corresponds to that of $[\text{Na}_2(\text{B}(\text{OCH}_3)_4)_2(\text{CH}_3\text{OH})_2]_4$ reported elsewhere [51]. There are also few unidentified peaks (as shown by the symbol ?).

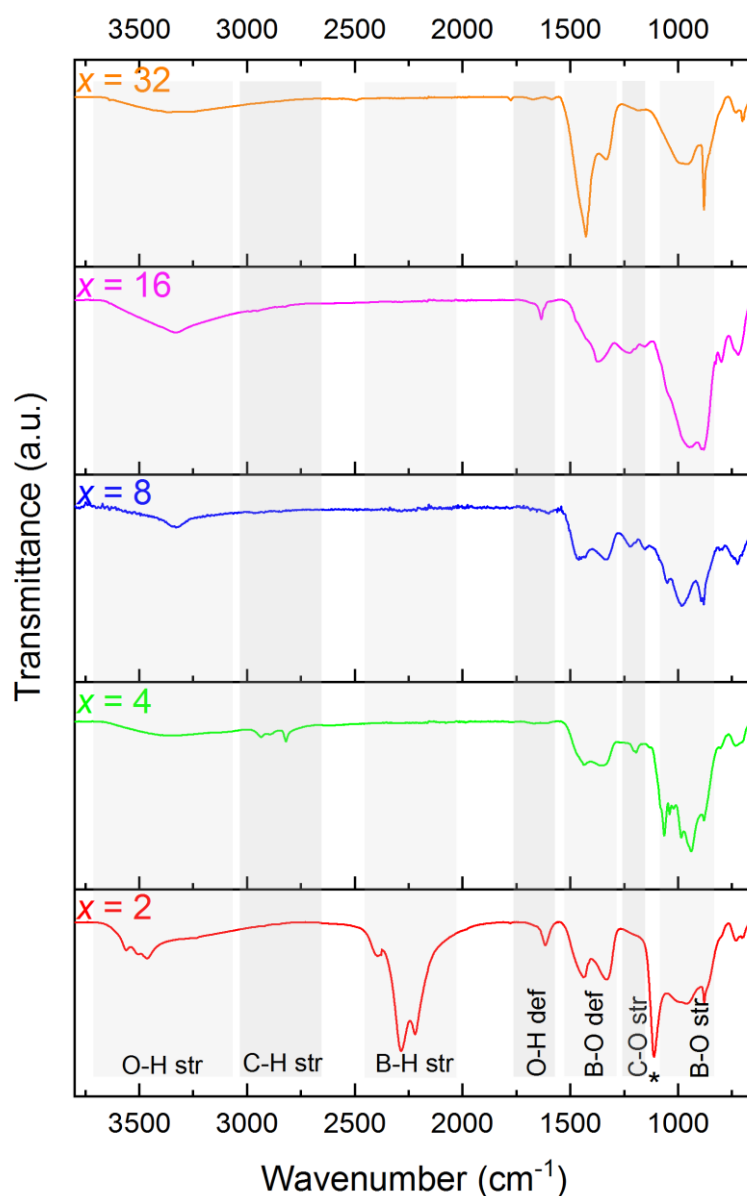


Figure 3. FTIR spectra of the solids recovered after methanolysis of NaBH_4 such as $x = 2, 4, 8, 16$ and 32 . The bands have assigned. The symbol $*$ is attributed to the B–H bending mode. The spectra for $x = 8, 16$ and 32 are also shown in Figures S7 to S9.

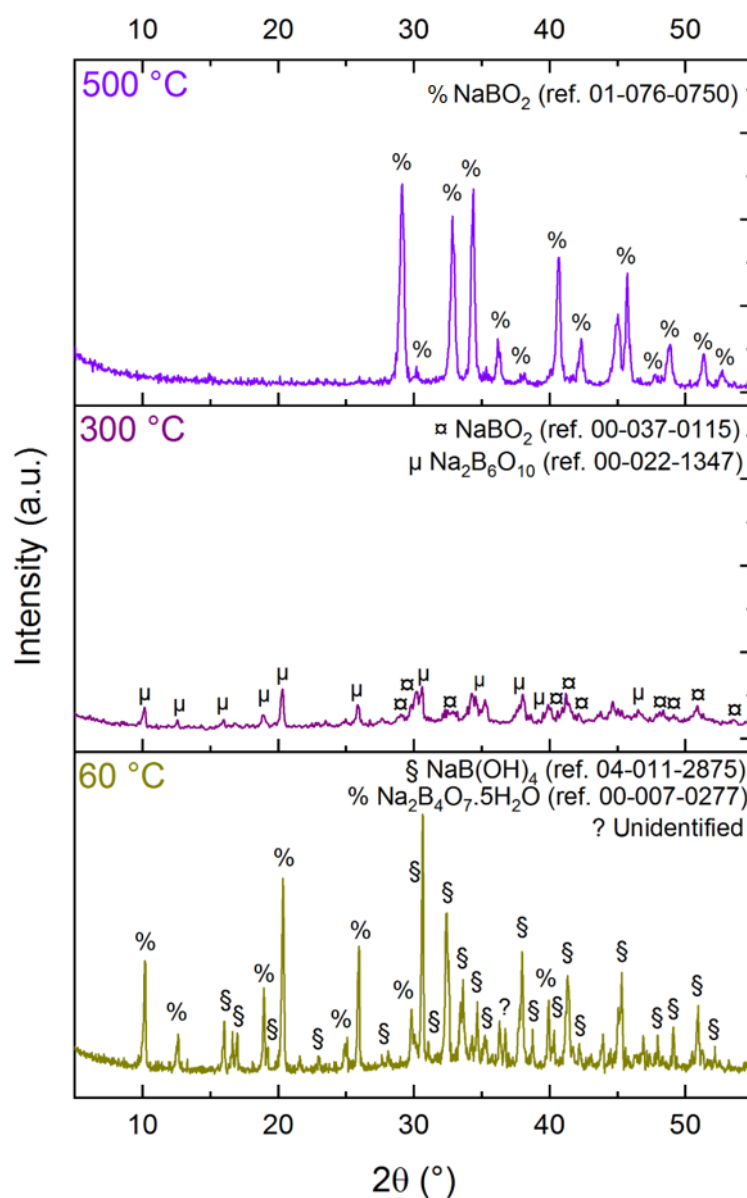


Figure 4. XRD patterns of the hydrolysis product of $\text{NaB}(\text{OCH}_3)_4$ (i.e. $x = 4$) heated at 60, 300, and 500 °C. The peaks have been assigned, when possible, as shown in the figure. There are few peaks (shown by the symbol ?) that have not been assigned because of unsuccessful pattern matching.

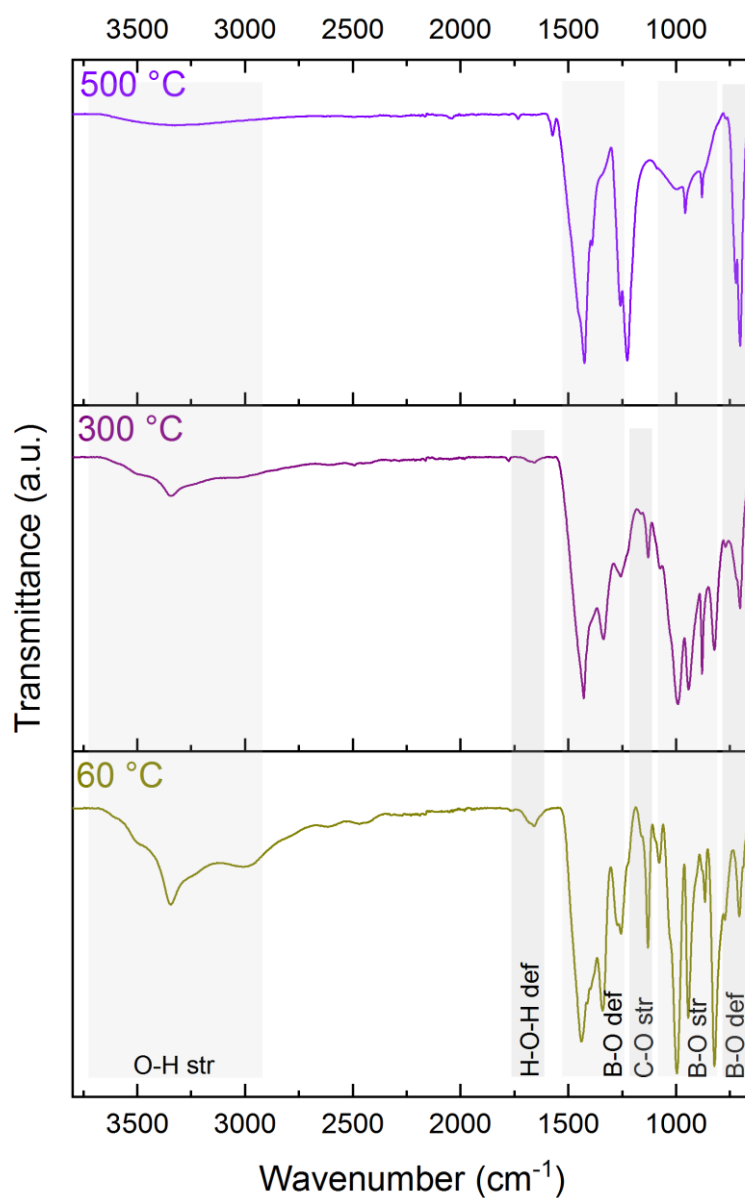


Figure 5. FTIR spectra of the hydrolysis product of $\text{NaB}(\text{OCH}_3)_4$ (i.e. $x = 4$) heated at 60, 300, and 500 °C. The bands have assigned.

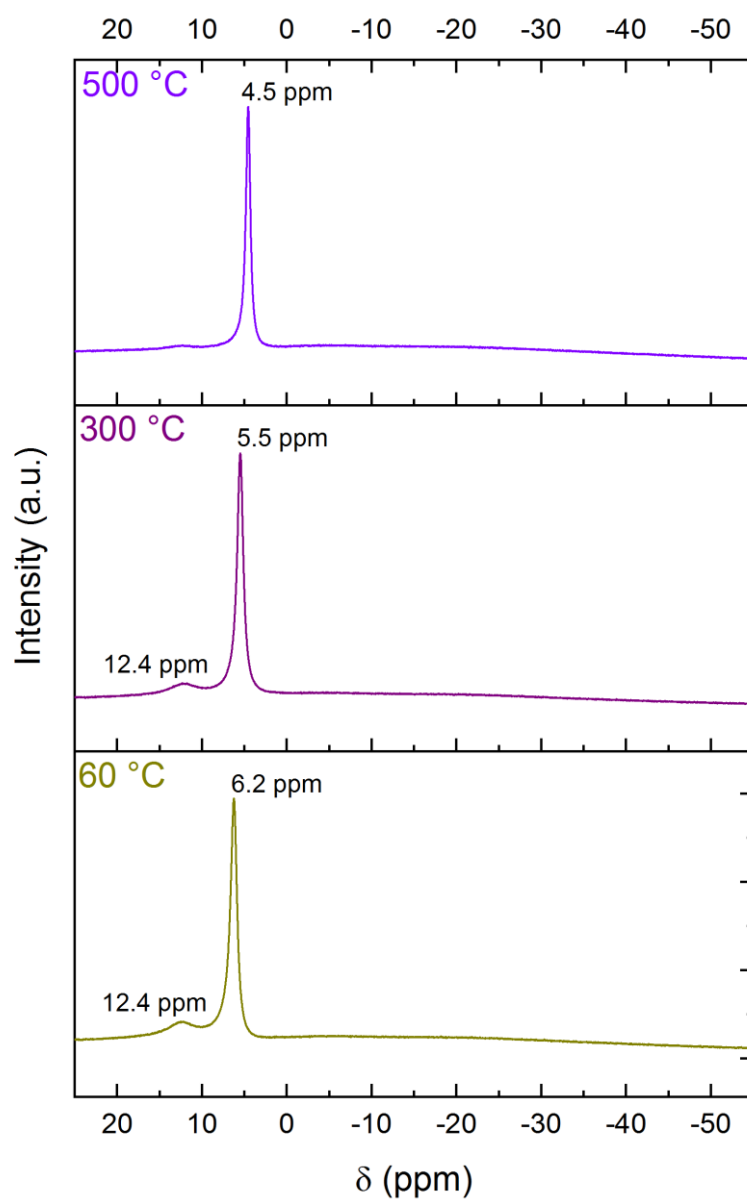


Figure 6. ^{11}B NMR spectra of the hydrolysis product of $\text{NaB}(\text{OCH}_3)_4$ (i.e. $x = 4$) heated at 60, 300, and 500 °C. They were dissolved in deuterated water for analysis.

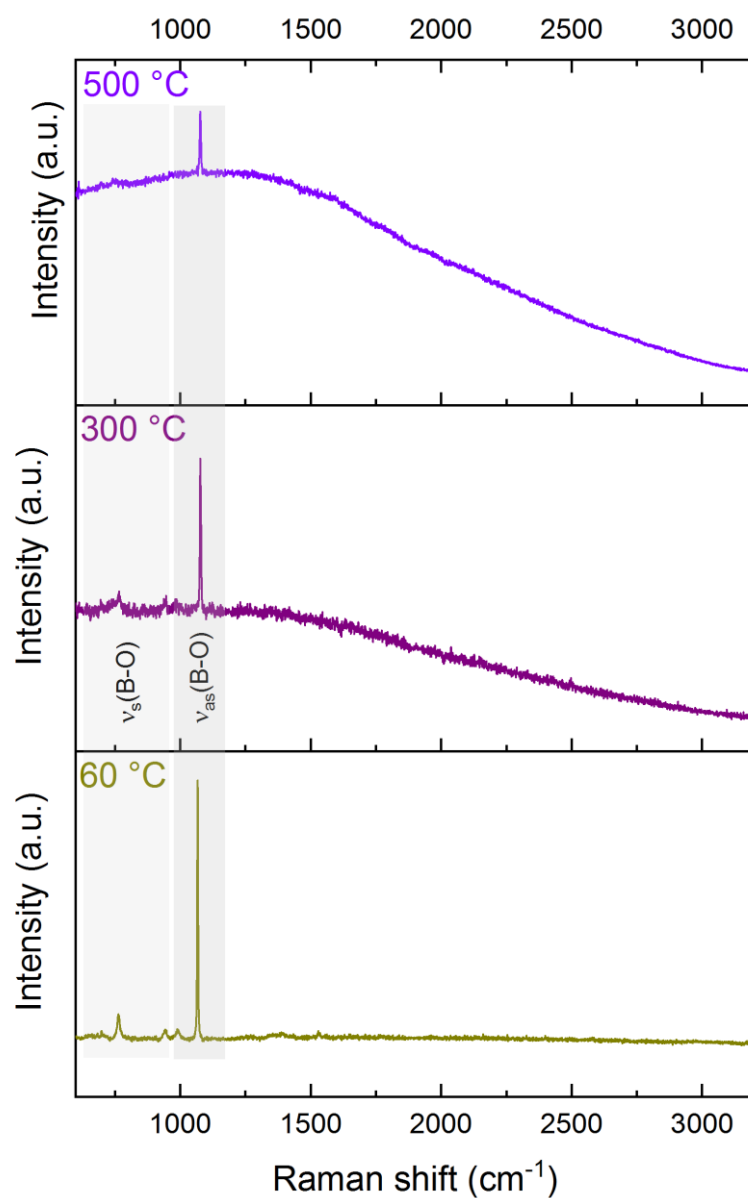


Figure 7. Raman spectra of the hydrolysis product of $\text{NaB}(\text{OCH}_3)_4$ (i.e. $x = 4$) heated at 60, 300, and 500 °C. The bands have assigned.

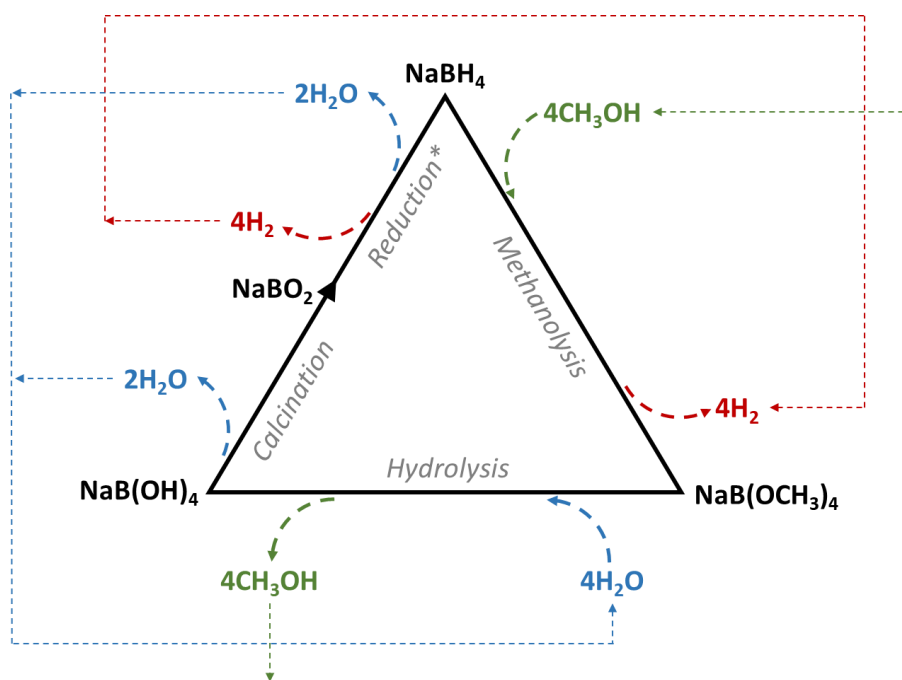


Figure 8. Triangular scheme of the recycling process of the spent fuel stemming from methanolysis of NaBH_4 and subsequent hydrolysis of $\text{NaB(OCH}_3)_4$. The reduction process transforming NaBO_2 to NaBH_4 requires a reducing agent such H_2 or MgH_2 ; here the scheme has been illustrated with H_2 .

Table 1. Comparison of the H₂ generation rates (HGR) for a series of hydride-protonic solvent couples (spontaneous solvolysis reactions without the presence of a catalyst or of an acid).

Hydride	Protonic solvent	T (°C)	HGR (mL H ₂ min ⁻¹)	Ref.
LiBH ₄	H ₂ O	23	2	[64]
NaBH ₄	H ₂ O	20-30	<2	[22,65–67]
NaBH ₄	CH ₃ OH	5	37	[30]
NaBH ₄	CH ₃ OH	20	331	This work
NaBH ₄	CH ₃ OH	45	480	[21]
NaBH ₄	CH ₃ CH ₂ OH	25	<0.1	[68]
KBH ₄	H ₂ O	30	55	[69]
KBH ₄	CH ₃ CH ₂ OH	30	60	[69]
MgH ₂	H ₂ O	25	20	[70]
CaH ₂	H ₂ O	20	3	[71]
NH ₃ BH ₃	H ₂ O	20	<0.1	[64]
NH ₃ BH ₃	CH ₃ OH	20	<0.1	[72]
LiNH ₂ BH ₃	H ₂ O	20	546	[73]
NaNH ₂ BH ₃	H ₂ O	20	381	[74]