



**HAL**  
open science

## **First observation of [Pu<sub>6</sub>(OH)<sub>4</sub>O<sub>4</sub> ]<sup>12+</sup> cluster during the hydrolytic formation of PuO<sub>2</sub> nanoparticles using H/D kinetic isotope effect**

Manon Cot-Auriol, Matthieu Viot, Thomas Dumas, Olivier Diat, Denis Menut, Philippe Moisy, Sergey Nikitenko

### ► To cite this version:

Manon Cot-Auriol, Matthieu Viot, Thomas Dumas, Olivier Diat, Denis Menut, et al.. First observation of [Pu<sub>6</sub>(OH)<sub>4</sub>O<sub>4</sub> ]<sup>12+</sup> cluster during the hydrolytic formation of PuO<sub>2</sub> nanoparticles using H/D kinetic isotope effect. *Chemical Communications*, 2022, 58 (94), pp.13147-13150. <10.1039/D2CC04990B>. <hal-03916056>

**HAL Id: hal-03916056**

**<https://hal.umontpellier.fr/hal-03916056v1>**

Submitted on 30 Dec 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire HAL, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



HAL Authorization

## COMMUNICATION

# First observation of $[\text{Pu}_6(\text{OH})_4\text{O}_4]^{12+}$ cluster during the hydrolytic formation of $\text{PuO}_2$ nanoparticles using H/D kinetic isotope effect

Received 00th January 20xx,  
Accepted 00th January 20xx

Manon Cot-Auriol,<sup>a</sup> Matthieu Virost,<sup>a\*</sup> Thomas Dumas,<sup>b</sup> Olivier Diat,<sup>a</sup> Denis Menut,<sup>c</sup>

DOI: 10.1039/x0xx00000x




Philippe Moisy<sup>b</sup> and Sergey I. Nikitenko<sup>a</sup>

**New insights are provided about the formation mechanism of  $\text{PuO}_2$  nanoparticles (NPs) by investigating an unprecedented kinetic isotope effect observed during their hydrolytic synthesis in  $\text{H}_2\text{O}$  or  $\text{D}_2\text{O}$  and attributed to OH/OD zero point energy difference. The signature of a Pu(IV) oxo-hydroxo hexanuclear cluster, appearing as an important intermediate during the formation of the 2 nm  $\text{PuO}_2$  NPs (synchrotron SAXS/XAS), is further revealed indicating that their formation is controlled by H-transfer reactions occurring during hydroxo to oxo-bridge conversions.**

Anthropogenic activities significantly contributed in the release of plutonium in the environment and related colloids are currently interrogated about their role in the migration of radioactivity in aquatic systems.<sup>1–4</sup> Pu chemistry in aqueous solution involves complex processes including redox/disproportionation, hydrolysis and complexation reactions that can particularly compete for the (+IV) redox state.<sup>5,6</sup> Pu(IV) is indeed highly prone to hydrolysis and the subsequent formation of oligomers that further condensate yielding intrinsic colloids and/or precipitates, even in acidic conditions.<sup>7–9</sup> Meanwhile, disproportionation of Pu(IV) and Pu(V) significantly contribute in the accumulation of ionic Pu(VI), Pu(V) and Pu(III) species during their formation.<sup>7,8,10</sup> While recent investigations reach a consensus in describing intrinsic Pu colloids as *ca.* 2 nm  $\text{PuO}_2$ -like NPs, much less is known about their formation mechanism.<sup>11–14</sup> The description of Pu oxo-hydroxo clusters, with a characteristic size situated somewhere between the ones of ionic and colloidal species of Pu, highlighted the relation between their core structures revealing some striking similarities with bulk  $\text{PuO}_2$ . This suggested that bigger clusters could be formed from the

assembly of those smaller molecular fragments.<sup>5,15–18</sup> A better knowledge about the underlying mechanism would help in understanding the behaviour of these species in environmental context and pave the way for pioneering approaches devoted to the control of the size-property relationship of Pu nanomaterials.<sup>13</sup> Kinetic isotope effect (KIE) can be observed when comparing reaction rates in  $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$ .<sup>19</sup> Primary KIE originates from the cleavage of O-H bonds and differs from solvent isotope effect which is related to differences in the physico-chemical properties of  $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$  solvents ( $\text{pK}_w$ , polarity, viscosity...).<sup>20</sup> In this work, H/D KIE was explored to probe the formation mechanism of colloidal  $\text{PuO}_2$  NPs.

The formation kinetics of intrinsic Pu(IV) colloids was monitored by Vis-NIR absorption spectroscopy (Fig. 1a) by diluting a Pu(IV) concentrated solution in  $\text{H}_2\text{O}$  or  $\text{D}_2\text{O}$  (ESI). It is important to mention that the pH (pD) of the studied solutions is imposed by the acidity of the added Pu(IV) solution aliquot (the slight  $\text{pK}_w$  difference resulting from self-ionization of  $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$  is not responsible for KIE described below, ESI). After a few minutes in  $\text{H}_2\text{O}$ , the characteristic electronic signature from Pu(IV) colloids (resulting from Pu(IV) hydrolysis, Eq. 1) was observed with a main absorption band located around 616 nm and several others at 578, 688 and 735 nm.<sup>21</sup> The sharp absorption band at 830 nm was attributed to the additional presence of Pu(VI) in solution ( $\text{PuO}_2^{2+}$  form, less than *ca.* 3% of total Pu) resulting from Pu(IV) disproportionation (Eq. 2–4).<sup>9,22</sup>



<sup>a</sup> ICSM, Univ Montpellier, CEA, CNRS, ENSCM, Marcoule, France.


[matthieu.virost@cea.fr](mailto:matthieu.virost@cea.fr)

<sup>b</sup> CEA, DES, ISEC, DMRC, Univ Montpellier, Marcoule, France.

<sup>c</sup> Synchrotron SOLEIL, MARS beamline, l'Orme des Merisiers, Saint Aubin BP 48, 91192 Gif-sur-Yvette, France.

† Footnotes relating to the title and/or authors should appear here.

Electronic Supplementary Information (ESI) available: additional spectra, experimental details and methods. See DOI: 10.1039/x0xx00000x

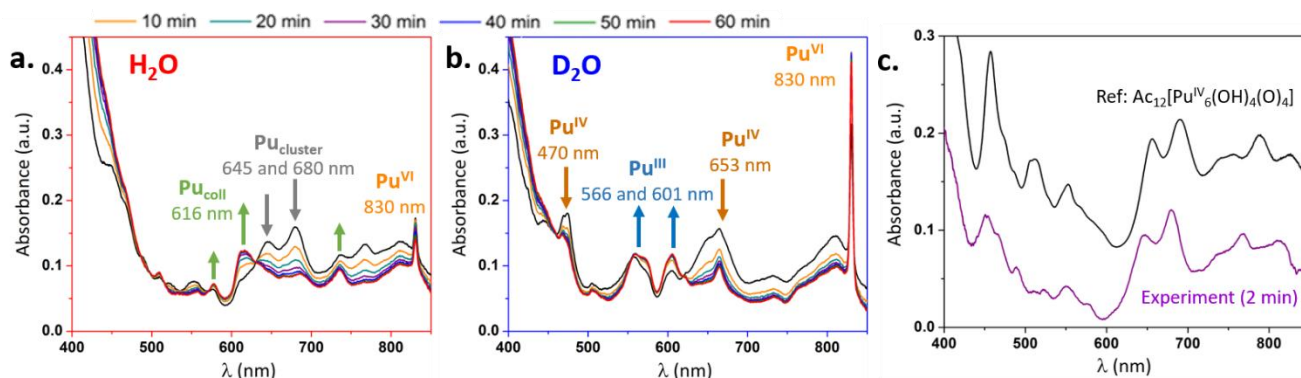

**Fig. 1.** Vis-NIR absorption spectra acquired during the synthesis of Pu(IV) colloids in (a) H<sub>2</sub>O and (b) D<sub>2</sub>O in the 2–60 min range. (c) Vis-NIR absorption spectrum acquired 2 min after dispersion of concentrated Pu(IV) in H<sub>2</sub>O (without contributions of Pu(III), Pu(VI) and Pu<sub>coll</sub>) compared to Pu(IV) acetate hexanuclear cluster, with courtesy of C. Tamain.<sup>15</sup>

Pu(III) concentration should be *ca.* twice the one of Pu(VI) according to Eq. 2–4 but it is hardly observed due to low molar coefficient ( $33 \text{ M}^{-1}\cdot\text{cm}^{-1}$ ) and the superposition of the various transitions in the 600–700 nm spectral range. The absorption spectra acquired in D<sub>2</sub>O for similar other conditions evolved differently. In particular, indisputable signatures of Pu(IV) (hydrolyzed forms, 470 nm and 653 nm) and Pu(III) (Pu<sup>3+</sup> form at 601 nm and 566 nm) were observed contrasting with experiments carried out in H<sub>2</sub>O.<sup>9,22</sup> Also, the determined amount of Pu(VI) at 830 nm was much higher in D<sub>2</sub>O (*ca.* 15% of total Pu) (Fig. 1b). After several weeks and despite strong kinetic differences, both aged H<sub>2</sub>O and D<sub>2</sub>O solutions of Pu converged to stable Pu(IV) intrinsic colloids as evidenced by characteristic absorption spectra (Fig. S3, ESI). Such a behaviour is attributed to KIE occurring during Pu(IV) hydrolysis and leading to slowdown of Pu colloid formation.<sup>23,24</sup>

A closer look at the electronic spectra acquired during the first hour in H<sub>2</sub>O medium (Fig. 1a) allows observing an original transient species with principal absorption bands located at 680 and 645 nm. The spectrum appears directly after Pu(IV) dilution in H<sub>2</sub>O (spectra at 2 min) and decreases in absorbance with time while the characteristic spectra of the Pu colloids appear. An isobestic point observed at 630 nm suggests a two-component conversion. Deconvolution studies which consisted in the subtraction of reference spectra (Pu(III–VI) and Pu<sub>coll</sub>) from the experimental ones revealed an unprecedented signature (Fig. 1c) which offered striking similarities with a recently described oxo-hydroxo hexanuclear core of a Pu(IV) cluster  $[\text{Pu}_6(\text{OH})_4\text{O}_4]^{12+}$  decorated by acetate or DOTA ligands.<sup>15,16</sup> Slight differences between both spectra were attributed to the decoration of the latter with acetate ligands (on-going efforts aim at stabilizing this specie during Pu(IV) colloid synthesis). A similar observation in D<sub>2</sub>O appeared more complicated due to the important contribution of other Pu ionic species originated from Pu(IV) disproportionation and hydrolysis. The deconvoluted spectrum revealed a noisy signal most likely attributed to low concentrated Pu(IV) polynuclear cores including the hexamer or Pu(IV) hydrolysed species (Fig. S4, ESI).

Kinetic curves were extracted from deconvolution (approach described in ESI) studies to understand the

observed reactivity differences during the first minutes. Fig. 2a and 2b confirm the more important disproportionation of Pu(IV) (with a stronger accumulation of ionic Pu(VI) and Pu(III) in solution) and the lower concentration of the Pu cluster intermediate in D<sub>2</sub>O medium. Pu(VI) concentration is twice the one of Pu(III) in agreement with the Eq. 4. Note that Pu(V) was not observed during deconvolution but its presence in the process can't be excluded. In both media, Pu(VI) quickly accumulated in solution during *ca.* 30 min before slowly decreasing with time (Fig. 2c). The initial accumulation rate of Pu(VI) was found to be slightly higher in D<sub>2</sub>O than in H<sub>2</sub>O ( $20.1 \text{ vs. } 5.2 \text{ mM}\cdot\text{h}^{-1}$ , respectively).

After *ca.* 30 min, Pu(VI) consumption was explained by its reaction with Pu(III) (*i.e.* Pu(IV) comproportionation). A first order reaction law was used on Pu(VI) to compare both kinetics in agreement with the work of Rabideau and Kline (Eq. 2, ESI).<sup>25</sup> It is interesting to note that the logarithm function only fitted in the 30–120 min range for H<sub>2</sub>O medium which was attributed to the evolution of Pu species during comproportionation and a possible alternative mechanism in solution.<sup>9</sup> Fig 2c evidences the significantly higher reduction rate of Pu(VI) observed in H<sub>2</sub>O ( $k^{\text{H}}(-\text{Pu}^{\text{VI}})/k^{\text{D}}(-\text{Pu}^{\text{VI}}) = 6.8$ ). The consumption of Pu(III) was not considered due to its low absorbance and the interferences with the spectra of other Pu species. Deconvolutions also allowed to estimate the formation kinetics of Pu(IV) colloids at *ca.* 616 nm (Fig. 2d). Assuming a first order formation rate on the colloid (Eq. 5, ESI), it was confirmed that the latter accumulates at a much lower rate in D<sub>2</sub>O. The calculated ratio of the colloid formation kinetic constants  $k^{\text{H}}(\text{Pu}_{\text{coll}})/k^{\text{D}}(\text{Pu}_{\text{coll}})$  equalled 7.4.

Synchrotron measurements allowed the quasi-simultaneous characterization of the aged (> 1 month) colloids by small-angle X-ray scattering (SAXS) and X-ray absorption spectroscopy (XAS) without altering the nature of the samples (Fig. S5, ESI). Normalized SAXS diagrams exhibited similar scattering profiles in both cases (Fig. 3), characteristic from sharp interfaces typical for 3D dense particles.<sup>26</sup> Considering a simple model of spherical and homogeneous NPs with a slight polydispersity (0.15), the data adjustment provided a slightly higher radius for the colloid formed in D<sub>2</sub>O ( $1.1 \pm 0.1 \text{ nm}$  vs.  $0.9 \pm 0.1 \text{ nm}$  in H<sub>2</sub>O). The determined scattering length density (*ca.*

69  $10^{10}$   $\text{cm}^{-2}$ ) and the volume fraction were very close to the estimated parameters (Table S3, ESI). This simple model, with few but consistent parameters, is well representative of the scattering signal variation in absolute scale.

faster disproportionation of Pu(IV) in  $\text{H}_2\text{O}$  which is not the case in our study (Fig. 2c). By contrast, the KIE can be explained by the zero point energy difference between O-H and O-D bonds ( $\Delta E = 5.89$   $\text{kJ}\cdot\text{mol}^{-1}$ ).<sup>19,34</sup> As a consequence, more energy is

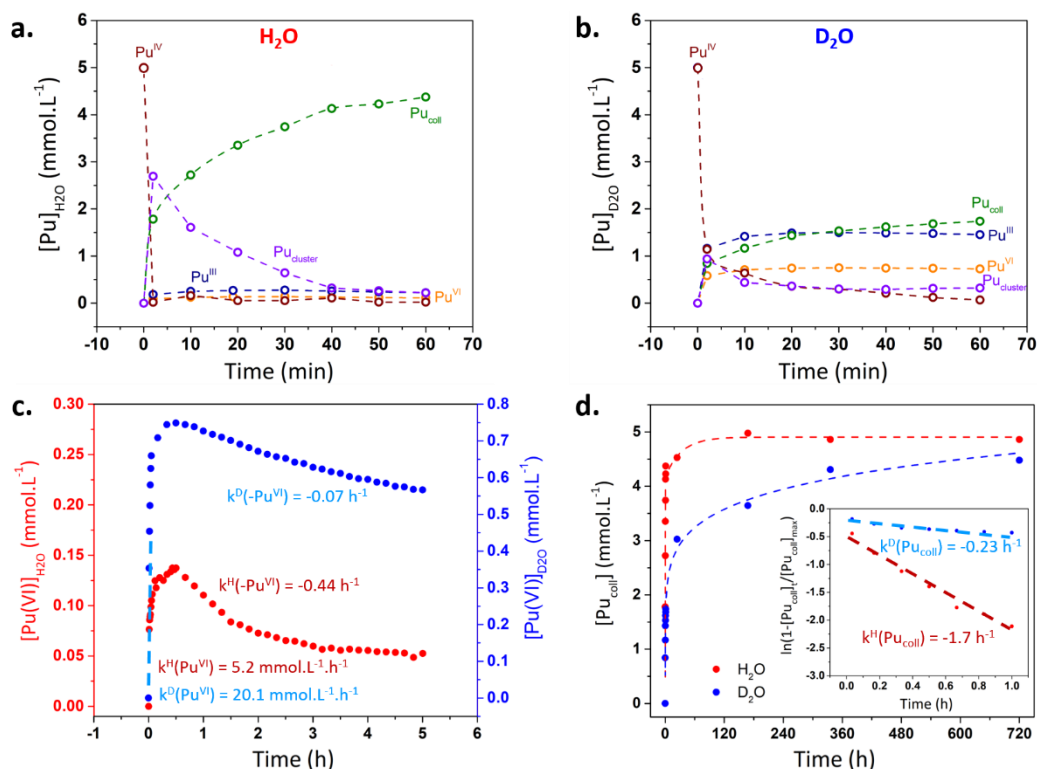


Fig. 2. (a,b) Kinetics related to Pu species in  $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$  after deconvolution. (c) Evolution of Pu(VI) concentration during the synthesis of Pu(IV) colloids in  $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$ . A special care should be given to scale bar differences. Dashed lines represent linear regressions used to determine kinetic rates (corresponding values given in ESI). (d) Evolution of the colloid absorbance ( $\lambda = 616$  nm) as a function of time after deconvolution of the absorbance spectra. Insert: plot of the natural logarithm of Pu colloid absorbance against time.

X-ray absorption near-edge structure (XANES) spectra acquired at the Pu  $L_3$  edge on the colloids formed in both media exhibited a white line (18067 eV) at similar positions, agreeing with the strong predominance of the (+IV) oxidation state for Pu (Fig. S6, ESI).<sup>27,28</sup> A slight difference observed on the spectra at *ca.* 18080 eV was attributed to the significant contribution of Pu(VI) ions in  $\text{D}_2\text{O}$ . In order to compare the data obtained in  $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$ , a XAS spectrum of Pu(VI) was subtracted from the experimental data obtained in  $\text{D}_2\text{O}$ .<sup>27,28</sup> The resulting EXAFS spectrum was found to be similar to the one acquired in  $\text{H}_2\text{O}$  (Fig. S6, ESI). Both FT showed two main peaks at  $R\text{-}\phi = \text{ca.}$  1.84 and 3.68  $\text{\AA}$ , agreeing with Pu(IV) colloids<sup>11,26,29</sup> and crystalline bulk  $\text{PuO}_2$  (CFC, Fm-3m).<sup>7,30</sup> The structural parameters of the fits demonstrated that local structures of the colloids prepared in this study are similar and close to bulk  $\text{PuO}_2$  (Table S5, ESI).

As a first conclusion, the observed strong KIE only shows little influence on the final shape, size and local structure of the NPs which can be described as 2 nm spherical NPs with a  $\text{PuO}_2$ -like local structure.<sup>7,11,14,26,31,32</sup> The physico-chemical property differences reported for  $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$  at room temperature and originating solvent isotope effects in some cases cannot explain the observed KIE.<sup>20</sup> As well, it has been demonstrated that quantum tunnelling observed for electron or H atom transfer is more important in  $\text{H}_2\text{O}$  than in  $\text{D}_2\text{O}$ .<sup>33</sup> Such a phenomenon could have been invoked to explain a

required to break the latter bonds favouring disproportionation of Pu(IV) in  $\text{D}_2\text{O}$  medium instead of the cluster formation. Therefore, O-H bond ruptures appear as rate-limiting steps during the colloid formation. The calculated theoretical isotopic separation factor  $\alpha_{(\text{H/D})}$  equals 10.6 at  $T = 300$  K (Eq. 6, ESI) which is in good agreement with the  $k^{\text{H}}/k^{\text{D}}$  ratios observed for Pu(VI) reduction and Pu colloid formation. Interestingly, kinetic studies related to hydrolysis in  $\text{D}_2\text{O}$  are scarce in the literature. We only found one recent publication describing the hydrolysis of Ce(IV) and subsequent formation of  $\text{CeO}_2$  NPs with a close ratio  $k^{\text{H}}/k^{\text{D}} = 10$ .<sup>35</sup>

It has been argued that Pu(IV) disproportionation is preceded by Pu(IV) ions hydrolyses and the generation of polynuclear hydroxo complexes.<sup>36</sup> The slightly higher accumulation rates observed for Pu(VI) in  $\text{D}_2\text{O}$  after disproportionation suggest that hydrolysis of Pu(IV) (Eq. 1) is poorly affected by KIE. By contrast, both the cluster core and Pu colloid formation are limited in  $\text{D}_2\text{O}$ . The presence of


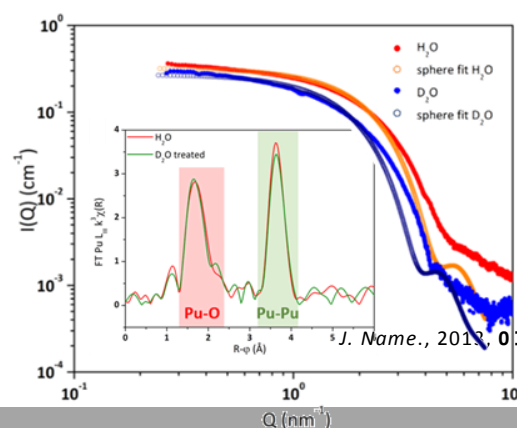


Fig. 3. SAXS diagrams of Pu(IV) colloids formed in  $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$  and corresponding fits. Inset:  $k^3$ -weighted FT for Pu(IV) colloids ( $\text{H}_2\text{O}$  and  $\text{D}_2\text{O}$ , without Pu(VI) contribution).

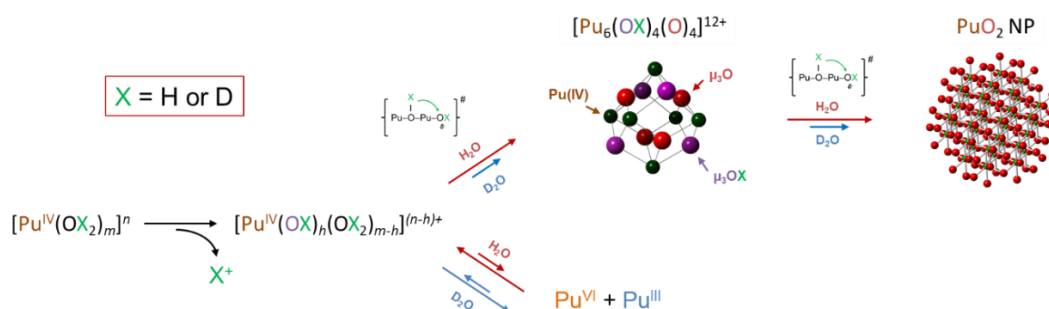

hydroxo-bridges in the hexanuclear cluster and their absence in the final oxo-NP demonstrates that the Pu colloid formation involves a succession of olation and oxolation reactions confirming that PuO<sub>2</sub> NPs formation is limited by H-atom transfer reactions (scheme 1).<sup>6,18</sup> This observation further discards classical crystal nucleation theory for PuO<sub>2</sub> NPs in aqueous media where crystal growth occurs through the addition of monomeric units<sup>37</sup> but rather suggests the stacking of metastable and structurally well-defined oxo-hydroxo Pu(IV) clusters as a favoured mechanism,<sup>17</sup> as also suggested for U(IV) cluster analogues.<sup>38,39</sup>

## Conflicts of interest

There are no conflicts to declare.

## References

- G. J.-P. Deblonde, A. B. Kersting and M. Zavarin, *Commun. Chem.*, 2020, **3**, 167.
- A. Yu. Romanchuk, I. E. Vlasova and S. N. Kalmykov, *Front. Chem.*, 2020, **8**, 630.
- A. B. Kersting, *Inorg. Chem.*, 2013, **52**, 3533–3546.
- E. L. Tran, O. Klein-BenDavid, N. Teutsch and N. Weisbrod, *Environ. Sci. Technol.*, 2015, **49**, 13275–13282.
- L. Soderholm, P. M. Almond, S. Skanthakumar, R. E. Wilson and P. C. Burns, *Angew. Chem. Int. Ed.*, 2008, **47**, 298–302.
- D. A. Costanzo, R. E. Biggers and J. T. Bell, *J. Inorg. Nucl. Chem.*, 1973, **35**, 609–622.
- J. Rothe, C. Walther, M. A. Denecke and Th. Fanghänel, *Inorg. Chem.*, 2004, **43**, 4708–4718.
- V. Neck and J. I. Kim, *Radiochim. Acta*, 2001, **89**, 1–16.
- D. L. Clark, S. S. Hecker, G. D. Jarvinen and M. P. Neu, in *The chemistry of the actinide and transactinide elements*, Springer Netherland, Dordrecht, 2006, pp. 813–1264.
- C. Walther, H. R. Cho, C. M. Marquardt, V. Neck, A. Seibert, J. I. Yun and T. Fanghänel, *Radiochim. Acta*, 2007, **95**, 7–16.
- E. Dalodière, M. Viro, V. Morosini, T. Chave, T. Dumas, C. Hennig, T. Wiss, O. Dieste Blanco, D. K. Shuh, T. Tyliszczak, L. Venault, P. Moisy and S. I. Nikitenko, *Sci. Rep.*, 2017, **7**, 43514.
- M. Viro, T. Dumas, M. Cot-Auriol, P. Moisy and S. I. Nikitenko, *Nanoscale Adv.*, 2022, In press.
- E. Gerber, A. Yu. Romanchuk, S. Weiss, A. Kuzenkova, M. O. J. Y. Hunault, S. Bauters, A. Egorov, S. M. Butorin, S. N. Kalmykov and K. O. Kvashnina, *Environ. Sci.: Nano*, 2022, **9**, 1509–1518.
- E. Gerber, A. Yu. Romanchuk, I. Pidchenko, L. Amidani, A. Rossberg, C. Hennig, G. B. M. Vaughan, A. Trigub, T. Egorova, S. Bauters, T. Plakhova, M. O. J. Y. Hunault, S. Weiss, S. M. Butorin, A. C. Scheinost, S. N. Kalmykov and K. O. Kvashnina, *Nanoscale*, 2020, **12**, 18039–18048.
- G. Chupin, C. Tamain, T. Dumas, P. L. Solari, P. Moisy and D. Guillaumont, *Inorg. Chem.*, 2022, **61**, 4806–4817.
- C. Tamain, T. Dumas, D. Guillaumont, C. Hennig and P. Guilbaud, *Eur. J. Inorg. Chem.*, 2016, **2016**, 3536–3540.
- K. E. Knope and L. Soderholm, *Inorg. Chem.*, 2013, **52**, 6770–6772.
- G. E. Sigmon and A. E. Hixon, *Chem. Eur. J.*, 2019, **25**, 2463–2466.
- S. Scheiner and M. Čuma, *J. Am. Chem. Soc.*, 1996, **118**, 1511–1521.
- G. Swain and F. W. Bader, *Tetrahedron*, 1960, **10**, 182–199.
- M. H. Lloyd and R. G. Haire, *Radiochim. Acta*, 1978, **25**, 139–148.
- D. Jebaraj Mahildoss and T. N. Ravi, *J. Radioanal. Nucl. Chem.*, 2012, **294**, 87–91.
- S. W. Rabideau, *J. Am. Chem. Soc.*, 1953, **75**, 798–801.
- S. W. Rabideau and R. J. Kline, *J. Phys. Chem.*, 1960, **64**, 680–682.
- S. W. Rabideau and R. J. Kline, *J. Phys. Chem.*, 1958, **62**, 617–620.
- C. Micheau, M. Viro, S. Dourdain, T. Dumas, D. Menut, P. L. Solari, L. Venault, O. Diat, P. Moisy and S. I. Nikitenko, *Environ. Sci.: Nano*, 2020, **7**, 2252–2266.
- T. Vitova, I. Pidchenko, D. Fellhauer, T. Pruessmann, S. Bahl, K. Dardenne, T. Yokosawa, B. Schimmelpfennig, M. Altmaier, M. Denecke, J. Rothe and H. Geckeis, *Chem. Commun.*, 2018, **54**, 12824–12827.
- S. D. Conradson, D. L. Clark, M. P. Neu, W. Runde and C. D. Tait, *Los Alamos Sci.*, 2000, **26**, 418–421.
- C. Ekberg, K. Larsson, G. Skarnemark, A. Ödegaard-Jensen and I. Persson, *Dalton Trans.*, 2013, **42**, 2035–2040.
- A. Kuzmin and J. Chaboy, *IUCr*, 2014, **1**, 571–589.
- M. Altmaier, X. Gaona and D. Fellhauer, in *Plutonium Handbook*, American Nuclear Society, La Grange Park, IL, USA, D.A.G. D.L. Clark, R.J. Hanrahan Jr., 2019, vol. 3.
- L. Bonato, M. Viro, T. Dumas, A. Mesbah, E. Dalodière, O. Dieste Blanco, T. Wiss, X. Le Goff, M. Odorico, D. Prieur, A. Rossberg, L. Venault, N. Dacheux, P. Moisy and S. I. Nikitenko, *Nanoscale Adv.*, 2020, **2**, 214–224.
- T. Kumagai, M. Kaizu, S. Hatta, H. Okuyama, T. Aruga, I. Hamada and Y. Morikawa, *Phys. Rev. Lett.*, 2008, **100**, 166101.
- M. Ceriotti, W. Fang, P. G. Kusalik, R. H. McKenzie, A. Michaelides, M. A. Morales and T. E. Markland, *Chem. Rev.*, 2016, **116**, 7529–7550.
- N. W. Pettinger, R. E. A. Williams, J. Chen and B. Kohler, *Phys. Chem. Chem. Phys.*, 2017, **19**, 3523–3531.
- J. M. Haschke, *J. Nucl. Mater.*, 2007, **362**, 60–74.
- J. De Yoreo, *Nature Mater.*, 2013, **12**, 284–285.

- 38 L. Chatelain, R. Faizova, F. Fadaei-Tirani, J. Pécaut and M. Mazzanti, *Angew. Chem. Int. Ed.*, 2019, **58**, 3021–3026.
- 39 N. P. Martin, C. Volkringer, N. Henry, X. Trivelli, G. Stoclet, A. Ikeda-Ohno and T. Loiseau, *Chem. Sci.*, 2018, **9**, 5021–5032.