



HAL
open science

Ca²⁺-based metal-organic framework as enzyme preparation to promote the catalytic activity of amylase

J. Song, X. Shen, F. Liu, X. Zhao, Y. Wang, S. Wang, P. Wang, J. Wang, F. Su, S. Li

► To cite this version:

J. Song, X. Shen, F. Liu, X. Zhao, Y. Wang, et al.. Ca²⁺-based metal-organic framework as enzyme preparation to promote the catalytic activity of amylase. *Materials Today Chemistry*, 2023, 30, pp.101522. 10.1016/j.mtchem.2023.101522 . hal-04080065

HAL Id: hal-04080065

<https://hal.umontpellier.fr/hal-04080065>

Submitted on 4 May 2023

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

1 **Ca²⁺ based metal-organic framework as enzyme preparation to**
2 **promote the catalytic activity of amylase**

3 *Jie Song,^{a,b} Xin Shen,^{a,b} Fangyu Liu,^{a,b} Xinshuang Zhao,^{a,b} Yuandou Wang,^{a,b} Shuxin Wang,^{a,b}*

4 *Pinyi Wang,^c Jinjun Wang,^{c*} Feng Su,^{a,b*} Suming Li^{d*}*

5
6 *^a State Key Laboratory Base of Eco-chemical Engineering, College of Chemical Engineering,*
7 *Qingdao University of Science and Technology, Qingdao 266042, China*

8 *^b Institute of High Performance Polymers, Qingdao University of Science and Technology,*
9 *Qingdao 266042, China*

10 *^c Qingdao Traditional Chinese Medicine Hospital (Qingdao Hiser Hospital), Qingdao 266033,*
11 *China*

12 *^d Institut Europeen des Membranes, IEM, UMR 5635, Univ Montpellier, CNRS, ENSCM, 34095*
13 *Montpellier, France*

14 **Corresponding authors: yayang2001@163.com (J. Wang); sufeng@qust.edu.cn (F. Su);*
15 *suming.li@umontpellier.fr (S. Li)*

19 **Abstract**

20 Enzyme preparation can protect the enzyme conformation in storage, transportation, and
21 operation process, but excessive additives can affect enzyme performance. In this work, a Ca^{2+}
22 based metal-organic framework (UTSA-280) was prepared to encapsulate amylases (α -
23 amylase, pullulanase, and glucoamylase) in situ. After release from UTSA-280, the relative
24 activity of α -amylase and pullulanase increased to 177.8 and 201.0 %, respectively, as
25 compared to pure enzymes. Mechanism explorations indicate that amylase released from
26 UTSA-280 has more Ca^{2+} on its surface with stronger combination, which probably leads to
27 the activation effect to metal ion activating enzyme. Besides, UTSA-280 could protect enzymes
28 from heat, organic solvent, and trypsin, which is beneficial for the storage, transportation, and
29 operation of enzyme. Therefore, it is concluded that MOFs could be a promising metal ion
30 activating enzyme preparation material with activity promoting and protective effects.

31

32 **Keywords:** Metal-organic frameworks; enzyme preparation; amylase; catalysis.

33

34

35 1. Introduction

36 Traditional enzyme preparations usually suffer from a number of disadvantages such as
37 excessive additives, redundant purification operations, and reduced activity, which could
38 restrain their application [1, 2]. Enzyme preparations often possess a small portion of active
39 enzyme molecules, while a large amount of additives such as inactive proteins, preservatives,
40 salts, and polymers are added to maintain the enzyme conformation on storage conditions [3-
41 6]. However, excessive additives could affect the enzyme performance [7]. On the other hand,
42 addition of enzyme activators such as metal ions is often ineffective and costly because high
43 concentrations of activators are needed due to their low accessibility to and weak interactions
44 with enzyme molecules in the catalytic process [8]. For example, a large amount of ammonium
45 sulfate usually used in the salting-out process, as well as high operating temperature of spray
46 drying, can significantly affect the enzyme performance [9]. Therefore, it is of crucial
47 importance to develop advanced materials for uses in enzyme preparation.


48 In enzyme applications, metal ions (Mn^{2+} , Zn^{2+} , Ca^{2+} , $Fe^{2+/3+}$) are often required to
49 monitor the activity of enzymes [10]. For example, Ca^{2+} ions are considered to have crucial
50 roles for maintaining α -amylase structures in their correct conformations and improving the
51 thermal resistance [11-13]. Mao and Kinsella found that banana α -amylase activity increased
52 significantly when calcium was incorporated into the assay medium [14]. Mg^{2+} and K^+ are
53 typical activators of methionine adenosyltransferase (MAT) from all sources which can
54 enhance its activity and reaction rate [15]. Therefore, metal ions are excellent stabilizer and
55 activator of enzymes, and incorporating metal ions as a component is a promising approach for
56 metal ion activating enzyme preparations.

57 Metal-organic frameworks (MOFs) are an emerging class of crystalline materials
58 assembled by organic links and metal ions or clusters. Owing to their unique properties such
59 as high surface areas, ultra high porosity, high thermal stability, and good surface chemistry,

60 MOFs have become an ideal material for the preparation of enzyme/MOF biocomposites [16].
61 In fact, MOFs present several advantages for enzyme encapsulation, i.e. mild preparation
62 environments (room temperature, aqueous solution), high loading efficiency and good
63 protection for enzymes [17, 18]. In the past decade, great efforts have been made to develop
64 enzyme@MOF composites for enzyme immobilization. However, these heterogeneous
65 biocatalytic systems suffer from the decrease of enzyme activity caused by the immobilization
66 and diffusion processes. Interestingly, unstable MOFs could degrade under mild conditions,
67 releasing metal ions which could become enzyme activator. Therefore, enzyme-MOF
68 composites could be promising as high-performance enzyme preparations.

69 Amylases are a class of industrial enzymes representing approximately 30% of the world
70 enzyme production [19]. Amylases are used in many industrial processes such as food,
71 fermentation, paper, sugar and pharmaceutical industries. Calcium ions play an important role
72 in monitoring the structure, activity, and thermal stability of some amylases [11, 12], thus
73 affecting their performance [20, 21]. However, there is no report on the use of Ca^{2+} based MOF
74 for amylase preparation in spite of its potential in activating amylases.

75 In this study, a Ca^{2+} based MOF, namely UTSA-280, was synthesized as Ca^{2+} activating
76 enzyme preparation for α -amylase and pullulanase as shown in Scheme 1. UTSA-280 could
77 efficiently encapsulate enzymes in-situ under mild synthesis conditions. The release
78 performance of enzyme@UTSA-280 and the activity of released enzymes were evaluated.
79 Mechanism experiments were performed to understand the strong increase in enzyme activity.
80 The enzyme protection performance and size control of enzyme@UTSA-280 were also
81 explored to further evaluate the potential of UTSA-280 as enzyme preparation material.

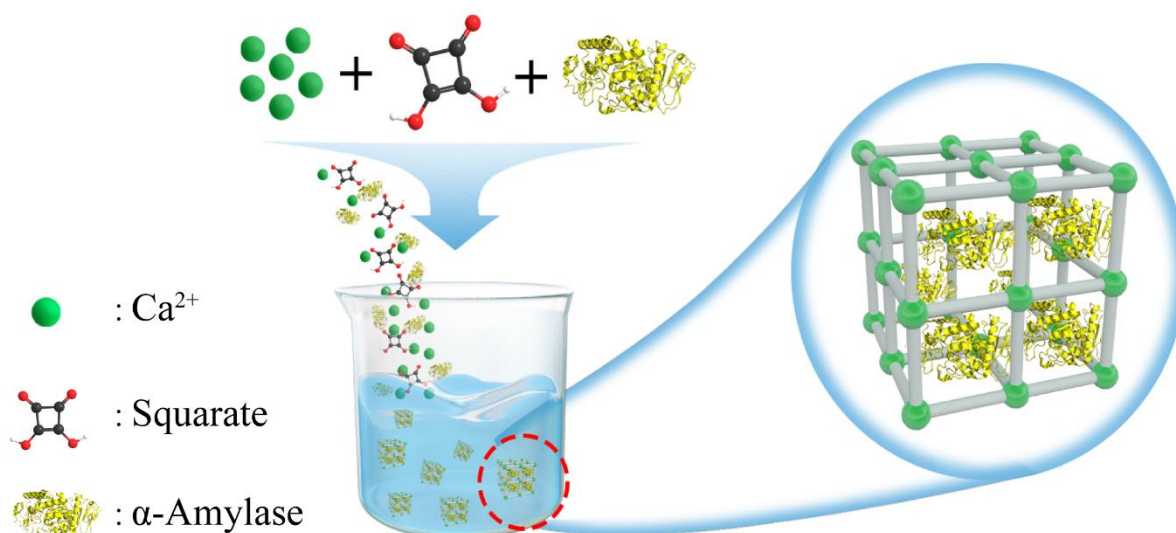

82

83 **Scheme 1.** Schematic description of enzyme@UTSA-280 preparation by in-situ method.

84

85 **2. Materials and methods**

86 *2.1 Materials and reagents*

87 Squaric acid (98%), calcium nitrate tetrahydrate ($\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$, 99%), starch
 88 (analytical grade) and pullulan (analytical grade) were purchased from Mucklin (Shanghai,
 89 China). α -Amylase (from *Bacillus subtilis*, 4000 U g^{-1}) was obtained from Coolaber (Beijing,
 90 China). Glucoamylase (from *Aspergillus niger* variant strain, >100,000 U g^{-1}) was purchased
 91 from Meilunbio (Dalian, China). Pullulanase (from *Klebsiella*, >1000 U g^{-1}) was obtained from
 92 Mucklin (Shanghai, China). Citric acid ($\geq 99.5\%$), sodium citrate dihydrate (99%), fluorescein
 93 isothiocyanate (FITC, $\geq 90\%$), HEPES buffer solution (pH 7.0), MES monohydrate (99%),
 94 polyvinylpyrrolidone (PVP, MW: 10 kDa) were supplied by Mucklin (Shanghai, China). All
 95 enzymes were further purified before use (Supplementary data). All solvents were of analytical
 96 grade and used as received.

97

98 *2.2 Synthesis of materials*

99 *2.2.1 Synthesis of UTSA-280*

100 UTSA-280 was synthesized as follows. Aqueous solutions of $\text{Ca}(\text{NO}_3)_2 \cdot 4\text{H}_2\text{O}$ (2 mL,
101 26 mg mL⁻¹) and sodium squarate (2 mL, 15 mg mL⁻¹) were mixed under stirring. The reaction
102 then proceeded for 1 h at room temperature. The resulted white crystals were washed 3 times
103 with water, and collected by centrifugation.

104

105 2.2.2 Synthesis of enzyme@UTSA-280

106 Enzyme@UTSA-280 was prepared by using in situ method. A solution of $\text{Ca}(\text{NO}_3)_2 \cdot$
107 $4\text{H}_2\text{O}$ (2 mL, 26 mg mL⁻¹) was mixed with a solution of sodium squarate (2 mL, 15 mg mL⁻¹)
108 containing enzymes at various concentrations, and reaction proceeded for 1 h at room
109 temperature. The resulted enzyme@UTSA-280 crystals were washed 3 times with water, and
110 collected by centrifugation.

111

112 2.3 Calculation of encapsulation efficiency and loading content

113 The encapsulation efficiency and loading content of enzymes was determined via standard
114 Bradford assay. Typically, the enzyme encapsulation efficiency of the preparations was
115 calculated via determining the enzyme concentration of the supernatant solution before and
116 after encapsulation by Bradford assay. The encapsulation efficiency and loading content were
117 calculated from the following formulae:

$$\text{Encapsulation efficiency \%} = \frac{C_0 - C_s}{C_0} \times 100\% \quad (1)$$

118 Where C_0 is the initial enzyme concentration before encapsulation, and C_s is the enzyme
119 concentration of supernatant after encapsulation.

$$\text{Loading content (mg mg}^{-1}\text{)} = \frac{W_0 - W_s}{W_M - (W_0 - W_s)} \quad (2)$$

120 Where W_0 is the weight of enzyme before encapsulation, W_s is the enzyme weight in
121 supernatant after encapsulation, and W_M is the weight of enzyme@UTSA-280.

122

123 2.4 Characterization

124 X-ray diffraction (XRD) patterns were recorded in the 2θ range from 5 to 50° on a Rigaku
125 d_{\max} 2500 diffractometer using Cu $K\alpha$ ($\lambda = 1.5418 \text{ \AA}$) radiation, with a scan speed of 1 sec/step,
126 and a step size of 0.02° . Fourier transform infrared (FT-IR) spectra were registered using a
127 Thermo Fisher spectrometer in ATR mode. 128 scans were made for each measurement in the
128 wavenumber range from 500 to 4000 cm^{-1} at a resolution of 2 cm^{-1} . Circular dichroism (CD)
129 measurements were performed using a spectropolarimeter BioLogic MOS-450. The spectra
130 were collected at a rate of 60 nm per minute and a response time of 16 s. Scanning electron
131 microscopy (SEM) was realized using JSM-7610F field-emission microscope. Freeze-dried
132 crystals were gold-coated for 90 s and observed using an electron beam at accelerating voltage
133 of 10.0 kV.

134

135 2.5 Activity test of α -amylase

136 The activity of α -amylase was determined according to the 3, 5-dinitrosalicylic acid
137 (DNS) method [12]. 2 mg of α -amylase@UTSA-280 was placed in 1 mL of citrate buffer (50
138 mM, pH 6.0), and released α -amylase was determined by using Bradford method. The
139 concentration of original and released α -amylase was adjusted to 0.1 mg mL^{-1} . $50 \mu\text{L}$ of original
140 α -amylase or released α -amylase ($50 \mu\text{g mL}^{-1}$) were added in 5 mL of HEPES buffer (50 mM,
141 pH 7.0) containing 1.0 wt% soluble starch. The relative activity (%) was the ratio between the
142 activities of released and original α -amylases. All measurements were repeated three times.
143 The activity of pullulanase and glucoamylase was determined using the same method, and the
144 detailed steps are described in Supplementary data.

145

146 2.6 Enzymatic kinetic parameters determination

147 Enzymatic kinetic parameters were determined according to the literature [22]. The
148 kinetic constants (V_{max} , K_m , K_{cat}) were derived from Lineweaver Burke plot by using eq. 3 and
149 eq. 4.

$$1/V = (K_m/V_{max}) * 1/[S] + 1/V_{max} \quad (3)$$

$$K_{cat} = V_{max}/[e] \quad (4)$$

150 Where [S] is the substrate concentration, and [e] is the molar concentration of α -amylase.

151 To determine the kinetic parameters of released and pure α -amylase, experiments were
152 performed at 37 °C with different concentrations of soluble starch of 0.1 to 2.0 wt% in HEPES
153 buffer solution (pH 7.0), at an initial enzyme concentration of 10 $\mu\text{g mL}^{-1}$ and a reaction time
154 of 1 min. The amount of produced glucose was determined by DNS method.

155

156 2.7 Enzyme protection assay

157 Pure α -amylase powder (10 mg) and α -amylase@UTSA-280 composite (10 mg) were
158 treated by exposure to heat (80 °C), trypsin solution (1 mg mL^{-1}), and acetone for 1 h. After
159 treatment, α -amylase was released from UTSA-280 in citrate buffer (pH 6.0), and the enzyme
160 concentration was determined by using Bradford method. Then, the activity of pure and
161 released α -amylases was measured by using DNS method and compared to untreated enzymes.


162

163 3. Results and discussion

164 3.1 Characterization of UTSA-280

165 UTSA-280 was synthesized by reaction between calcium nitrate hexahydrate and sodium
166 squarate under mild conditions in water [23]. Sodium squarate was previously obtained by
167 neutralization of squaric acid using NaOH, as shown in Supplementary data [24]. In as-
168 synthesized UTSA-280, the Ca atom (pentagonal bipyramidal) is coordinated by seven O atoms
169 from five squarate linkers and one water molecule, resulting in one-dimensional channels (Fig.

170 1a). The hydrogen bonding between coordinated H₂O molecules and O atoms of squarate
 171 linkers could further stabilize the framework by restrain the rotation of the organic linkers (Fig.
 172 1b). The XRD pattern of UTSA-280 exhibits high crystallinity in comparison with the
 173 calculated pattern, as shown in Fig. 1c. The FT-IR spectrum of UTSA-280 shows various
 174 characteristic signals (Fig. 1d), especially those at 1088, 1450, and 3231 cm⁻¹, corresponding
 175 to C-O, C=C, and O-H bonds, respectively. TGA data reveal the good thermal stability of
 176 UTSA-280 (Fig. 1e). A weight loss of 7.2 % is observed from 50 to 96 °C, corresponding to
 177 the loss of H₂O molecules in the channels. Weight loss of 10.2 % between 156 to 303 °C
 178 corresponds to the loss of H₂O coordinated with Ca²⁺ ions. Weight loss beyond 392 °C results
 179 from the framework decomposition. UTSA-280 exhibits a cylindrical crystal structure as
 180 shown in Fig. 1f, in agreement with high crystallinity. All these data demonstrate the successful
 181 synthesis of uniform UTSA-280 crystals.

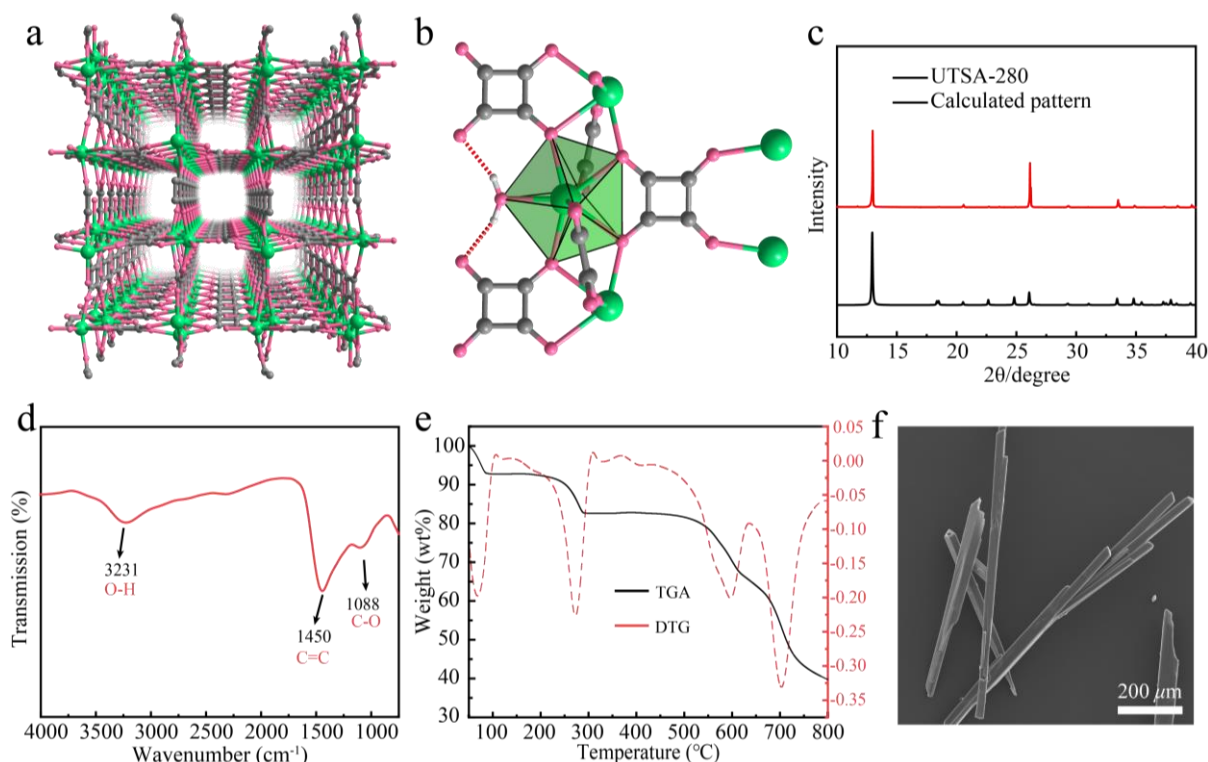

182
 183 **Fig. 1** Structure and characterization of UTSA-280: (a) Crystal structure of UTSA-280,
 184 showing one-dimensional channels viewed along the [001] direction. Green, red, and grey balls

185 represent Ca, O and C atoms, respectively. (b) Local coordination environment of the squarate
186 linkers and Ca atoms. (c) XRD pattern of UTSA-280. (d) Infrared spectrum of UTSA-280. (e)
187 TGA and DTG patterns of UTSA-280. (f) SEM image of UTSA-280.


188

189 3.2 Characterization of α -amylase@UTSA-280

190 α -amylase@UTSA-280 was synthesized in-situ under mild conditions. In this reaction, α -
191 amylase is added together with metal ions and ligand, and α -amylase is loaded during the
192 crystallization process of MOFs. Bradford method was employed to determine the enzyme
193 concentration in α -amylase@UTSA-280. A calibration curve was first established using α -
194 amylase as the standard. A good linearity was obtained from the regression line in the 0.1-1.5
195 mg mL⁻¹ range (Fig. 2a). The encapsulation efficiency and loading content of α -
196 amylase@UTSA-280 were then calculated (Fig. 2b-c). With increasing the initial enzyme
197 concentration from 1.0 to 5.0 mg mL⁻¹, the encapsulation efficiency decreases from 61% to
198 38%, and the loading content increases from 0.036 to 0.109 mg mg⁻¹. α -Amylase@UTSA-280
199 at enzyme concentration of 2 mg mL⁻¹ was selected for subsequent experiments as it has
200 suitable encapsulation efficiency (59.2 ± 1.0 %) and loading content (0.070 ± 0.004 mg mg⁻¹).

201 Fig. 2d shows the XRD patterns of α -amylase@UTSA-280 and UTSA-280. Both present
202 the same diffraction peaks, indicating that enzyme encapsulation didn't affect the crystalline
203 structure and crystallinity of UTSA-280, even at an enzyme concentration of 5 mg mL⁻¹ in the
204 synthesis process (Fig. S1). In the FT-IR spectra (Fig. 2e), a band assigned to the bending
205 vibration of the N-H group is detected at 1646 cm⁻¹ for α -amylase and α -amylase@UTSA-280,
206 but not for UTSA-280, thus demonstrating the successful synthesis of α -amylase@UTSA-280.
207 The thermal stability of α -amylase@UTSA-280 was evaluated by TGA under nitrogen
208 atmosphere in comparison with α -amylase (Fig. 2f). In the TGA thermogram of α -
209 amylase@UTSA-280, a weight loss of 6.9 % is observed from 50 to 96 °C, corresponding to

210 the loss of H₂O molecules. Weight loss of 9.9% between 168 to 287 °C belongs to α -amylase
 211 decomposition and the loss of H₂O coordinated with Ca ions in UTSA-280. Weight loss beyond
 212 430 °C mainly results from the MOF framework. In contrast, an almost continuous weight loss
 213 is observed for α -amylase beyond 200°C due to its decomposition. In SEM image of α -
 214 amylase@UTSA-280 (Fig. 2g), rod-like aggregates of crystals are observed. α -Amylase was
 215 labeled by FITC (Supplementary data). Confocal laser scanning microscopy (CLSM) shows a
 216 uniform distribution of FITC-labeled α -amylase in UTSA-280 (Fig. 2h). All these data prove
 217 that α -amylase is successfully encapsulated in UTSA-280.

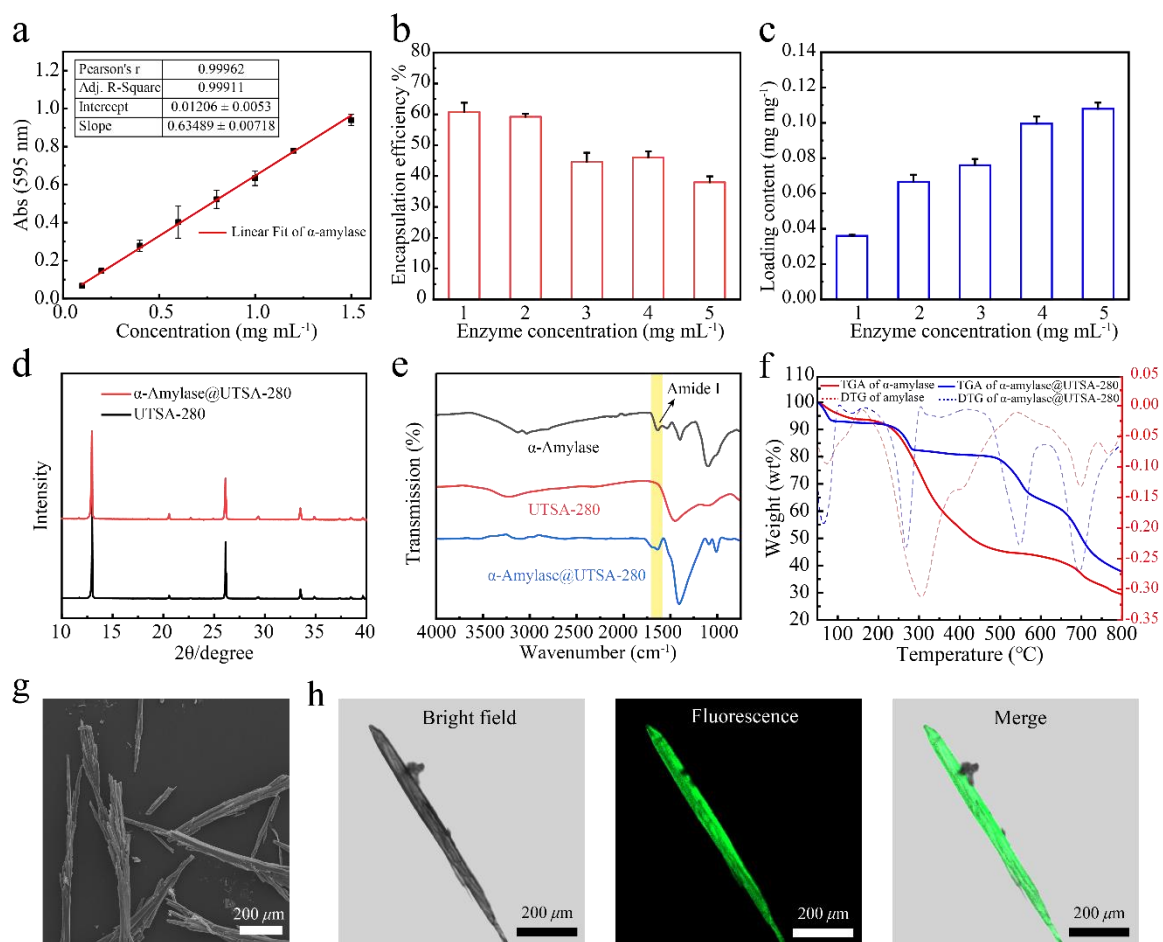

218
 219 **Fig. 2.** Characterization of α -amylase@UTSA-280: (a) linear fitting of α -amylase by Bradford
 220 method; (b-c) the encapsulation efficiency and loading content of α -amylase@UTSA-280; (d)
 221 XRD patterns of UTSA-280 and α -amylase@UTSA-280; (e) FT-IR spectra of α -amylase,
 222 UTSA-280, and α -amylase@UTSA-280; (f) TGA and DTG patterns of α -amylase and α -

223 amylase@UTSA-280; (g) SEM image of α -amylase@UTSA-280; (h) CLSM images α -
224 amylase@UTSA-280.


225

226 3.3 Enzyme release behavior of α -amylase@UTSA-280

227 The absorbance of α -amylase was determined at 540 nm in MES buffers at various pH in
228 order to determine the suitable releasing pH value. As shown in Fig. 3a, α -amylase exhibits
229 high activity between pH 5.0-7.0. Therefore, the enzyme release behavior from α -
230 amylase@UTSA-280 was evaluated in this pH range (Fig. 3b). Biphasic release profiles are
231 observed in all cases with initial faster release followed by slower release. The release rate
232 increases with pH decrease, which could be attributed to the accelerated degradation of MOFs
233 under acidic conditions. The degradability and enzyme loading properties of UTSA-280 make
234 it a potential enzyme preparation material.

235 Maintaining enzyme conformation during the storage and operation process is crucial for
236 the application of enzymes. Thus, the secondary structure of α -amylase was determined using
237 circular dichroism (CD) to confirm the protective effect of MOFs. Released α -amylase was
238 collected via ultrafiltration with 8 kDa MWCO device to remove impurities (digested ligands
239 and metal salts). Notably, both pristine α -amylase and released α -amylase exhibit a typical α -
240 helix structure without any difference [25], suggesting that the in-situ encapsulation process
241 did not affect the conformation of enzyme (Fig. 3c).

242

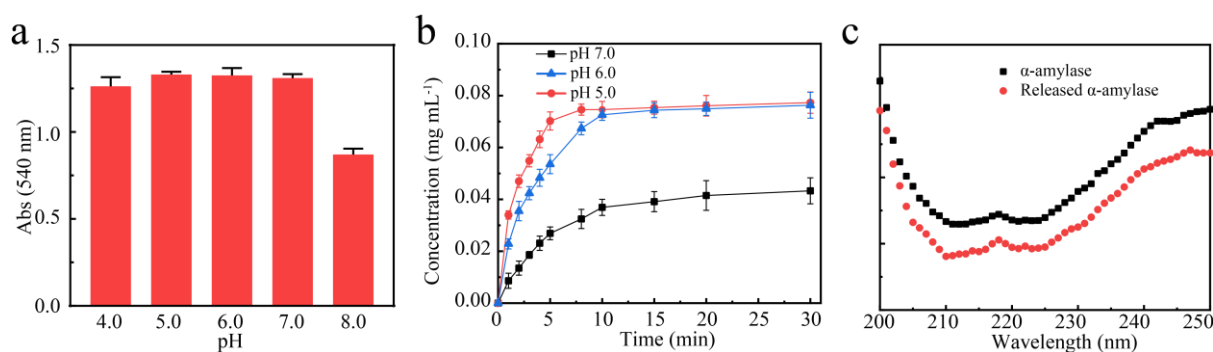


243 **Fig. 3** (a) Absorbance of α -amylase at different pH values; (b) enzyme release profiles in citrate
244 buffer (50 mM, pH 5.0-7.0); (c) CD spectra of pristine α -amylase and α -amylase released from
245 UTSA-280.

246

247 *3.4 Catalytic activity test*

248 The catalytic activity of released α -amylase was determined using soluble starch as the
249 substrate in HEPES buffer (50 mM, pH 7.0). The concentration of produced glucose was
250 measured using a previously established calibration curve (Fig. S2) [26]. Fig. 4a shows the
251 glucose concentration changes as a function of reaction time in the presence of pristine α -
252 amylase, released α -amylase, α -amylase + $\text{Na}_2\text{C}_4\text{O}_4$, α -amylase + Ca^{2+} , and UTSA-280. The
253 added concentrations of Ca^{2+} and $\text{Na}_2\text{C}_4\text{O}_4$ were 11.75 mM, *i.e.* equal to that of released α -
254 amylase. Higher glucose concentration is obtained for released α -amylase during the whole
255 reaction period up to 20 min. The relative activity of released α -amylase is 177.8% compared
256 to pristine α -amylase. In contrast, direct addition of Ca^{2+} or squaric acid has no effect on the
257 enzyme activity, and pure UTSA-280 material has no catalytic effect. Further investigation
258 suggests that a relatively high concentration (100 mM) of free Ca^{2+} is required to achieve a
259 relative activity of 127.0 % at an incubation enzyme concentration of 2 mg mL⁻¹ (Fig. 4c), and
260 the Ca^{2+} concentration during synthesis (79.2 mM) does not have such a promoting effect. Fig.
261 4d shows that sodium squarate has little influence on the activity of α -amylase. Therefore, the
262 enhanced activity is likely related to the release process. These results suggest that metal ion
263 activators from the enzyme/MOF matrix could strongly ameliorate the enzymatic activity,
264 which might be attributed to the enhanced interactions between calcium ions and enzyme
265 molecules during the release process.

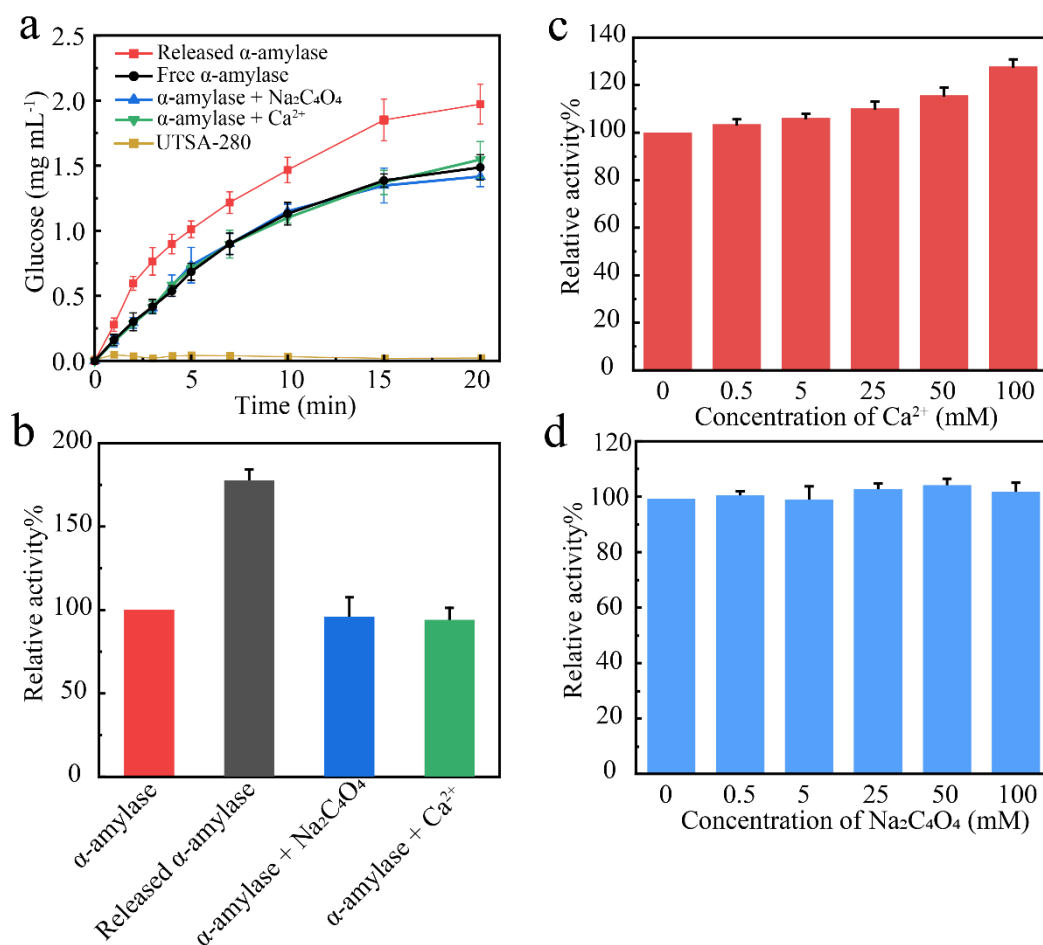

266


267 **Fig. 4** (a) Glucose concentration changes as a function of reaction time in the presence of
 268 pristine α -amylase, released α -amylase, α -amylase + Na₂C₄O₄, α -amylase + Ca²⁺, and UTSA-
 269 280; (b) relative activity of α -amylase, released α -amylase, α -amylase + Na₂C₄O₄, and α -
 270 amylase + Ca²⁺; (c) relative activity of α -amylase in the presence of Ca²⁺ at different
 271 concentrations; (d) relative activity of α -amylase in the presence of Na₂C₄O₄ at different
 272 concentrations. Test conditions: 1 wt% soluble starch solution in HEPES buffer (50 mM, pH
 273 7.0) at 37 °C.

274

275 3.5 Exploration of mechanism for the increase of enzymatic activity

276 Energy dispersive X-ray spectroscopy (EDX) was used to characterize the released α -
 277 amylase in comparison with purchased one so as to figure out the mechanism for the increase

278 of enzymatic activity. Released α -amylase and α -amylase incubated with Ca^{2+} were collected
279 via ultrafiltration, 3 times washing with deionized water to remove free Ca^{2+} , and freeze-
280 drying. As shown in Fig. 5a-c and Table 1, released α -amylase has higher Ca^{2+} content (10.7
281 ± 2.3 % of weight, 4.3 ± 1.1 % of atom) than purchased α -amylase (2.8 ± 0.4 % of weight, 0.7
282 ± 0.1 % of atom) and α -amylase incubated with Ca^{2+} (4.7 ± 0.6 % of weight, 1.6 ± 0.2 % of
283 atom). Inductively coupled plasma-optical emission spectrometry (ICP-OES) was also used to
284 quantify the Ca^{2+} content of these three groups, as shown in Fig. S3. The Ca^{2+} content of
285 released α -amylase, pristine α -amylase, and α -amylase incubated with Ca^{2+} are 99.7 ± 3.3 ,
286 4.7 ± 1.1 , and $29.2 \pm 4.7 \mu\text{g mg}^{-1}$, respectively. ICP-OES data are consistent with those of EDX,
287 which revealed that MOF encapsulation enhances enzyme activity more effectively than direct
288 addition of metal ions. These results suggest that the improved enzymatic activity could result
289 from more interaction between Ca^{2+} ions and α -amylase. The enzymatic kinetic parameters of
290 α -amylase released from UTSA-280 were determined by using Lineweaver Burke plot (Fig.
291 S4) and Michaelis-Menten model [22, 27]. The results revealed that released α -amylase has a
292 V_{max} of 0.25 mM s^{-1} , K_m of 0.27 mM , and K_{cat} of $1.25 \times 10^3 \text{ s}^{-1}$, while untreated α -amylase has
293 V_{max} , K_m and k_{cat} of 0.14 mM s^{-1} , 0.46 mM and $0.69 \times 10^3 \text{ s}^{-1}$, respectively (Table 2). The lower
294 K_m value of released α -amylase implies higher affinity towards substrates while the higher K_{cat}
295 of released α -amylase could be attributed to the activation effect of Ca^{2+} from UTSA-280,
296 which is consistent with literature data [28].

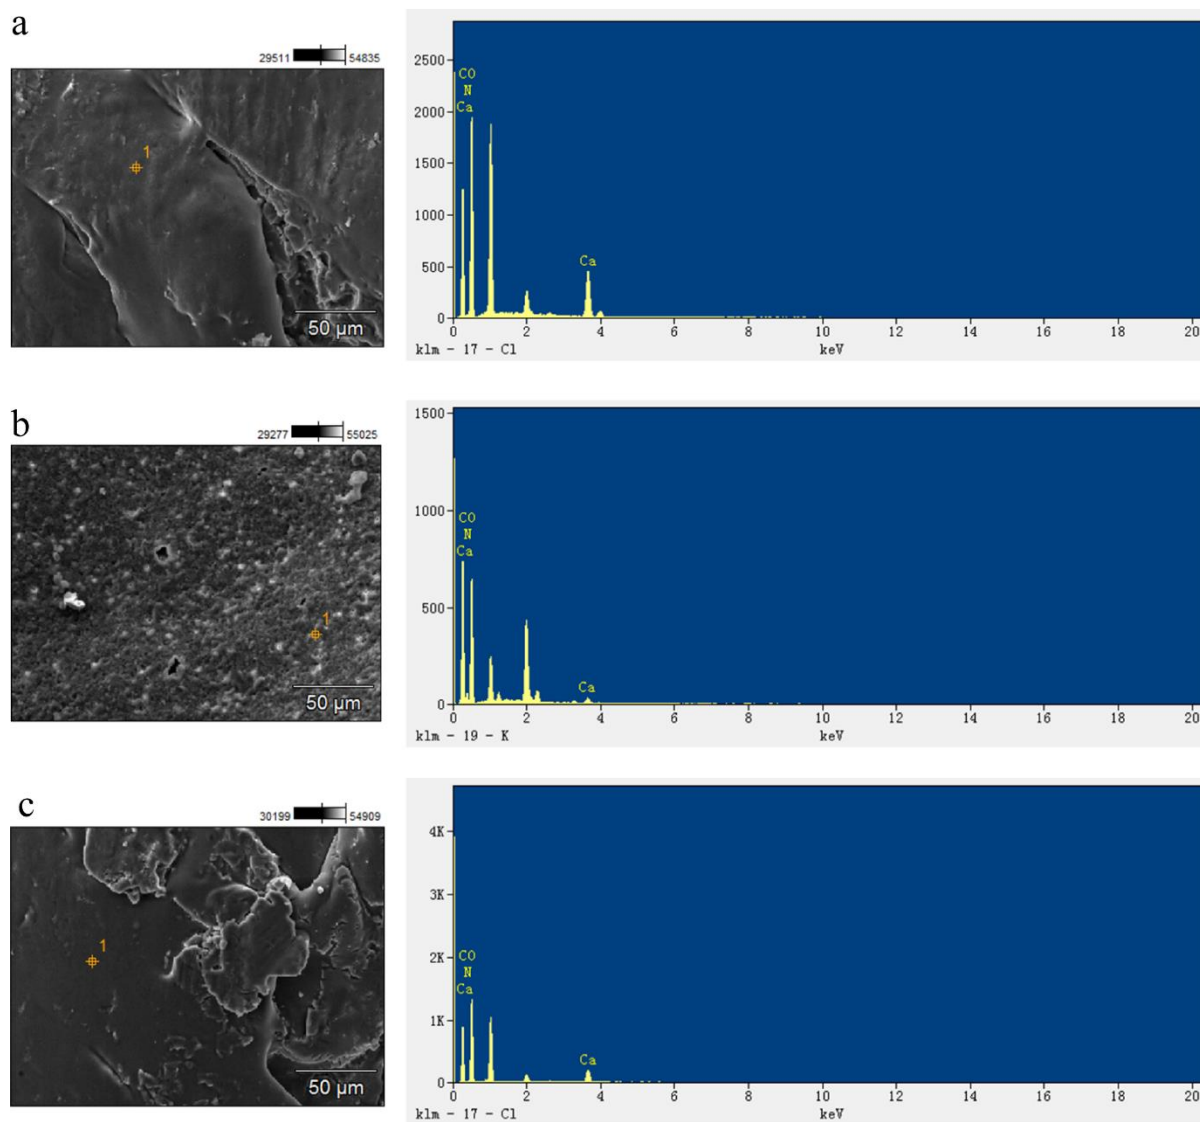

297

298 **Fig. 5.** Energy dispersive X-ray spectroscopy (EDX) of (a) released α -amylase, (b) pristine α -
 299 amylase, and (c) α -amylase incubated with Ca^{2+} (11.75 mM) for 1 h. (n=3)

300

301 **Table 1.** Element contents of released α -amylase, pristine α -amylase, and α -amylase incubated
 302 with Ca^{2+} (11.75 mM) for 1 h determined by EDX (n=3)

	Element	Weight %	Atom %
Released α -amylase	C	15.8 ± 1.8	20.9 ± 1.9
	O	65.9 ± 0.8	65.9 ± 0.4

	N	7.8 ± 0.2	8.9 ± 0.4
	Ca	10.7 ± 2.3	4.3 ± 1.1
	C	22.3 ± 0.5	29.3 ± 2.1
	O	60.1 ± 3.6	53.0 ± 4.8
Pristine α -amylase	N	14.8 ± 0.1	17.3 ± 2.7
	Ca	2.8 ± 0.4	0.7 ± 0.1
	C	12.7 ± 0.5	14.6 ± 3.1
	O	74.2 ± 1.3	72.7 ± 2.1
α -amylase incubated with Ca^{2+}	N	8.5 ± 1.2	11.2 ± 1.3
	Ca	4.7 ± 0.6	1.6 ± 0.2

303

304 Two other enzymes, pullulanase (Ca^{2+} activating enzyme) and glucoamylase (non Ca^{2+}
305 activating enzyme) were also encapsulated in UTSA-280 to better understand the activation
306 effect of UTSA-280. The enzyme concentration was determined by Bradford method using
307 enzyme standard calibration curves (Fig. S5-6). And the encapsulation efficiency and loading
308 content of pullulanase ($64.1 \pm 2.4\%$, $0.150 \pm 0.011 \text{ mg mg}^{-1}$) and glucoamylase ($44.2 \pm 3.2\%$,
309 $0.110 \pm 0.004 \text{ mg mg}^{-1}$) were then obtained (Fig. S7). FT-IR spectra and CLSM data prove the
310 successful encapsulation of the two enzymes in UTSA-280 (Fig. S8-10). In addition, XRD and
311 SEM data demonstrate the high crystallinity of UTSA-280 after enzyme encapsulation (Fig.
312 S11-12). Then, pullulanase and glucoamylase were released from UTSA-280 and their catalytic
313 activity was evaluated in the pH range from pH 4.0 to 8.0 (Fig. S13-14). As shown in Fig. S15,
314 the activity of released pullulanase shows a dramatic increase ($201 \pm 28 \%$), which may be
315 attributed to the fact that pullulanase is a Ca^{2+} activated enzyme. Meanwhile, glucoamylase,
316 which is not a Ca^{2+} activated enzyme, shows no activity increase. These findings prove that

317 this strategy can be applied to other Ca^{2+} activated amylases, suggesting that MOFs could serve
318 as metal ion activated enzyme preparation. Thus MOFs materials with different metal ions can
319 be selected according to metal ions-activated enzymes.



320 **Table 2** Kinetic parameters for released α -amylase and pristine α -amylase.

	V_{max} [mM s^{-1}]	K_m [mM]	K_{cat} [10^3 s^{-1}]
Released α -amylase	0.25	0.27	1.25
Pristine α -amylase	0.14	0.46	0.69

321

322 3.6 Size control of UTSA-280

323 The size control of MOFs is important as it affects the release performance of enzymes.
324 Polyvinylpyrrolidone (PVP) is a water soluble polymer with low toxicity and high thermal
325 stability [29]. PVP is widely used as a capping agent to prevent colloidal aggregation, thus
326 allowing to control the size of nanoparticles, especially MOFs [30]. The size of UTSA-280 was
327 adjusted by using PVP to further modulate the release performance of α -amylase from UTSA-
328 280. As shown in Fig. 7a-f and Fig. S16, the crystal size of UTSA-280 decreases from above
329 $1000 \mu\text{m}$ to below $100 \mu\text{m}$ with increase of PVP concentration from 0.1 to 1.0 mg mL^{-1} . It is
330 also noteworthy that larger crystal size of UTSA-280 leads to higher loading content (Fig. 6g),
331 and thus leading to higher final concentration of released enzyme (Fig. 6h). XRD patterns show
332 that α -amylase@UTSA-280 synthesized using PVP as capping agent presents the same
333 crystalline structure as that synthesized without PVP (Fig. S17).

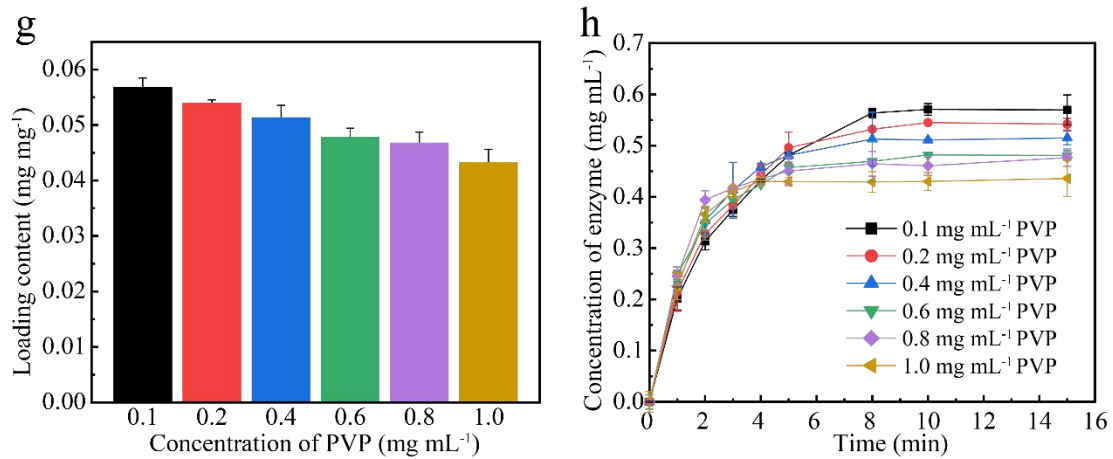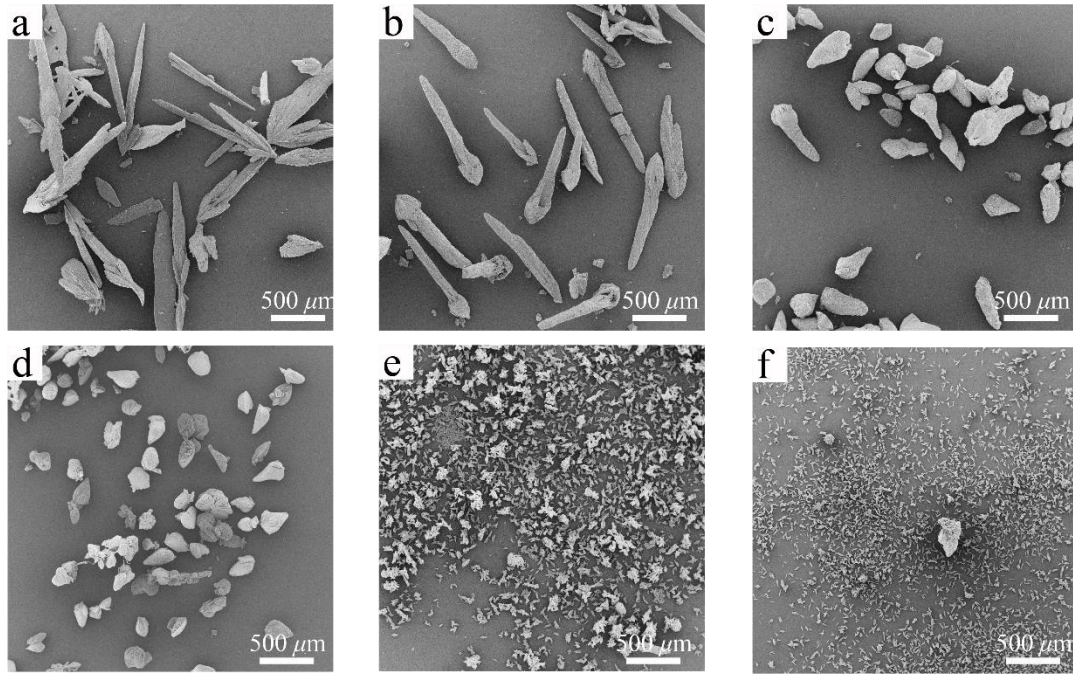


334
 335 **Fig. 6** (a-f) SEM images (30 ×) of, (g) loading content of, and (h) enzyme release profiles from
 336 α -amylase@UTSA-280 synthesized using PVP capping agent at concentrations of 0.1, 0.2, 0.4,
 337 0.6, 0.8, 1.0 mg mL⁻¹. Test conditions: 10 mg material in 1 mL citrate buffer (50 mM, pH 6.0)
 338 at room temperature.

339
 340 *3.7 Protection assay of α -amylase@UTSA-280*

341 It is of major importance to preserve enzyme activity during the storage and operation
 342 process. The confined space created by MOFs should provide excellent protection to enzymes
 343 [30]. The protection performance of UTSA-280 to α -amylase was evaluated by exposure to

344 heat (80 °C), trypsin (1 mg mL⁻¹), and organic solvent (acetone) for 1 h. As shown in Fig. 7,
345 the relative activity of α -amylase decreases to 67.2, 37.4, and 76.5% after treatment by heat,
346 trypsin, and acetone, respectively. In contrast, the relative activity of enzyme in α -
347 amylase@UTSA-280 is 80.1, 65.6, and 86.4% after the same treatments. These findings
348 indicate that UTSA-280 could efficiently protect α -amylase against harsh conditions.
349 Moreover, sodium squarate presents good biocompatibility according to MTT and live-dead
350 staining experiments. The cell viability is above 81% for all groups (Fig. S18), and no apparent
351 apoptosis is observed (Fig. S19). Therefore, UTSA-280 could facilitate the storage, transport,
352 and operation of enzyme preparations.

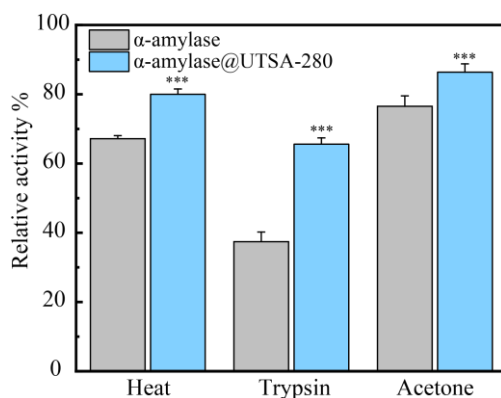

353
354 **Fig. 7** Relative activity of nude α -amylase and α -amylase@UTSA-280 after 1 h exposure to
355 heat (80 °C), trypsin (1 mg mL⁻¹), organic solvent (acetone). The enzyme activity was measured
356 in HEPES buffer (50 mM, pH 7.0). (n=3, *** p<0.001)

357

358 4. Conclusions

359 MOFs are able to function as metal ion activator and protector, and is thus a material of
360 choice for enzyme preparations, especially metal-activated enzyme preparations. However,
361 there is no research reported on MOFs as a metal ion activated enzyme preparation, so far. In
362 this work, α -amylase and pullulanase were successfully encapsulated in situ in a Ca²⁺ based
363 MOF (UTSA-280) under mild conditions. The enzyme@UTSA-280 composite crystals could

364 degrade rapidly in acidic environment and release enzyme. Importantly, the structural integrity
365 of released enzyme was preserved as evidenced by CD spectra. The relative activity of released
366 α -amylase and pullulanase increased to 177.8 % and 201.0 % as compared to original enzyme.
367 Mechanistic investigation proves that the increase of enzyme activity could be attributed to the
368 activation by Ca^{2+} . Ca^{2+} could activate α -amylase and pullulanase, but has no effect on
369 glucoamylase which is not Ca^{2+} activated enzyme. Enzyme activity tests after exposure to heat,
370 trypsin, and acetone showed that α -amylase@UTSA-280 provides good protection to enzyme
371 molecules. In addition, the size and enzyme release rate of α -amylase@UTSA-280 can be
372 tailored by using PVP capping agent at different concentrations. Compared with current
373 enzyme preparations, this MOFs based platform present several advantages. Firstly, MOFs
374 could combine the advantages of metal ion activation and enzyme protection, especially for
375 metal ion activating enzymes. Secondly, the preparation conditions are milder than those used
376 in traditional methods such as salting out or spray drying. Thirdly, this platform could avoid
377 the use of excessive additives to maintain the enzyme conformation on storage conditions. Last
378 but not least, this platform can efficiently activate enzymes by providing small amount of
379 activator. Compared to direct addition of activator, this platform is more friendly to
380 applications which require post-processing and purification. Therefore, enzyme@MOFs
381 preparations are most promising for applications in the field of enzyme production, biocatalytic
382 production, and food processing.

383

384 **Acknowledgments**

385 The work was financially supported by the Shandong Provincial Natural Science Foundation
386 (ZR2020QH271, ZR2021ME208, ZR2022ME083).

387

388 **Author Contributions**

389 J. Song did most experiments, data analysis, and wrote the manuscript; X. Shen, and F. Liu
390 prepared the specimens and made FT-IR and CD measurements, X. Zhao, Y. Wang, and S.
391 Wang performed kinetic studies of enzymes, P. Wang made FITC-labeling of enzyme; J. Wang,
392 F. Su and S. Li co-initiated the work, and revised the manuscript. All authors discussed and
393 contributed the discussion and analysis of the results regarding the manuscript. All authors
394 have given approval for the final version of the manuscript.

395

396 **Declaration of competing interest**

397 The authors declare that they have no known competing financial interests or personal
398 relationships that could have appeared to influence the work reported in this paper.

399

400

401 Reference

- 402 [1] C. Silva, M. Martins, S. Jing, J. Fu, A. Cavaco-Paulo, Practical insights on enzyme stabilization, *Crit. Rev.*
403 *Biotechnol.* 38 (2018), 335-350.
- 404 [2] M.A. Singer, S. Lindquist, Multiple effects of trehalose on protein folding in vitro and in vivo, *Mol. Cell* 1
405 (1998), 639-648.
- 406 [3] S.A. Costa, T. Tzanov, A. Filipa Carneiro, A. Paar, G.M. Gübitz, A. Cavaco-Paulo, Studies of stabilization of
407 native catalase using additives, *Enzyme Microb. Technol.* 30 (2002), 387-391.
- 408 [4] R.V. Parthasarathy, C.R. Martin, Synthesis of polymeric microcapsule arrays and their use for enzyme
409 immobilization, *Nature* 369 (1994), 298-301.
- 410 [5] J.T. Duskey, I. Ottonelli, A. Rinaldi, I. Parmeggiani, B. Zambelli, L.Z. Wang, R.K. Prud'homme, M.A.
411 Vandelli, G. Tosi, B. Ruozi, Tween® preserves enzyme activity and stability in PLGA nanoparticles,
412 *Nanomaterials* 11 (2021), 2946.
- 413 [6] T. Fan, J. Qin, X. Meng, J. Li, Q. Liu, G. Wang, Biodegradable membrane of poly (l-lactide acid-dioxanone-
414 glycolide) and stereocomplex poly (lactide) with enhanced crystallization and biocompatibility, *Front.*
415 *Bioeng. Biotechnol.* 10 (2022).
- 416 [7] B.t. Limoges, J.-M. Savéant, Catalysis by immobilized redox enzymes. Diagnosis of inactivation and
417 reactivation effects through odd cyclic voltammetric responses, *J. Electroanal. Chem.* 562 (2004), 43-52.
- 418 [8] K.A. Shisler, R.U. Hutcheson, M. Horitani, K.S. Duschene, A.V. Crain, A.S. Byer, E.M. Shepard, A.
419 Rasmussen, J. Yang, W.E. Broderick, J.L. Vey, C.L. Drennan, B.M. Hoffman, J.B. Broderick, Monovalent
420 Cation Activation of the Radical SAM Enzyme Pyruvate Formate-Lyase Activating Enzyme, *J. Am. Chem.*
421 *Soc.* 139 (2017), 11803-11813.
- 422 [9] S.N. Gummadi, T. Panda, Purification and biochemical properties of microbial pectinases—a review, *Process*
423 *Biochem.* 38 (2003), 987-996.
- 424 [10] J. He, S. Sun, M. Lu, Q. Yuan, Y. Liu, H. Liang, Metal-nucleobase hybrid nanoparticles for enhancing the
425 activity and stability of metal-activated enzymes, *Chem. Commun.* 55 (2019), 6293-6296.
- 426 [11] N. Goyal, J. Gupta, S. Soni, A novel raw starch digesting thermostable α -amylase from *Bacillus* sp. I-3 and
427 its use in the direct hydrolysis of raw potato starch, *Enzyme Microb. Technol.* 37 (2005), 723-734.
- 428 [12] S.-M. Liao, G. Liang, J. Zhu, B. Lu, L.-X. Peng, Q.-Y. Wang, Y.-T. Wei, G.-P. Zhou, R.-B. Huang, Influence
429 of calcium ions on the thermal characteristics of α -amylase from thermophilic *Anoxybacillus* sp. GXS-BL,
430 *Protein Pept. Lett.* 26 (2019), 148-157.
- 431 [13] D.S. Bush, L. Sticher, R. Van Huystee, D. Wagner, R.L. Jones, The calcium requirement for stability and
432 enzymatic activity of two isoforms of barley aleurone α -amylase, *J. Biol. Chem.* 264 (1989), 19392-19398.
- 433 [14] W. Mao, J. Kinsella, Amylase activity in banana fruit: properties and changes in activity with ripening, *J.*
434 *Food Sci.* 46 (1981), 1400-1403.
- 435 [15] Y. Liu, W. Wang, W. Zhang, Y. Dong, F. Han, M. Raza, L. Liu, T. Tan, Y. Feng, Structure of a thermostable
436 methionine adenosyltransferase from *Thermus thermophilus* HB27 reveals a novel fold of the flexible loop,
437 *RSC adv.* 6 (2016), 41743-41750.
- 438 [16] C. Doonan, R. Riccò, K. Liang, D. Bradshaw, P. Falcaro, Metal–Organic Frameworks at the Biointerface:
439 Synthetic Strategies and Applications, *Acc. Chem. Res.* 50 (2017), 1423-1432.
- 440 [17] W. Liang, P. Wied, F. Carraro, C.J. Sumby, B. Nidetzky, C.-K. Tsung, P. Falcaro, C.J. Doonan, Metal–
441 Organic Framework-Based Enzyme Biocomposites, *Chem. Rev.* 121 (2021), 1077-1129.

442 [18] W. Liang, P. Wied, F. Carraro, C.J. Sumby, B. Nidetzky, C.-K. Tsung, P. Falcaro, C.J. Doonan, Metal–
443 Organic Framework-Based Enzyme Biocomposites, *Chemical Reviews* 121 (2021), 1077-1129.

444 [19] M. Mobini-Dehkordi, F.A. Javan, Application of alpha-amylase in biotechnology, *J. Biol. Today World* 1
445 (2012), 39-50.

446 [20] N. Declerck, M. Machius, P. Joyet, G. Wiegand, R. Huber, C. Gaillardin, Hyperthermostabilization of
447 *Bacillus licheniformis* α -amylase and modulation of its stability over a 50 C temperature range, *Protein Eng.*
448 16 (2003), 287-293.

449 [21] J.W. Torrance, M.W. MacArthur, J.M. Thornton, Evolution of binding sites for zinc and calcium ions playing
450 structural roles, *Proteins: Struct., Funct., Bioinf.* 71 (2008), 813-830.

451 [22] F. ADNAN, Kinetics and thermodynamic studies of alpha amylase from *Bacillus licheniformis* mutant, *Pak.*
452 *J. Bot* 42 (2010), 3507-3516.

453 [23] R.-B. Lin, L. Li, H.-L. Zhou, H. Wu, C. He, S. Li, R. Krishna, J. Li, W. Zhou, B. Chen, Molecular sieving of
454 ethylene from ethane using a rigid metal–organic framework, *Nat. Mater.* 17 (2018), 1128-1133.

455 [24] S. Cohen, S.G. Cohen, Preparation and Reactions of Derivatives of Squaric Acid. Alkoxy-, Hydroxy-, and
456 Aminocyclobutenediones1, *J. Am. Chem. Soc.* 88 (1966), 1533-1536.

457 [25] T. Konno, Conformational diversity of acid - denatured cytochrome c studied by a matrix analysis of far -
458 UV CD spectra, *Protein Sci.* 7 (1998), 975-982.

459 [26] G.L. Miller, Use of dinitrosalicylic acid reagent for determination of reducing sugar, *Anal. Chem.* 31 (1959),
460 426-428.

461 [27] L. Michaelis, M.L. Menten, Die kinetik der invertinwirkung, *Biochem. z* 49 (1913), 352.

462 [28] H. Torabizadeh, M. Tavakoli, M. Safari, Immobilization of thermostable α -amylase from *Bacillus*
463 *licheniformis* by cross-linked enzyme aggregates method using calcium and sodium ions as additives, *J. Mol.*
464 *Catal. B: Enzym.* 108 (2014), 13-20.

465 [29] P. Arul, S.A. John, Size controlled synthesis of Ni-MOF using polyvinylpyrrolidone: New electrode material
466 for the trace level determination of nitrobenzene, *J. Electroanal. Chem.* 829 (2018), 168-176.

467 [30] T.-H. Wei, S.-H. Wu, Y.-D. Huang, W.-S. Lo, B.P. Williams, S.-Y. Chen, H.-C. Yang, Y.-S. Hsu, Z.-Y. Lin,
468 X.-H. Chen, Rapid mechanochemical encapsulation of biocatalysts into robust metal–organic frameworks,
469 *Nat. Commun.* 10 (2019), 1-8.

470

471