



# Exploring the technological maturity of hydrogen production by hydrolysis of sodium borohydride

Umit Demirci

## ► To cite this version:

Umit Demirci. Exploring the technological maturity of hydrogen production by hydrolysis of sodium borohydride. International Journal of Hydrogen Energy, 2023, 10.1016/j.ijhydene.2023.04.176 . hal-04093600

**HAL Id: hal-04093600**

**<https://hal.umontpellier.fr/hal-04093600>**

Submitted on 10 May 2023

**HAL** is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

# Exploring the technological maturity of hydrogen production by hydrolysis of sodium borohydride

Umit B. Demirci <sup>1,\*</sup>

<sup>1</sup> Institut Européen des Membranes, IEM – UMR 5635, Univ Montpellier, ENSCM, CNRS, Montpellier, France

\* [umit.demirci@umontpellier.fr](mailto:umit.demirci@umontpellier.fr)

## Abstract

Sodium borohydride  $\text{NaBH}_4$  (SB) has been rediscovered in the late 1990s and been presented as a promising hydrogen storage material owing to its high gravimetric hydrogen density of 10.8 wt% and ability to produce  $\text{H}_2$  by hydrolysis at ambient conditions. This looked promising, but soon hydrolysis of SB encountered numerous obstacles. In 2015, a progress report (Int J Hydrogen Energy 2015;40:2673-91) showed that the 2000-2014 research did not overcome all of the obstacles, making SB far from being technologically mature. Eight years have passed since 2015. Have we put more effort into all aspects relating to hydrolysis of SB? If so, do we have produced scaled-up technologies and prototypes, of which we would have a better knowledge? Have we been able to gain in technological readiness level? Answering these questions is the main objective of this article. A secondary objective is to summarize the newly acquired knowledge. Five main observations stand out. First, the 2015-2022 period is regrettably similar to the 2000-2014 since, again, catalysts have dominated the field and the other aspects (e.g. recycling of the by-product to regenerate SB, scale-up and implementation) have received little attention. Second, hydrolysis of SB still runs into numerous obstacles, some of the obstacles being known since a long time and other ones being relatively new and unknown. Third, there has been little gain in terms of technological readiness level while few research groups have shown that there is room for new ideas and innovation. Fourth, energy, exergy and economic analyses are needed to evaluate the overall cost of  $\text{H}_2$  from SB. Fifth, SB has not effectively thought from the end user perspective. In conclusion, many obstacles remain to be overcome before hydrolysis of SB can be a commercial solution for carrying and producing


H<sub>2</sub>. However, all efforts should be dedicated to (i) construct, operate and optimize H<sub>2</sub> production systems (i.e. prototypes and demonstrators), (ii) handle SB at the gram-to-kilogram scale, (iii) make production of SB even more efficient, and (iv) overcome all obstacles while thinking from the end user perspective.

## Keywords

Hydrogen carrier; Hydrogen production; Hydrogen storage; Hydrolysis; Sodium borohydride

## 1. Introduction


Sodium borohydride NaBH<sub>4</sub> (SB) was discovered and identified in the 1940s as a hydrogen carrier (gravimetric hydrogen density of 10.8 wt%) capable of producing H<sub>2</sub> by hydrolysis (Eq. 1) at ambient conditions [1,2]:



Producing H<sub>2</sub> at ambient conditions is attractive, but producing H<sub>2</sub> knowing that half comes from water is even more attractive (Figure 1). The theoretical gravimetric hydrogen storage capacity of SB and water in stoichiometric conditions is 7.3 wt%. The hydrolysis reaction is exothermic (ca. -240 kJ mol<sup>-1</sup>), which makes that H<sub>2</sub> is produced spontaneously. Such a spontaneous production can be mitigated at basic pH, but it is then necessary to use a catalyst or an accelerator to produce H<sub>2</sub> at controllable rates and reach conversions of 100%. The reaction produces sodium tetrahydroxyborate NaB(OH)<sub>4</sub>, a by-product that is less soluble in water than SB is [3].

SB and hydrolysis of SB were rediscovered in the late 1990s [4]. A prototype using an aqueous alkaline solution of SB was constructed and tested as a H<sub>2</sub> production system for fuel cell vehicles [5]. This looked promising, but hydrolysis of SB encountered obstacles and well-founded criticism. For instance, the US Department of Energy made a no-go decision (for light-duty vehicles application) because of the cost of SB and the inefficiency of the regeneration processes studied at that time [6]. Research on hydrolysis of SB has nonetheless remained active and dynamic as evidenced by a selection of review articles released since 2015 [7-17]. Reading these articles indicates that the research on hydrolysis of SB performed between 2000 and 2015 had mainly focused on catalysts and accelerators,

and other equally important aspects (i.e. recycling of the by-product to regenerate SB, scale-up and implementation) had been neglected [18].

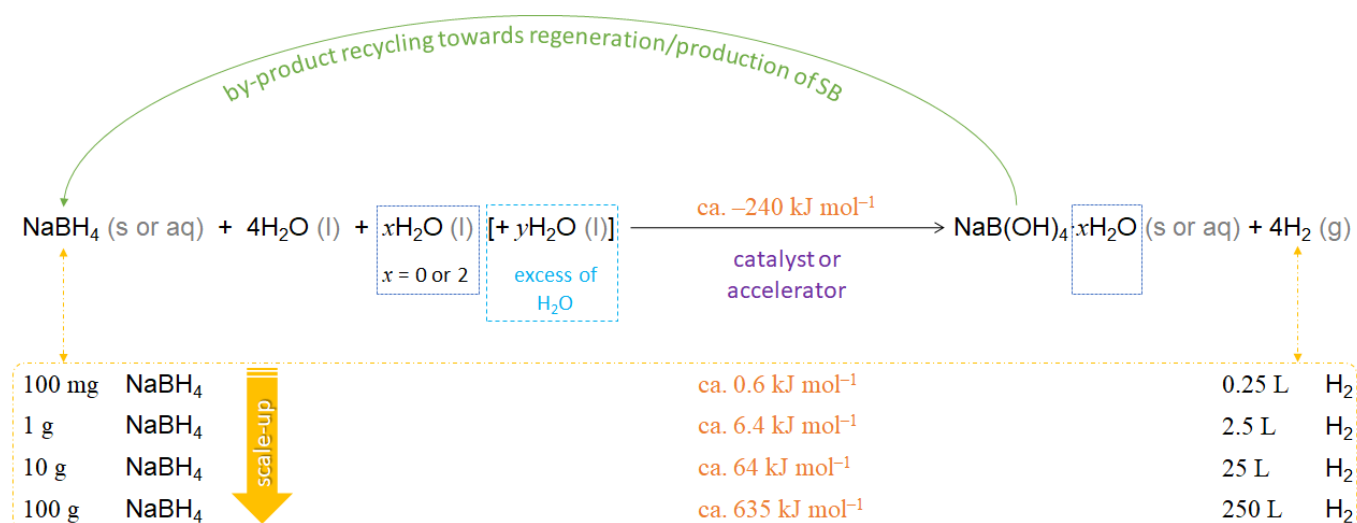

**Figure 1.** Hydrolysis of SB: the reactants, water in excess as solvent, a catalyst or an accelerator, the heat of the reaction, the by-products, the product  $\text{H}_2$ , and the amounts of SB and  $\text{H}_2$  towards scale-up.

Eight years have passed since 2015. Have we put more effort into all aspects relating to hydrolysis of SB? If so, do we have produced scaled-up technologies and prototypes, of which we would have a better knowledge? Have we been able to gain in technological readiness level? Or, on the contrary, have catalysts or accelerators dominated the field? Answering the above questions is the primary objective of the present article. To that end, it surveys the open literature dedicated to hydrolysis of SB since 2015 and until 2022. The second objective is to summarize the newly acquired knowledge. For the sake of clarity and of consistency, alcoholysis of SB and thermolysis of SB are not discussed herein.

The structure of the present article is based on the different aspects of the hydrolysis reaction as illustrated in Figure 1. The first of the next sections is about the reaction, the reactants and the products. The second one deals with catalysts and accelerators in a brief and concise manner. The third one is entitled scale-up and focuses on scaled-up technologies and prototypes. The fourth, and last one before the conclusion, is about regeneration of SB. Before getting to the heart of the matter, it is worth mentioning that catalyzed hydrolysis of SB has been also considered for other applications such as hydrogenation/reduction of nitro compounds to produce amines [19-38], reduction of azides to anilines [39,40], *N*-cycle hydrogenation of quinolone [41], reduction of carbon dioxide

CO<sub>2</sub> into the formate ion [42], reduction of bromate ions onto bromide ions [43-46], removal of Cr(VI) from aqueous solutions [47-50], degradation of organic dyes [51-53], detoxification of olive-tree pruning hydrolyzates [54], and gas foaming [55].


## 2. Hydrolysis of SB

SB in solid state degrades if contaminated by moisture and CO<sub>2</sub> of air (upon its storage for example). Such an aspect had been neglected until recently [56]. Such a contamination leads to the formation of sodium polyborates (e.g. Na<sub>2</sub>B<sub>4</sub>O<sub>7</sub>) and sodium carbonate Na<sub>2</sub>CO<sub>3</sub>, and these degradation products cover the SB grains. It then becomes necessary to purify SB before its use. This can be done by using diglyme as solvent, plus ammonia to increase the dissolution of SB, and the process is terminated by the crystallization of SB. This way, a 95%-pure SB can be recovered.

SB and water carry hydrogens that are respectively negatively and positively charged, i.e. H<sup>δ-</sup> and H<sup>δ+</sup>. These hydrogens interact and combine to produce H<sub>2</sub>, which implies that dihydrogen bonds B–H<sup>δ-</sup>...H<sup>δ+</sup>–O form is an intermediate step [57]. This was notably predicted by theoretical calculations [58]. The anion BH<sub>3</sub>OH<sup>-</sup> is assumed to form as the first short-living reaction intermediate and the corresponding reaction is the rate-determining step [59]. This was experimentally confirmed by using NMR spectroscopy [60]. The formation of BH<sub>3</sub>OH<sup>-</sup> is followed by that of the consecutive short-living reaction intermediates BH<sub>2</sub>(OH)<sub>2</sub><sup>-</sup>, BH(OH)<sub>3</sub><sup>-</sup>, and finally, B(OH)<sub>4</sub><sup>-</sup>. With respect to BH<sub>3</sub>OH<sup>-</sup>, it was also predicted that it may exist in the form of BH<sub>3</sub> and OH<sup>-</sup> separated by water molecules [61]. Because of the intermediates BH<sub>3</sub>OH<sup>-</sup> and BH<sub>3</sub> (both being able to oscillate), hydrolysis of SB undergoes an oscillatory instability and the consequence is that the production of H<sub>2</sub> is not smooth (i.e. occurrence of fluctuations) [62].

From a practical point of view, it would be more convenient to provide an aqueous solution of SB (instead of SB in solid state and water separately) to the end user. This supposes that the aqueous solution of SB is stabilized by addition of sodium hydroxide NaOH (basic pH), even though this does not totally hinder the occurrence of spontaneous hydrolysis of SB. The question of long-term storage of aqueous alkaline solution of SB then arises. Netskina et al. [63,64] answered it. A solution containing 15 wt% SB and 5 wt% NaOH was kept for

one year at 23-25 °C. During this time, 66% of the initial SB hydrolyzed, and the solution pH increased from 11.5 to 12.9. For another solution initially containing 25 wt% SB and 1 wt% NaOH, 76% of SB hydrolyzed after one year, and the pH increased from 11.2 to 13.2. The by-product that formed and precipitated is sodium tetrahydroxyborate dihydrate  $\text{NaB(OH)}_4 \cdot 2\text{H}_2\text{O}$ . We [65] also answered the above question. We conducted a systematic study by using NMR spectroscopy. The SB concentration was varied from 3.65 to 31.22 wt%, the NaOH concentration from 1 to 16 M, and the storage temperature from –15 to 60 °C; each solution was stored for up to 12 weeks. Hydrolysis took place whatever the conditions (Figure 2). Nonetheless, a relatively good stability of SB was noticed when the solutions with a NaOH concentration of  $\geq 8$  M were kept at  $\leq 4$  °C. Otherwise, storing at higher temperatures, and above all at the high temperatures that are reached in summer time ( $>30$  °C in Montpellier, France, from June to September, even nowadays from May to October) will pose serious safety concerns.

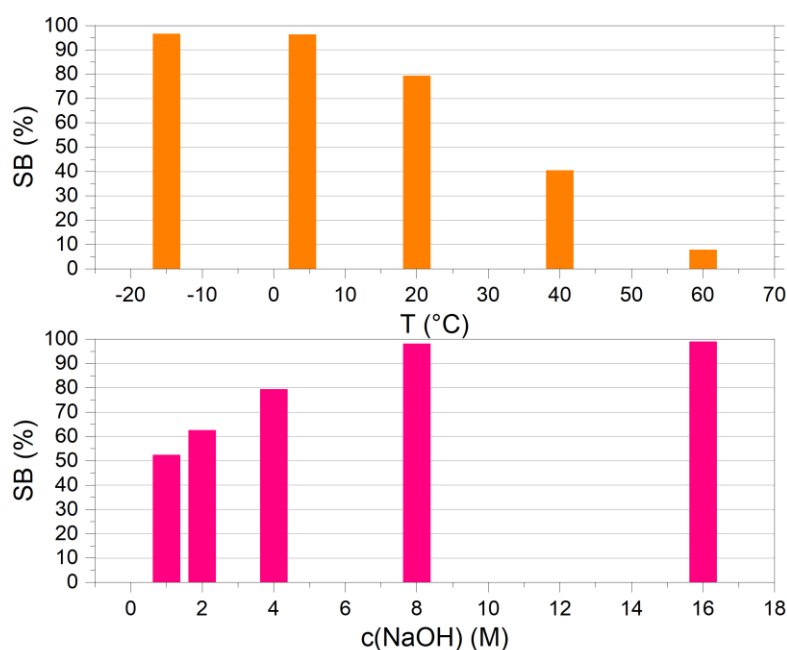

**Figure 2.** SB remaining (in mole percentage) in aqueous alkaline solution after a storage of 12 weeks: (top) effect of the temperature (–15, 4, 20, 40 and 60 °C) for an aqueous solution of SB (initial concentration of 4 M) having a concentration of NaOH of 4 M; (bottom) effect of the initial concentration of NaOH (1, 2, 4, 8 and 16 M) for an aqueous solution of SB (initial concentration of 4 M) stored at 20 °C.

Water has not been the subject of particular attention until recently. Yet, it is just as important as SB (Eq. 1). For example, what water should we use? At the laboratory scale and to avoid

any experimental bias, it is obvious that we have to use distilled water. However, the use of distilled water by the end user will be a constraint and will add to the cost of the H<sub>2</sub> production system. Mosier-Boss et al. [66] studied the effect of distilled water, tap water and seawater, on the CoCl<sub>2</sub>-catalyzed hydrolysis of SB. They observed slower kinetics of H<sub>2</sub> production when tap water was used, and even slower when seawater was used. Organic species present in both tap water and seawater were found to form complexes with Co<sup>2+</sup>, thereby impeding an efficient catalysis of the hydrolysis reaction. One cannot generalize these observations because of the use of CoCl<sub>2</sub>. Indeed, in such conditions, Co<sup>2+</sup> of CoCl<sub>2</sub> is a pre-catalyst, and as such it in situ transforms into a Co-based catalyst (e.g. cobalt boride) when it is put into contact with SB in aqueous solution. The Co-based catalyst, and not Co<sup>2+</sup>, thus catalyzes the hydrolysis reaction, whereas in this study, a proportion of Co<sup>2+</sup> did not generate the Co-based catalyst. With less catalyst, the hydrolysis reaction is thus less efficient. Oh et al. [67] reported different results for Co-P-B/C used as catalyst. They found that fresh water (versus distilled water) allows better performance in terms of H<sub>2</sub> production yields and rates. Regrettably, and in conclusion to these paragraph, too little is known about the use of water of different qualities.

The by-product that forms upon hydrolysis of SB is NaB(OH)<sub>4</sub>. It is less soluble than SB is in water (16 vs 55 g in 100 mL of water), and precipitates when SB solutions are concentrated (as mentioned above) [69]; this is an issue (see section 4). NaB(OH)<sub>4</sub> forms when the mole ratio Na/B is 1 as in the case of the use of SB without addition of NaOH, and when the mole ratio Na/B is >1 as in the case of aqueous alkaline solutions [68]. When the mole ratio Na/B is lower than 1 (e.g. 0.33), polyborate anions (B<sub>3</sub><sup>-</sup>, B<sub>4</sub><sup>-</sup>, B<sub>5</sub>-based) form [70]. Sodium polyborates are more water-soluble than NaB(OH)<sub>4</sub>. Note that a mole ratio of e.g. 0.33 assumes that a boron-containing compound like boric acid B(OH)<sub>3</sub> has to be added to the SB solution. Another option would be to use sodium octahydrotriborate NaB<sub>3</sub>H<sub>8</sub> instead of SB.

The value-added product of hydrolysis of SB is H<sub>2</sub>, and the reaction (Eq. 1) suggests that the produced H<sub>2</sub> is pure. However, the situation is not quite as simple as that. Because of the reaction exothermicity, water vapor is transported along with H<sub>2</sub>, and this water vapor contains Na<sup>+</sup> and B(OH)<sub>4</sub><sup>-</sup> [71,72]. This poses a constraint and a question. The constraint is that the produced H<sub>2</sub> must be purified (owing to downstream traps; see section 4) or the reactor design should be thought so that NaB(OH)<sub>4</sub> remains within it. The question is, what

will be the purity of H<sub>2</sub> when its production will be considered for greater amounts of SB and water? A response and actions are required, but an experiment based on the use of a lot of SB requires an appropriate and secured facility (1 kg of SB for example, is able to produce more than 2500 liters of H<sub>2</sub> at 20 °C).

### 3. Catalysts and accelerators


This article does not intend to explore the complete list of catalysts and accelerators reported since 2015. It aims to be concise, to focus on the essentials (i.e. new findings and knowledge), and to present a selection of catalysts and accelerators that can be defined as being out of the ordinary and/or that offer obvious prospects for scale-up and implementation. That represents 15 articles (see below), knowing that a total of 466 articles with catalysts or accelerators as central topic were found for the period 2015 to 2022.

The remaining 451 articles (listed as [supplementary material](#)) can be summarized as follows. Most of them report on catalysts, synthesized via chemical or physical methods, and intended to be used many times: e.g. mono-/bi-/tri-metallic or multi-element catalysts supported onto a support like mesoporous silica, carbonaceous materials (e.g. graphene, carbon nanotubes, biosourced carbons) and metal organic frameworks (among other ones); mono-/bi-/tri-metallic catalysts (including alloys) in the form of nanostructures, being dense or porous, and with or without magnetic properties; metallic catalysts contained into polymer capsules; polymer- and ionic liquid-based composites containing a metallic active phase; supported or unsupported metal oxides; alkali metal oxides; salts or hydroxides of metal cations; and, boron- and nitrogen-doped, functionalized and/or surface-charged carbon dots. Cobalt remains the most studied metal, though it is often combined with at least one p-block element (e.g. B or P) or one other transition metal. Metals like platinum, ruthenium, nickel and gold were also reported. Some articles report on photocatalysts (based on e.g. titanium oxide) as well as single-use accelerators (e.g. acids, polyols, oxides or clays with H<sup>+</sup>-treated surfaces, sulfonated polymers, metal chlorides). Beyond the routinely studied aspects (e.g. kinetics and thermodynamics), reusability and stability of the catalysts over cycles (generally 5 to 10) were studied, and the majority of the catalysts show more or less pronounced loss of activity upon cyclic use. Such a loss is mainly explained by catalyst poisoning due to surface adsorption of borates. Another explanation, in the case of the



cobalt catalysts, is the loss of the active phase by formation of cobalt hydroxide and oxyhydroxide and their detachment from the catalyst surface [73]. To go beyond this summary, the reader is invited to refer to a selection of review articles [7-17].

Singh et al. reported a catalyst that is out of the ordinary [74]. They synthesized Pt-black/Ti Janus microparticles, in fact micromotors (Figure 3), to catalyze the production of H<sub>2</sub> by hydrolysis of SB. The Janus microparticle is made of a catalytically active side (i.e. Pt-black) and an inactive one (i.e. Ti), which allows the microparticles moving in the solution owing to the propulsion created by the production of H<sub>2</sub> onto the Pt-black surface. The efficiency of these micromotors was demonstrated by feeding with H<sub>2</sub> a polymer exchange membrane fuel cell (PEMFC) model car.

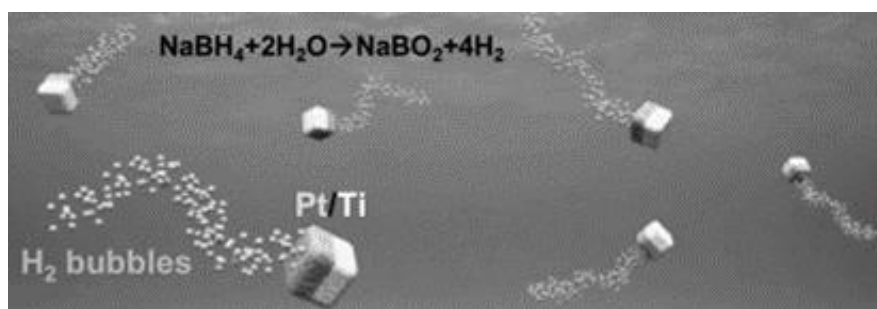


**Figure 3.** Schematic representation of the Pt-black/Ti Janus micromotors by the production of H<sub>2</sub> microbubbles by hydrolysis of SB. Reproduced from ref. [74] with permission granted by John Wiley and Sons (January 6, 2023).

With powdery catalysts, handling is tedious and material losses are almost inevitable. It is more convenient to develop one-block catalysts, at least from a practical point of view. First examples of one-block catalysts are based on nickel foam that is used as support of an active phase like the binary Co-P. Oh et al. [75] optimized such a catalyst. Co-P was loaded onto nickel foam by electroless deposition, and the most efficient one was selected to produce H<sub>2</sub> for a 200-watt PEMFC. In a subsequent study, the PEMFC was successfully operated for 30 min, stopped for 30 min, and re-operated for 30 min [76]. A 500-watt PEMFC was successfully operated in the same way [77], as well as a 100-watt one [78]. Pure cobalt can also be loaded onto nickel foam, which is done by electrodeposition at -2 V<sub>Ag/AgCl</sub> [79]. Aluminum-surface modified nickel foams, obtained through a three-step process including aluminization, post-annealing and selective aluminum selective leaching, are also potential catalysts [80]. Second examples of one-block catalysts are based on ceramic monoliths.

Marchionni et al. [81] explored cordierite honeycomb monoliths as supports of Co-B. Dai et al. [82] also studied cordierite honeycomb monoliths onto which alumina was wash-coated and then platinum was deposited by incipient wet impregnation. The as-obtained monolithic catalysts catalyzed a continuous and stable  $H_2$  production (e.g.  $0.6 \text{ L min}^{-1}$ ) by hydrolysis of SB (10 wt%) in aqueous alkaline (5 wt% NaOH) solution (feed rate of  $2 \text{ mL min}^{-1}$ ). Other examples include mesh nickel [83], dealloyed ruthenium on Teflon substrate [84], Ru/MgO wash-coat onto a magnesium substrate [85], and platinum-decorated polydopamine-coated wood pulp sponge [86].

There is also an alternative approach, not using a catalyst, as proposed by Sankir et al. [87]. One chamber was filled with the SB solution, another chamber with an acid solution (e.g. 18 M  $H_2SO_4$ ), and both chambers were separated by a proton exchange membrane made from a disulfonated poly(arylene ether sulfone) copolymer (Figure 4). Protons were provided by the acid, via the membrane, to the SB solution in order to initiate the hydrolysis reaction. The  $H_2$  production rate was controlled by tailoring the proton conductivities of the membranes, which was possible by varying the degrees of disulfonation. This  $H_2$  production system was coupled to a 8-watt PEMFC that worked for about 300 h.

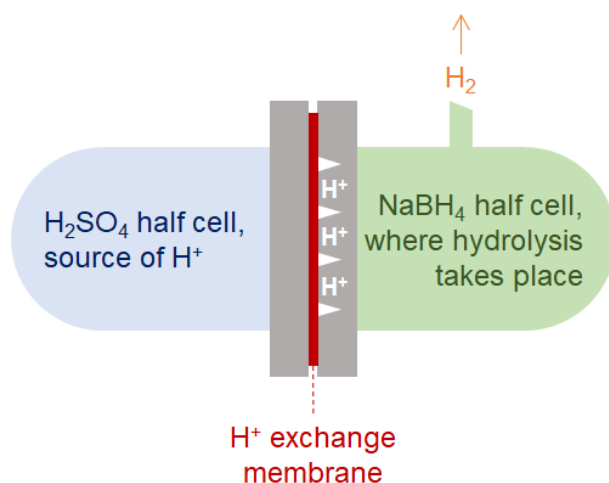

**Figure 4.** Scheme of the  $H_2$  production system, based on two half-cells, as proposed in ref. [87]. The  $H_2SO_4$  half cell is separated from the SB half cell by a proton exchange membrane (disulfonated poly(arylene ether sulfone) copolymer), and the  $H_2$  produced in the latter cell is vented through an outlet.

## 4. Scale-up

Hydrolysis of SB at the milligram scale has been much studied over the past twenty years and we have learned about the issues that the reaction is encountering. However, hydrolysis of SB at the gram-to-kilogram scale has not been thoroughly studied yet [88,89], and our knowledge of the issues that are inevitably exacerbated due to effect of scale is limited. In addition, it remains possible that we are not yet aware of issues that would be specific to the use of SB at the gram-to-kilogram scale. We have to expend more effort on closing these gaps, which involves developing and studying prototypes and demonstrators (e.g. H<sub>2</sub> production systems feeding fuel cells powering unmanned aerial vehicles [90,91]).


The period 2015-2022 was punctuated with interesting studies, showing a real dynamic around scale-up of hydrolysis of SB. From here on, these studies will be discussed from two perspectives: a selection of the prototypes developed so far will be presented (Table 1) [92-101], and the lessons learned from the operation of these prototypes (with particular emphasis focused on the challenges to be met) will be summarized. For more details about the operation conditions (e.g. catalyst amounts, H<sub>2</sub> yields and operation pressures), and the algorithms used for maintaining a constant H<sub>2</sub> production and a constant power supply, the reader is invited to refer to the articles discussed hereafter.

As shown in Table 1, the H<sub>2</sub> production systems were dimensioned to produce pure H<sub>2</sub> to feed 20-watt to 3000-watt PEMFCs, and in most of the case to power unmanned aerial vehicles. SB was used in solid state or in aqueous alkaline solution. In the former case, water, containing an acid for example, is pumped or injected into the SB containing reactor, and the by-product is kept inside the reactor. Various acids can be used, with typical examples being hydrochloric acid, sulfuric acid, acetic acid and citric acid [102-104]. Lee et al. [92] identified an issue not really seen before. They noticed that reactor pressurization is an important factor for stable system operation, that is, for constant H<sub>2</sub> production rates. In case SB is in aqueous alkaline solution, it is pumped onto a one-block catalyst (e.g. Co-P loaded onto nickel foam), and the aqueous alkaline solution of the by-product is either purged out the system or stored in a tank placed at the outlet of the catalytic chamber. The fluids circulation are allowed by a pump. Known et al. [93] demonstrated that the energy density of a H<sub>2</sub> production system using SB in solid state is 1.3 times higher than a system using an aqueous alkaline solution of SB.

**Table 1.** H<sub>2</sub> production systems, coupled or not to a fuel cell (PEMFC) as reported in references [92-101]. Information (when available from the articles) about the state of SB (solid or in aqueous solution), the nature of the catalyst or accelerator used, how the reaction was made start, the cooling technology used, how the by-product was managed during hydrolysis, the power of the fuel cell, the H<sub>2</sub> production rate recorded, the total volume of H<sub>2</sub> measured, and the gravimetric hydrogen storage capacity (GHSC) of the system, are given.

State of SB	Cat./Accel.	How the reaction starts	Cooling approach	By-product management	Fuel cell power	H <sub>2</sub> production rate	Volume of H <sub>2</sub>	GHSC	Reference
SB as a solid	Aqueous HCl (2.5-4 M)	Pumping HCl onto SB	Fan (2.4 W)	Kept in the reactor	20 to 100 W	0.2-0.9 L min <sup>-1</sup>	11-49 mL	3.1-4.2 wt% H	[92]
SB as a solid	Aqueous NaHCO <sub>3</sub>	Pumping NaHCO <sub>3</sub> onto SB	Fan	Kept in the reactor		7-9 L min <sup>-1</sup>	3464 L from 283 g SB	5.1 wt% H	[93]
SB as a solid	Aqueous NaHCO <sub>3</sub>	Pumping NaHCO <sub>3</sub> onto SB	Fins and fans						[94]
SB as a solid	Aqueous FeCl <sub>3</sub> (1g vs. 10g SB)	Injection of FeCl <sub>3</sub> onto SB		Kept in the reactor	20 W	1.17 L min <sup>-1</sup>			[95]
Aqueous SB (25 wt%)	Co-B supported on Ni foam	Pumping SB onto the catalyst	Fins and fans	Purged out	100 W	1.2-1.7 L min <sup>-1</sup>		3.55 wt% H	[96]
Aqueous SB (20 wt%)	Co-P supported on Ni foam	Pumping SB onto the catalyst	Fan	Purged out	300-500 W	4.5-5.9 L min <sup>-1</sup>			[97-99]
Aqueous SB (20 wt%)	Not mentioned	Pumping SB into the reactor	Cooling coil	Stored after the cooling coil	200 W				[100]
Aqueous SB (5-15 wt%)	Cobalt oxide on Ni foam	Pumping SB onto the catalyst	Four 4-W fans	Waste tank	3000 W			31.7-149.9 L	[101]

Within the last two years, Avrahami and co-workers developed alternative H<sub>2</sub> production systems. On the one hand [105], they constructed five designs of lightweight reactors for which SB in solid state (powder or 3-mm granulates) is dropped into tap water containing a catalyst suspension of 1 wt% ruthenium black. The reactors design allows on-demand production of H<sub>2</sub> with an almost constant flow of about 400 mL min<sup>-1</sup> for 5-7 h of operation. All the reactors however faced technical and mechanical problems, mainly because of gumming of SB in the presence of water vapor rising from the exothermic hydrolysis reaction. Another problem was mentioned. Leakage of H<sub>2</sub> is unavoidable especially at pressures higher than 0.5 bar. On the other hand [106], they constructed a modified reactor with the aim of taking advantage of the aforementioned gumming of SB (Figure 5). This reactor allowed the production of 110 L of H<sub>2</sub> at a flow rate of 290 mL min<sup>-1</sup>, the conversion of SB reached 98 %, and the prototype was successfully coupled to a 30-watt PEMFC.

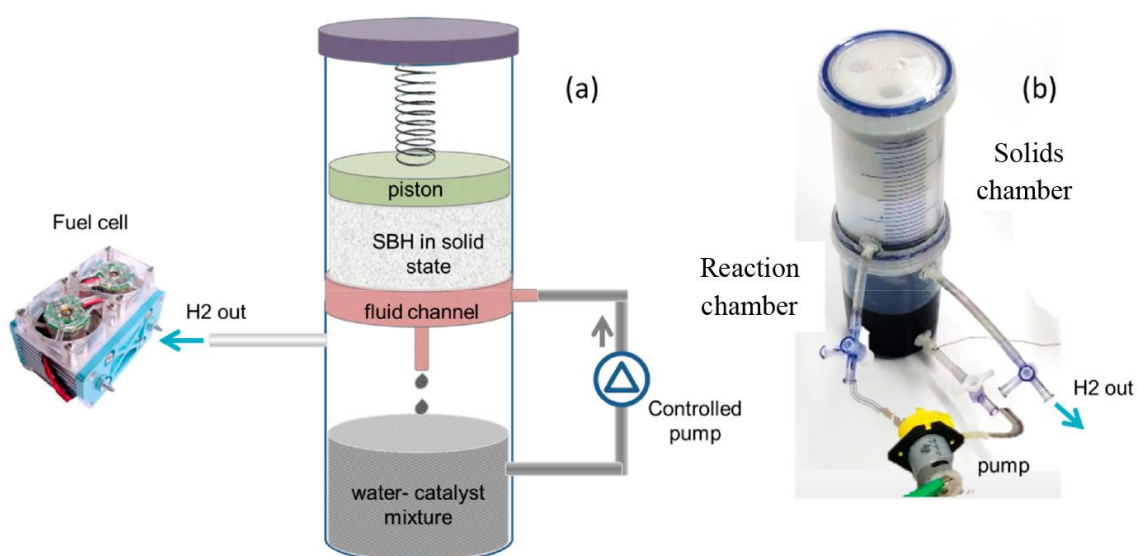


**Figure 5.** Avrahami and co-workers' pump-based circulation generator: (a) schematic concept (with SBH for sodium borohydride as denoted by the authors); (b) photograph of the generator described in (a). Reprinted with permission from reference [106]. Copyright 2021 American Chemical Society.

At the scale of a H<sub>2</sub> production system, the exothermic nature of hydrolysis of SB is a substantial issue. Cooling fins, fans, coils and/or traps (Table 1) have to be incorporated to the system to manage the evolving heat [98]. For example, Lee et al. [92] observed a temperature increase up to 110-120 °C in the absence of an appropriate cooling system. Kwon et al. [93] observed that the side of their reactor that was cooled down thanks to a fan kept its temperature below 30 °C whereas the top side, free of a fan, attained a temperature

of 65 °C. Heat removal is important to avoid heat damages, fuel cell inundation because of evaporated water, as well as uncontrollable and unpredictable hydrolysis rates [107,108].

Lapena-Rey et al. [100] published an excellent article where all the recurring issues that a H<sub>2</sub> production system feeding a 200-watt PEMFC to power an unmanned aerial vehicle is able to encounter. The issues are shown in Figure 6. These issues were actually rather well identified (as discussed above and in the previous sections). For example, the catalyst deactivation issue is known since many years now and is still reported [109,110]. Nevertheless, it must be admitted that the Lapena-Rey et al.'s study clearly underlines how critical the issues are when SB is used at the gram-to-kilogram scale.

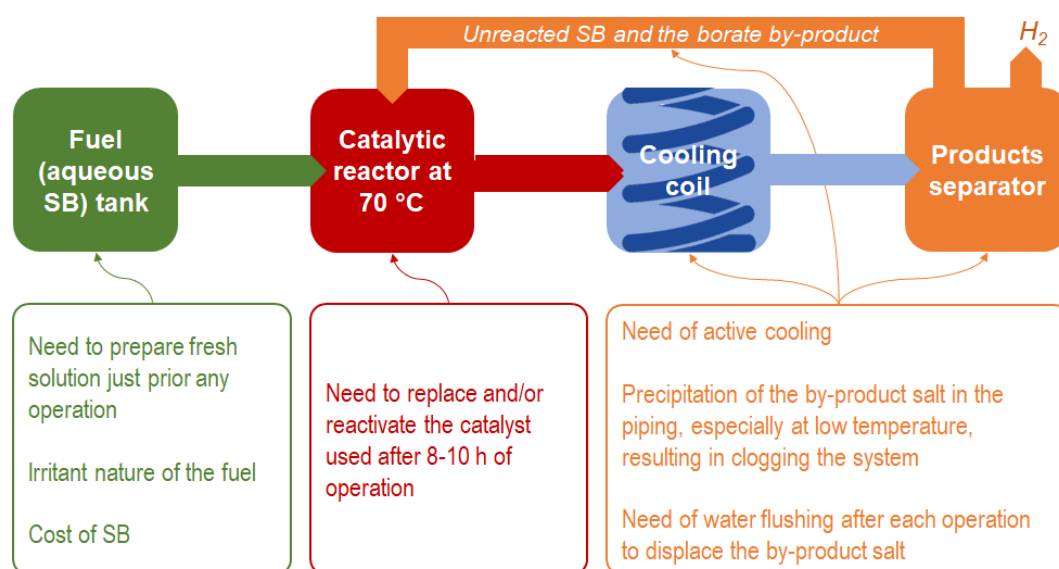

**Figure 6.** The recurring issues encountered by a H<sub>2</sub> production system, as reported by Lapena-Rey et al. [100].

Other issues were reported elsewhere (Table 2) [100,108,111,112]. One of them is specific to the aircraft applications as it is about the importance of keeping stable the center of gravity of the plane even when the SB tank is depleted [100]. Another issue is related to the alkaline pH values (up to 12) that are reached upon hydrolysis of SB and/or when the solution is stabilized with NaOH. Corrosion is likely to occur with stainless steel [108] and is unavoidable with aluminum alloys [111]. Coating of the internal walls of reactors will thus be required for long-term utilizations. Polytetrafluorethylene coating is a possibility [108]. A last issue concerns the weight of the constituent materials of a H<sub>2</sub> production system, and specifically that of the reactor materials. Nunes et al. [112] pointed out the negative impact


on gravimetric hydrogen storage capacities when stainless steel is used. Lighter materials and reactors are required, especially for small portable applications. A similar conclusion was made by Gang et al. [98], and they even stated that their portable electric fuel cell system is not optimized in terms of weight as shown in Figure 7. Indeed, the weight fraction of the SB solution is only 31% of the total weight. This is lower than the 50% that we generally target when discussing about the storage capacities of a H<sub>2</sub> production system [89]. The net gravimetric hydrogen storage capacity (i.e. the capacity for the system as a whole) is limited to 1.3 wt% in such a case. There is nevertheless room for improvement. One of the main challenges is just to make the system lighter without compromising security.

**Table 2.** Other issues to be encountered by H<sub>2</sub> production systems and reactors, as reported in references [100,108,111,112].

Studied device or system	Issue	Consequence / Risk	Reference
Complete H <sub>2</sub> production system	Depletion of the tank containing the SB fuel	Risk of disrupting the aircraft center of gravity	[100]
Complete H <sub>2</sub> production system	Increase of pH up to 12	Leaching of the stainless steel pressure vessel, implying coating with inert material	[108]
Aluminum alloy as light material for low weight reactor	Corrosion of aluminum (dissolution with alkali) with formation Al(OH) <sub>3</sub>	Unavoidable degradation of the reactor	[111]
Stainless-steel mini-reactor	Use of stainless steel	Negative impact on the gravimetric hydrogen storage capacities	[112]

There are few other articles including simulation works that are worth being briefly mentioned. Tomoda et al. [113] used a reactor simulation model to simulate hydrolysis of an aqueous alkaline solution of SB at 90 °C. Shabunya et al. [114] modeled heat- and mass-transfer processes in a circulating-type reactor. Chen and Lin [115] studied the dynamic response of a reactor between the input of the aqueous solution of SB and the output of the produced H<sub>2</sub>. Jung et al. [116] studied the H<sub>2</sub> pressures and the H<sub>2</sub> production rates for different geometries of their system channels. For a H<sub>2</sub> production system that will gain in maturity, simulation and optimization will bring much more studies in these topics. Scale-up is the only option to leapfrog towards hypothetical commercialization.



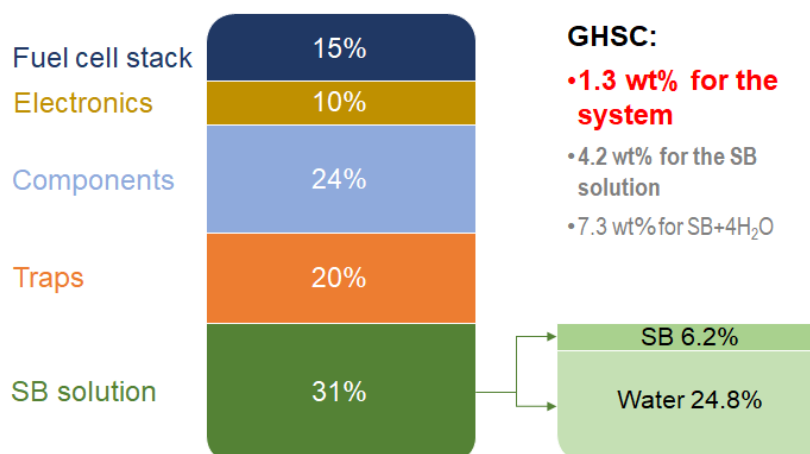

**Figure 7.** Weight percentage of the SB solution for the H<sub>2</sub> production system reported in reference [98]; this original scheme was drawn from the data available in this reference. The system is simply described by five items such as the SB solution, the traps (water and silica and their containers), the components (fuel tank, hydrogen generator, separator, pumps, cooling fan and fittings), the electronics (controller, monitoring device and DC-DC converter), and the fuel cell stack. The gravimetric hydrogen storage capacity for the system as a whole is given, as well as for the SB solution and for the couple SB+4H<sub>2</sub>O (as shown in Eq. 1).

Since 2018, our group has placed a renewed focus on scaling-up. We constructed a prototype, and we are working on its evolution and optimization with the objective to produce at least 100 liters of H<sub>2</sub> to feed a 200-W PEMFC. We have learned a lot about the change in scale (from e.g. 120 mg SB to 40 g SB), and though a large part of our results are confidential (due to partnerships), I am able to share our experience. Firstly, we do confirm the main observations reported and discussed above, such as the importance of heat removal, fast deactivation of cobalt and even ruthenium-alumina catalysts (commercial ones) requiring then reactivation, the fact that the H<sub>2</sub> production rates are not constant during the reaction, hygroscopicity of SB resulting in its gumming, and lowered gravimetric hydrogen storage capacities because of the weight of the stainless vessel we currently use. Secondly, we are faced with three other problems. The reactor design has an impact in terms of H<sub>2</sub> production rates and thus times of completion of hydrolysis, even though the experimental conditions are identical. When SB is used in solid state, and under certain conditions, the results are sometimes not reproducible; we observed that, for instance, the way water is put into contact with SB can lead to differences in terms of H<sub>2</sub> production rates. Upon the completion of the H<sub>2</sub> production, emptying the reactor containing the aqueous alkaline solution of the by-products, as well as a precipitate of the by-products, requires care and several rinses; this makes the process tedious. In summary, many obstacles remain to be overcome before we achieve the ultimate optimization.




Last, not least, there is an aspect that is just as critical as the technical and economic challenges discussed above. As well pointed out by Yao et al. [117], it is essential to gain approval from the regulatory bodies to facilitate the applications of hydrolysis of SB.

## 5. Regeneration of SB

The hydrogen cycle and the boron cycle must be closed. Recycling  $\text{NaB(OH)}_4$  to regenerate and thus produce SB remains a major challenge.


The achievements reported between 2015 and 2022 are summarized and discussed in the next paragraphs. Before, it is pertinent to briefly remind the main regeneration processes developed until 2014. These are the modified Brown-Schlesinger process, the modified Bayer process, the reduction processes using reducing agents such as methane  $\text{CH}_4$ ,  $\text{H}_2$ , and the pair carbon- $\text{H}_2$ , and the electrochemical reduction process (Figure 8). To enter the detail of these, the reader is invited to refer to the following review articles [118-124].

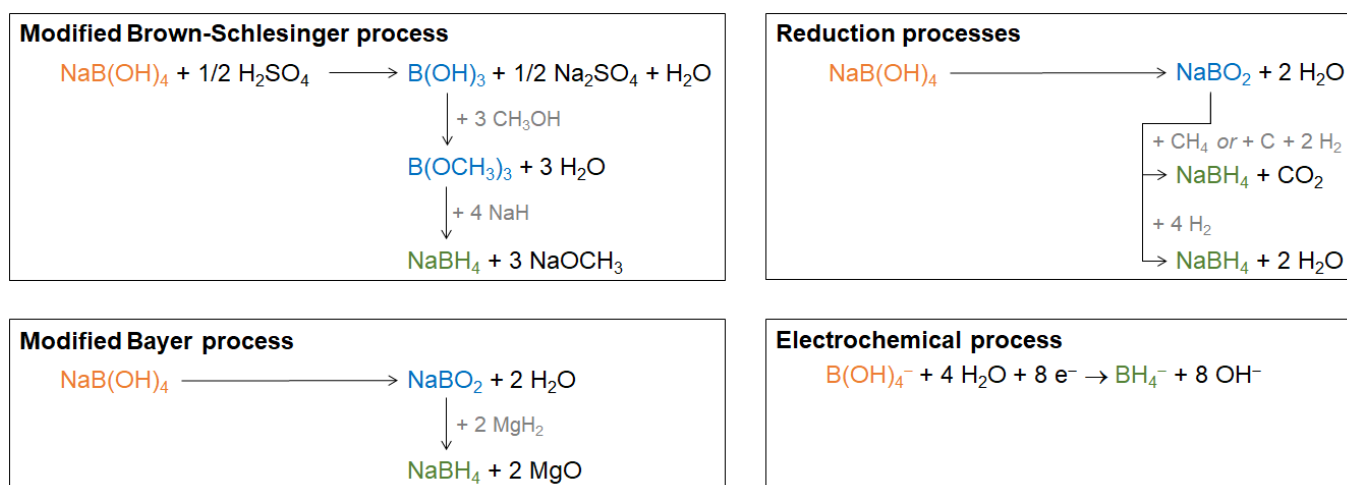


**Figure 8.** The main SB regeneration processes developed until 2014, as surveyed in references [118-124].

SB can be produced from anhydrous sodium metaborate  $\text{NaBO}_2$  that is obtained by dehydration of the by-products  $\text{NaB(OH)}_4$  and  $\text{NaB(OH)}_4 \cdot 2\text{H}_2\text{O}$  at  $>350^\circ\text{C}$  [125]. It is however preferable to produce SB directly from  $\text{NaB(OH)}_4$  and  $\text{NaB(OH)}_4 \cdot 2\text{H}_2\text{O}$  to save energy (the one that would be required to get  $\text{NaBO}_2$ ) and decrease the SB production costs. It is with this logic in sight that Ouyang and co-workers have developed effective regeneration processes over the past years (Figure 9). At room temperature and


atmospheric pressure [126], either  $\text{NaB(OH)}_4$  or  $\text{NaB(OH)}_4 \cdot 2\text{H}_2\text{O}$  was ball-milled with magnesium hydride  $\text{MgH}_2$ , using a high-energy shaker mill. The milling conditions were as follows: 1 mol  $\text{NaB(OH)}_4$ , 5.5 mol  $\text{MgH}_2$ , a ball-to-powder ratio of 30:1, and 15 h of milling while alternating 30 min of milling and 30 min of rest; 1 mol  $\text{NaB(OH)}_4 \cdot 2\text{H}_2\text{O}$ , 8.25 mol  $\text{MgH}_2$ , a ball-to-powder ratio of 50:1, and 20 h of milling while alternating milling and rest. In these conditions, SB was produced:




In both reactions, some  $\text{H}_2$  is produced. It could be recovered to hydrogenate the magnesium product  $\text{MgO}$  to regenerate  $\text{MgH}_2$ ; in doing so, the magnesium cycle would be closed. SB was separated by extraction using anhydrous ethylenediamine  $\text{C}_2\text{H}_4(\text{NH}_2)_2$  as solvent. The SB yields were 90 and 83.3% respectively. In other studies, Ouyang and co-workers explored alternatives to  $\text{MgH}_2$ . They used  $\text{Mg}$  [127],  $\text{Mg}_2\text{Si}$  [128,129], a mixture of  $\text{Mg}$  and  $\text{Mg}_2\text{Si}$  [130], and a magnesium-aluminum alloy  $\text{Mg}_{17}\text{Al}_{12}$  [131,132], with attractive results though the SB yields were lower than those reported above. In yet other studies, Ouyang and co-workers considered other borates. On the one hand, the aforementioned process was successfully applied to  $\text{NaBO}_2$ , the SB yield being 89% [133]:



On the other hand, a polyborate such as  $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$  that is the main constituent of naturally abundant borax mineral was selected [134]. This approach is interesting in two counts. First,  $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$  is the raw material of the industrially-applied Brown-Schlesinger process for production of SB. Second,  $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$  is known to form by reaction of  $\text{CO}_2$  with e.g.  $\text{NaB(OH)}_4$  in aqueous solution:




Similar to what has been described above,  $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$  (without separating  $\text{Na}_2\text{CO}_3$ ) was ball-milled with  $\text{Mg}$ , resulting in the production of SB (yield of 78.9%):



Higher yields were attained with the use of additives such as sodium hydride  $\text{NaH}$  [135]. For instance, a SB yield of 93.1% was achieved when the system  $\text{MgH}_2$ - $\text{NaH}$ - $\text{Na}_2\text{B}_4\text{O}_7 \cdot 5\text{H}_2\text{O}$  was ball-milled 3.5 h. A SB yield of 85.2% was obtained with the system  $\text{Mg}_{17}\text{Al}_{12}$ - $\text{NaH}$ - $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$  after a milling of 20 h [136]. The use of aluminum (without or with silicon) to hydrogenate  $\text{Na}_2\text{B}_4\text{O}_7 \cdot 10\text{H}_2\text{O}$  was also explored, and the SB yields were lower than 62%

[137]. In the main, Ouyang and co-workers have been much active and are currently the leading researchers on this matter [138].


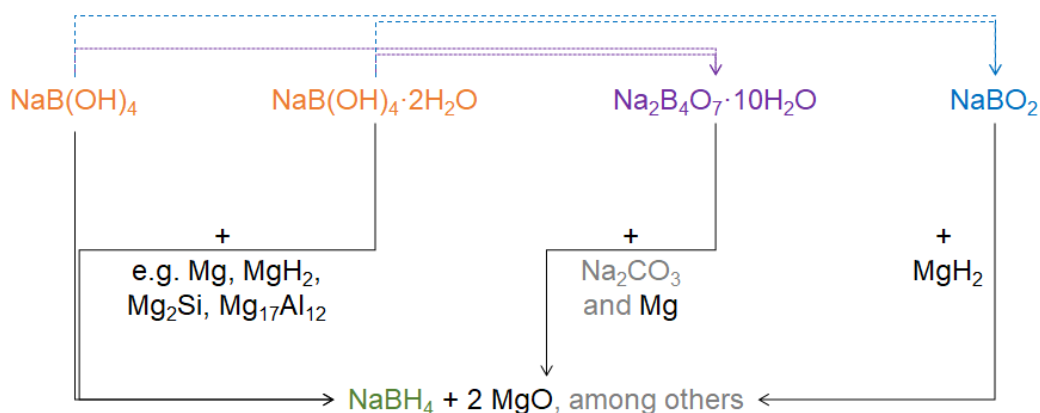


**Figure 9.** The SB regeneration processes developed by Ouyang and co-workers [126-137].

Few other studies are also of interest. Ar et al. [139] produced SB from boron oxide  $B_2O_3$ ,  $MgH_2$  and sodium amide  $NaNH_2$ , by mechanochemistry carried out at room temperature:



SB was extracted by using ethylenediamine as solvent. For a reaction lasting 500 min and using an excess of 30% of  $MgH_2$ , the SB yield was 84%. According to the authors, ammonium borohydride  $NH_4BH_4$  (Eq. 7) formed as by-product. However, no evidence of its formation is given. It is however unlikely that  $NH_4BH_4$  forms. Indeed, this compound is much unstable in the conditions mentioned above [140]. Le et al. [141] used a magnesium-aluminium alloy (76 wt% Mg and 13.6 wt% Al, plus other elements like Ca, Cu, Mn, Nd, Zn, Y, Ag) that was ball-milled with either  $NaBO_2$  or  $NaB(OH)_4 \cdot 2H_2O$  under  $H_2$  pressure (70 bar) and at room temperature:



Yields of 99.5%, upon extraction of SB by ethylenediamine, were found.

Progress has been made. However, there are two outstanding questions. How simple and safe is the extraction of SB from the ball-milled mixture? Our recent attempts (unpublished work) taught us two things. When the ball-milling is too harsh, the particles size of the magnesium products is so small that they remain in suspension after weeks of storage. Even

centrifugation turns out to be complicated. The other point is that the aforementioned small particles are pyrophoric, and ethylene diamine is a highly flammable solvent. This makes the extraction/separation process very constraining. These observations bring up the second question. What is the cost of the as-produced SB, and that of the H<sub>2</sub>? It is difficult to answer this question because there is a lack of energy, exergy and economic analyses. The only study available is that of Rivarolo et al. [142]. They carried out a thermo-economic analysis for a process where the electricity is from photovoltaic panels, H<sub>2</sub> is produced by electrolysis of water, and SB is synthesized from NaBO<sub>2</sub> in the presence of Mg and H<sub>2</sub> (Eq. 8). The total cost of H<sub>2</sub> was found to be 15.5 € per kilogram. At such a cost price, SB is not economically viable, except perhaps for niche applications.


## 6. Conclusions and prospects

The first conclusion that can be drawn is that the 2015-2022 period is regrettably too similar to the 2000-2014 (surveyed in reference [18]). Again, catalysts or accelerators have dominated the field, the other aspects have received little attention (Figure 10), and there has been little gain in terms of technological readiness level. There is now substantial literature on catalysts and accelerators showing a potential use in hydrolysis of SB. However, it is important to mention that the prototypes reported so far were based on the use of a one-block catalyst (e.g. cobalt supported on Ni foam) or an accelerator among very few ones (e.g. HCl or NaHCO<sub>3</sub>). There is clearly a gap between the hundreds (in fact >1000 since the early 2000s) of different catalysts or accelerators reported so far and the very few catalysts and accelerators tested on a prototype.

The 47 articles dated 2015-2022 and dealing with aspects other than catalysts or accelerators give valuable insights into hydrolysis of SB towards scaling up. These insights are much interesting, have been discussed above, and deserve to be put into perspective with a view of the end user.

Storage of SB gives rise to constraints. SB in solid state must be kept far from air contamination to avoid its degradation (by reaction with moisture and CO<sub>2</sub>). Aqueous alkaline solution of SB suffers from spontaneous hydrolysis even for high concentrations of NaOH and low temperatures, and its storage will require special care (e.g. chemically inert

high-pressure vessel, ventilated storage areas). May one impose such constraints to the end user knowing that one should do because of the safety concern related to uncontrolled  $H_2$  production by spontaneous hydrolysis? From what we know at present, the answer to the question is in the negative, and one may regret that there is no study and data about kilograms of SB stored in various conditions and in different vessels.

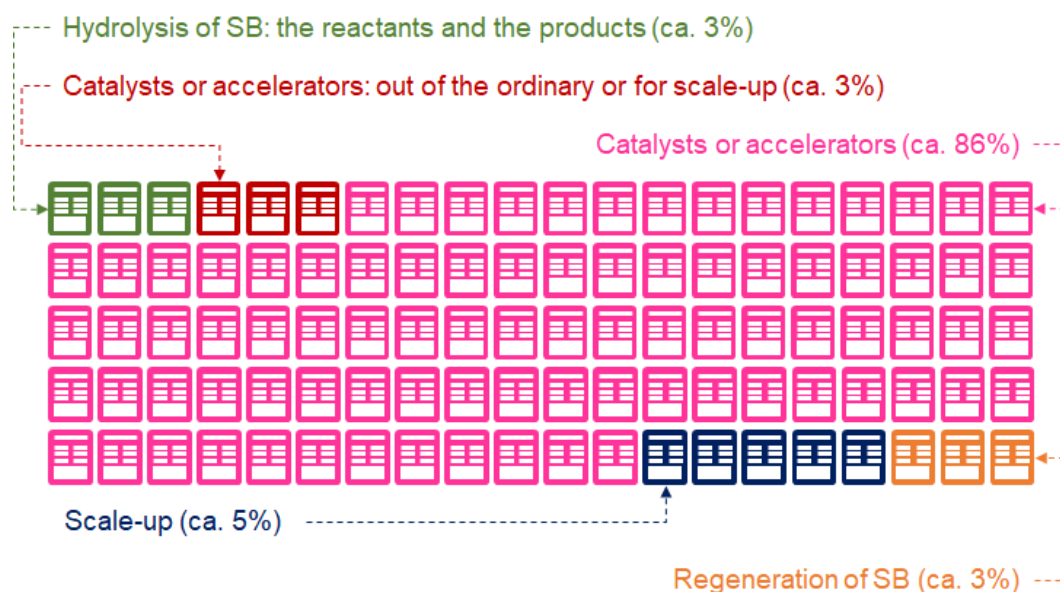

**Figure 10.** Percentage of articles dealing with the different aspects related to hydrolysis of SB, knowing that a total of 523 articles (for the period 2015-2022) were analyzed.

Perhaps, one may consider that the end user prepares a fresh aqueous alkaline solution of SB when it is required. But, is this conceivable? Perhaps the answer is yet for professionals. However, the normal end user should not have to handle chemicals like solid SB and NaOH because this could poses significant constraints and safety concerns. In fact, the question does not have a definite answer, but it is unquestionable that a SB-based technology must be easy and safe to operate.

Another, less critical, question raises from the discussion above. Which water should we use for preparing a fresh SB solution? Actually, we cannot answer the question from the point of view of the performance. There are only two studies dealing with the nature of water. This fact reflects how the aspects other than catalysts or accelerators have been little investigated or neglected. In any case, tap water or seawater for example would be preferable, at least because they are cheaper and more accessible than distilled water. More

studies on water quality (including also rainwater, bottled water, etc.) could lead to a better understanding of the impact of the species present in water on the overall performance of the hydrolysis reaction and of the catalyst. We however have to keep in mind that any species in water will complicate the already complex issue related to recycling of the hydrolysis by-product.

The articles dealing with prototypes represent a mine of information. Three types of issues can be identified. The first type of issues are those that have been identified a long time ago: need of active cooling of the system because of the exothermic nature of the hydrolysis reaction; deactivation of the catalyst requiring its reactivation or replacement; and, precipitation of the by-product resulting in clogging the system and/or requiring water flushing after each operation. Each of these issues have to be well managed, otherwise they have a greater or lesser impact on the system as a whole (including the PEMFC). It should be noted that, though these issues are known, they remain unexplored for a use of SB at the kilogram scale. The second type of issues was less known and documented: need of reactor pressurization for constant H<sub>2</sub> production rates; leakage of H<sub>2</sub>; and, risk of corrosion of stainless steel implying coating with inert material. All of these issues are related to the system and on its operation, and further development should allow further improvements. The third type of issues is typical of a specific type of reactor (e.g. gumming of SB) or of a specific application (e.g. risk of disrupting the aircraft center of gravity because of depletion of the tank containing the SB fuel). Other issues will obviously pop up as new prototypes will be constructed, tested and presented. Thus, the only conclusion to be drawn from this is that, we must expand our efforts to address each of these issues.

Even now SB is very often presented as being technologically much promising thanks to the 10.8 wt% of hydrogen atoms of which it is formed. This is both true and untrue. SB has indeed a gravimetric hydrogen density of 10.8 wt%, however this is far from the net gravimetric hydrogen storage capacities that could be reached with a H<sub>2</sub> production system integrated to a fuel cell-powered device. Net gravimetric hydrogen storage capacity takes into account the weight of each component of the system taken as whole and that of SB and water, and only a net value can give the real performance of the couple SB-water as hydrogen carriers. The only measure available is 1.3 wt% as discussed in section 4, and this illustrates how low is the net capacity in comparison to the gravimetric hydrogen density of SB. There is still room for improvement because there are few levers. For example, every

components of a H<sub>2</sub> production system (e.g. reactor) may be lightened by exploring and using light materials instead of heavy ones (e.g. steel). Further optimization with respect to the hydrolysis reaction may allow using an aqueous solution of highly concentrated SB; in doing so, less water would be embarked, positively affecting the net capacity. A last example is of using SB in solid state as the energy density of a H<sub>2</sub> production system using solid SB would be 1.3 times higher than a system using an aqueous alkaline solution of SB. In any case, we have to keep in mind the following values: SB and four equivalents of water have a gravimetric hydrogen density of 7.3 wt%; for a system where the weights of SB and water (both embarked) represent 50% of the system weight, the highest gravimetric hydrogen storage capacity would be about 3.7 wt%; and, for a system where the weights of SB and water is 31% (as in [Figure 7](#)), the highest capacity would be 2.3 wt%.

Last but not least, SB must be produced back from its by-products. Since 2015, significant progress has been made. It is now possible to produce SB by ball milling NaB(OH)<sub>4</sub> and MgH<sub>2</sub> at room temperature, and one of the highest yield reported so far is 90%. This presupposes that half of an initial amount of SB would not be 'lost' after 7 regeneration cycles. Improvement is thus still necessary, and the yield of 100% should be the target. We could also take inspiration from what is being done with electrochemical conversion of CO<sub>2</sub> in order to explore other possibilities. Improvement is all the more necessary in that the cost of H<sub>2</sub> from SB is still too high. With relation to that, another noteworthy observation is that energy, exergy and economic analyses are needed to better evaluate the overall cost of H<sub>2</sub> from SB.

After more than 20 years of research and innovation, many obstacles (as listed above) remain to be overcome before hydrolysis of SB can be a commercial solution for carrying and producing H<sub>2</sub>. In my view, our aim should be to answer the following question: does SB really offer prospects in terms of technological implementation and commercial deployment? We do not have the insight necessary to answer this question yet. But we have to answer it. To do so, we should overcome the obstacles at first, which means more efforts dedicated to construct, operate and optimize H<sub>2</sub> production systems, as well as more efforts to make production of SB from its by-product more efficient and cheaper. That is the only way to reach technological maturity. Next, other questions about the technology deployment will come (how will SB be distributed, how will SB be stored at the end user's home, how will the by-products be stored at home, how will the by-products will be recovered, how many

recycling sites will be available, what will be the transportation and distribution cost, and so forth?).



## References

- [1] Schlesinger HI, Brown HC, Finholt AE. The preparation of sodium borohydride by the high temperature reaction of sodium hydride with borate esters. *J Am Chem Soc* 1953;75:205-9. <https://doi.org/10.1021/ja01097a054>
- [2] Schlesinger HI, Brown HC, Finholt AE, Gilbreath JR, Hoekstra HR, Hyde EK. Sodium borohydride, its hydrolysis and its use as a reducing agent and in the generation of hydrogen. *J Am Chem Soc* 1953;75:215-9. <https://doi.org/10.1021/ja01097a057>
- [3] Fakioglu E, Yürüm Y, Veziroglu TN. A review of hydrogen storage systems based on boron and its compounds. *Int J Hydrogen Energy* 2004;29:1371-6. <https://doi.org/10.1016/j.ijhydene.2003.12.010>
- [4] Amendola SC, Sharp-Goldman SL, Janjua MS, Spencer NC, Kelly MT, Petillo PJ, Binder M. A safe, portable, hydrogen gas generator using aqueous borohydride solution and Ru catalyst. *Int J Hydrogen Energy* 2000;25:969-75. [https://doi.org/10.1016/S0360-3199\(00\)00021-5](https://doi.org/10.1016/S0360-3199(00)00021-5)
- [5] Energy.gov. Development of an advanced chemical hydrogen storage and generation system, <https://www.osti.gov/servlets/purl/1344385/>; 2017 [accessed 19 September 2022]. <https://doi.org/10.2172/1344385>
- [6] National Renewable Energy Laboratory. Go/no-go recommendation for sodium borohydride for on-board vehicular hydrogen storage, <https://www.nrel.gov/docs/gen/fy08/42220.pdf>; 2007 [accessed 19 September 2022].
- [7] Brack P, Dann SE, Wijayanthja KG. Heterogeneous and homogenous catalysts for hydrogen generation by hydrolysis of aqueous sodium borohydride (NaBH<sub>4</sub>) solutions. *Energy Sci Eng* 2015;3:174-88. <https://doi.org/10.1002/ese3.67>
- [8] Patel N, Miotello A. Progress in Co-B related catalyst for hydrogen production by hydrolysis of boron-hydrides: A review and the perspectives to substitute noble metals. *Int J Hydrogen Energy* 2015;40:1429-64. <https://doi.org/10.1016/j.ijhydene.2014.11.052>
- [9] Sun H, Meng J, Joai L, Cheng F, Chen J. A review of transition-metal boride/phosphide-based materials for catalytic hydrogen generation from hydrolysis of boron-hydrides. *Inorg Chem Front* 2018;5:760-72. <https://doi.org/10.1039/C8QI00044A>
- [10] Demirci UB. Sodium borohydride for the near-future energy: a "rough diamond" for Turkey. *Turk J Chem* 2018;42:193-220. <https://doi.org/10.3906/kim-1712-6>

- [11] Wang C, Wang Q, Fu F, Astruc D. Hydrogen generation upon nanocatalyzed hydrolysis of hydrogen-rich boron derivatives: Recent developments. *Acc Chem Res* 2020;53:2783-93. <https://doi.org/10.1021/acs.accounts.0c00525>
- [12] Simagina VI, Ozerova AM, Komova OV, Netskina OV. Recent advances in applications of Co-B catalysts in NaBH<sub>4</sub>-based portable hydrogen generators. *catalysts* 2021;11:268. <https://doi.org/10.3390/catal11020268>
- [13] Abdelhamiud HN. A review on hydrogen generation from the hydrolysis of sodium borohydride. *Int J Hydrogen Energy* 2021;46:726-65. <https://doi.org/10.1016/j.ijhydene.2020.09.186>
- [14] Dragan M. Hydrogen storage in complex metal hydrides NaBH<sub>4</sub>: Hydrolysis reaction and experimental strategies. *Catalysts* 2022;12:356. <https://doi.org/10.3390/catal12040356>
- [15] Sun QM, Wang N, Xu Q, Yu JH. Nanopore-supported metal nanocatalysts for efficient hydrogen generation from liquid-phase chemical hydrogen storage materials. *Adv Mater* 2020;32:2001818. <https://doi.org/10.1002/adma.202001818>
- [16] Yao QL, Ding YY, Lu ZH. Noble-metal-free nanocatalysts for hydrogen generation from boron- and nitrogen-based hydrides. *Inorg Chem Front* 2020;7:3837-74. <https://doi.org/10.1039/D0QI00766H>
- [17] Wang Y, Hu Z, Chen WH, Wu SW, Li GD, Chou SL. Non-noble metal-based catalysts applied to hydrogen evolution from hydrolysis of boron hydrides. *Small Structures* 2021;2:2000135. <https://doi.org/10.1002/ssstr.202000135>
- [18] Demirci UB. The hydrogen cycle with the hydrolysis of sodium borohydride: A statistical approach for highlighting the scientific/technical issues to prioritize in the field. *Int J Hydrogen Energy* 2015;40:2673-91. <https://doi.org/10.1016/j.ijhydene.2014.12.067>
- [19] Goksu H. Recyclable aluminium oxy-hydroxide supported Pd nanoparticles for selective hydrogenation of nitro compounds via sodium borohydride hydrolysis. *New J Chem* 2015;39:8498-504. <https://doi.org/10.1039/C5NJ01492A>
- [20] Nabid MR, Bide Y, Habibi Z. Synthesis of a yolk/shell Fe<sub>3</sub>O<sub>4</sub>@poly(ionic liquid)s-derived nitrogen doped graphitic porous carbon materials and its application as support for nickel catalysts. *RSC Adv* 2015;5:2258-65. <https://doi.org/10.1039/C4RA10374B>

- [21] Wu XQ, Wu XW, Huang Q, Shen JS, Zhang HW. In situ synthesized gold nanoparticles in hydrogels for catalytic reduction of nitroaromatic compounds. *Appl Surf Sci* 2015;331:210-8. <https://doi.org/10.1016/j.apsusc.2015.01.077>
- [22] Krishna R, Fernandes DM, Dias C, Ventura J, Ramana EV, Freire C, Titus E. Novel synthesis of Ag@Co/RGO nanocomposite and its high catalytic activity towards hydrogenation of 4-nitrophenol to 4-aminophenol. *Int J Hydrogen Energy* 2015;40:4996-5005. <https://doi.org/10.1016/j.ijhydene.2014.12.045>
- [23] Gao J, Xu J, Wen SX, Hu J, Liu HL. Plasma-assisted synthesis of Ag nanoparticles immobilized in mesoporous cellular foams and their catalytic properties for 4-nitrophenol reduction. *Microp Mesop Mater* 2015;207:149-55. <https://doi.org/10.1016/j.micromeso.2015.01.025>
- [24] Xu D, Diao P, Jun T, Wu QY, Liu XF, Guo X, Gong HY, Li F, Xiang M, Yu RH. Iridium oxide nanoparticles and iridium/iridium oxide nanocomposites: Photochemical fabrication and application in catalytic reduction of 4-nitrophenol. *ACS Appl Mater Interfaces* 2015;7:16738-79. <https://doi.org/10.1021/acsami.5b04504>
- [25] Fedorczyk A, Ratajczak J, Kuzmych O, Skompska M. Kinetic studies of catalytic reduction of 4-nitrophenol with NaBH<sub>4</sub> by means of Au nanoparticles dispersed in a conducting polymer matrix. *J Solid State Electrochem* 2015;19:2849-58. <https://doi.org/10.1007/s10008-015-2933-5>
- [26] Xie W, Grzeschik R, Schlucker S. Metal nanoparticle-catalyzed reduction Using borohydride in aqueous media: A kinetic analysis of the surface reaction by microfluidic SERS. *Angew Chem Int Ed* 2016;55:13279-33. <https://doi.org/10.1002/anie.201605776>
- [27] Mogudi BM, Ncube P, Meijboom R. Catalytic activity of mesoporous cobalt oxides with controlled porosity and crystallite sizes: Evaluation using the reduction of 4-nitrophenol. *Appl Catal B: Environ* 2016;198:74-82. <https://doi.org/10.1016/j.apcatb.2016.05.051>
- [28] Zhang YF, Xia Y, Yan SS, Han J, Chen YF, Zhai WZ, Gao ZN. One-step green synthesis of composition-tunable Pt-Cu alloy nanowire networks with high catalytic activity for 4-nitrophenol reduction. *Dalton Trans* 2018;47:17461-8. <https://doi.org/10.1039/C8DT03810D>
- [29] Cerimedo MSA, Baronio LG, Hoppe CE, Ayude MA. The effect of poly(vinylpyrrolidone) (PVP) on the Au catalyzed reduction of p-nitrophenol: The

fundamental role of  $\text{NaBH}_4$ . *ChemSelect* 2019;4:608-16.  
<https://doi.org/10.1002/slct.201803250>

- [30] Wang ZM, Huang Y, Lv DC, Jiang GC, Zhang FJ, Song AD. Tea polyphenol-assisted green synthesis of Ag-nanodiamond hybrid and its catalytic activity towards 4-nitrophenol reduction. *Green Chem Lett Rev* 2019 ;12:197-207.  
<https://doi.org/10.1080/17518253.2019.1624836>
- [31] Zoltowska S, Modelska M, Piasecki A, Jesionowski T. Commercial sponges in heterogeneous catalysis: developing novel composites with cobalt and silver. *Physicochem Probl Miner Process* 2020;56:89-100.  
<https://doi.org/10.37190/ppmp/126866>
- [32] Grzeschik R, Schafer D, Holtum T, Kupper S, Hoffmann A, Schlucker S. On the overlooked critical role of the pH value on the kinetics of the 4-nitrophenol  $\text{NaBH}_4$ -reduction catalyzed by noble-metal nanoparticles (Pt, Pd, and Au). *J Phys Chem C* 2020;124:2939-44. <https://doi.org/10.1021/acs.jpcc.9b07114>
- [33] Bravo MV, Silva OF, Adam C, Granados AM. A simple way to prepare palladium nanoparticles decorated with cyclodextrins and ionic liquid. The effects of coating on the catalytic activity and colloidal stability. *J Mol Liq* 2020;304:112725.  
<https://doi.org/10.1016/j.molliq.2020.112725>
- [34] Ayad AI, Luat D, Dris AO, Guenin E. Kinetic analysis of 4-nitrophenol reduction by water-soluble palladium nanoparticles. *Nanomaterials* 2020;10:1169.  
<https://doi.org/10.3390/nano10061169>
- [35] Chen Q, Jiang WD, Fan GY. Pt nanoparticles on  $\text{Ti}_3\text{C}_2\text{T}_x$ -based MXenes as efficient catalysts for the selective hydrogenation of nitroaromatic compounds to amines. *Dalton Trans* 2020;49:14914-20. <https://doi.org/10.1039/D0DT02594A>
- [36] Kassem AA, Abdelhamid HN, Fouad DM, Ibrahim SA. Catalytic reduction of 4-nitrophenol using copper terephthalate frameworks and  $\text{CuO@C}$  composite. *J Environ Chem Eng* 2021;9:104401. <https://doi.org/10.1016/j.jece.2020.104401>
- [37] Shan BQ, Zhou JF, Ding M, Hu XD, Zhang K. Surface electronic states mediate concerted electron and proton transfer at metal nanoscale interfaces for catalytic hydride reduction of  $-\text{NO}_2$  to  $-\text{NH}_2$ . *Phys Chem Chem Phys* 2021;23:12950-7.  
<https://doi.org/10.1039/D1CP01792F>
- [38] Choi S, Jeong Y, Yu J. Spontaneous hydrolysis of borohydride required before its catalytic activation by metal nanoparticles. *Catal Commun* 2016;84:80-4.  
<http://dx.doi.org/10.1016/j.catcom.2016.06.008>

- [39] Kara BY, Kilbas B, Goksu H. Selectivity and activity in catalytic hydrogenation of azido groups over Pd nanoparticles on aluminum oxy-hydroxide. *New J Chem* 2016;40:9550-5. <https://doi.org/10.1039/C6NJ01925K>
- [40] Kilbas B, Yilmaz YE, Ergen S. A practical and highly efficient transfer hydrogenation of aryl azides using a [Ru(p-cymene)Cl<sub>2</sub>]<sub>2</sub> catalyst and sodium borohydride. *CR Chim* 2018;21:880-3. <https://doi.org/10.1016/j.crci.2018.07.004>
- [41] Sun B, Carnevale D, Suss-Fink G. Selective N-cycle hydrogenation of quinolines with sodium borohydride in aqueous media catalyzed by hectorite-supported ruthenium nanoparticles. *J Organomet Chem* 2016;821:197-205. <https://doi.org/10.1016/j.jorganchem.2016.07.010>
- [42] Grice KA, Groenenboom MC, Manuel JDA, Sovereign MA, Keith JA. Examining the selectivity of borohydride for carbon dioxide and bicarbonate reduction in protic conditions. *Fuel* 2015;150:139-45. <https://doi.org/10.1016/j.fuel.2015.02.007>
- [43] Lin KYA, Che SY. Bromate reduction in water by catalytic hydrogenation using metal-organic frameworks and sodium borohydride. *RSC Adv* 2015;5:43885-96. <https://doi.org/10.1039/C5RA05705A>
- [44] Lin KYA, Che SY. Catalytic reduction of bromate using ZIF-derived nanoscale cobalt/carbon cages in the presence of sodium borohydride. *ACS Sustain Chem Eng* 2015;3:3096-103. <https://doi.org/10.1021/acssuschemeng.5b00570>
- [45] Nurlan N, Akmanova A, Han S, Lee W. Enhanced reduction of aqueous bromate by catalytic hydrogenation using the Ni-based Metal-organic framework Ni(4,4'-bipy)(1,3,5-BTC) with NaBH<sub>4</sub>. *Chem Eng J* 2021;414:128860. <https://doi.org/10.1016/j.cej.2021.128860>
- [46] Tuan DD, Yang HT, Huy NN, Kwon E, Khiem TC, You SM, Lee J, Lin KYA. Enhanced reduction of bromate in water by 2-dimensional porous Co<sub>3</sub>O<sub>4</sub> via catalytic hydrogenation. *J Environ Chem Eng* 2021;9:105809. <https://doi.org/10.1016/j.jece.2021.105809>
- [47] Liu Q, Xu MJ, Li F, Wu T, Li YJ. Rapid and effective removal of Cr(VI) from aqueous solutions using the FeCl<sub>3</sub>/NaBH<sub>4</sub> system. *Chem Eng J* 2016;296:340-8. <https://doi.org/10.1016/j.cej.2016.03.127>
- [48] Zhao SX, Chen ZL, Shen JM, Qu YF, Wang BY, Wang X. Enhanced Cr(VI) removal based on reduction-coagulation-precipitation by NaBH<sub>4</sub> combined with fly ash leachate as a catalyst. *Chem Eng J* 2017;322:646-56. <https://doi.org/10.1016/j.cej.2017.04.057>

- [49] Zhao SX, Zhang JN, Chen ZL, Tong YB, Shen JM, Li DM, Zhang MW. Hydrogen generation and simultaneous removal of Cr(VI) by hydrolysis of NaBH<sub>4</sub> using Fe-Al-Si composite as accelerator. *Chemosphere* 2019;223:131-9. <https://doi.org/10.1016/j.chemosphere.2019.02.050>
- [50] Njoya O, Zhao SX, Qu YF, Shen JM, Wang BY, Shi HY, Chen ZL. Performance and potential mechanism of Cr(VI) reduction and subsequent Cr(III) precipitation using sodium borohydride driven by oxalate. *J Environ Manag* 2020;275:111165. <https://doi.org/10.1016/j.jenvman.2020.111165>
- [51] Sahiner N, Yildiz S, Al-Lohedan H. The resourcefulness of p(4-VP) cryogels as template for in situ nanoparticle preparation of various metals and their use in H<sub>2</sub> production, nitro compound reduction and dye degradation. *Appl. Catal. B: Environ.* 2015;166-167:145-54. <https://doi.org/10.1016/j.apcatb.2014.11.027>
- [52] Tripathy T, Kolya H, Jana S, Senapati M. Green synthesis of Ag-Au bimetallic nanocomposites using a biodegradable synthetic graft copolymer; hydroxyethyl starch-g-poly (acrylamide-co-acrylic acid) and evaluation of their catalytic activities. *Europ Polym J* 2017;87:113-23. <https://doi.org/10.1016/j.eurpolymj.2016.12.019>
- [53] Ahmad S, Asiri AM, Kamal T, Khan SB. Efficient reduction of organic pollutants and H<sub>2</sub> generation using bimetallic nanoparticles coated alginate hydrogel beads. *Microp Mesop Mater* 2022;31:112065. <https://doi.org/10.1016/j.micromeso.2022.112065>
- [54] Peinado S, Mateo S, Sanchez S, Moya AJ. Effectiveness of sodium borohydride treatment on acid hydrolyzates from olive-tree pruning biomass for bioethanol production. *Bioenerg Res* 2019;12:302-11. <https://doi.org/10.1007/s12155-019-09979-4>
- [55] Joshi MK, Pant HR, Tiwari AP, Kim HJ, Park CH, Kim CS. Multi-layered macroporous three-dimensional nanofibrous scaffold via a novel gas foaming technique. *Chem Eng J* 2015;275:79-88. <https://doi.org/10.1016/j.cej.2015.03.121>
- [56] Ozerova AM, Komova OV, Mukha SA, Simagina VI, Odegova GV, Arzumanov SS, Bulavchenko OA, Netskina OV. An improved purification of NaBH<sub>4</sub> from storage induced impurities by ammonia assisted crystallization in diglyme. *Int J Hydrogen Energy* 2020;45:30756-66. <https://doi.org/10.1016/j.ijhydene.2020.08.071>
- [57] Zhou Y, Yoshida K, Yamaguchi T, Liu H, Fang C, Fang Y. Microhydration of BH<sub>4</sub><sup>-</sup>: Dihydrogen bonds, structure, stability, and Raman spectra. *J Phys Chem A* 2017;121:9146-55. <https://doi.org/10.1021/acs.jpca.7b09703>

- [58] Zhou Y, Fang C, Fang Y, Zhu F, Liu H, Ge H. Hydrogen generation mechanism of  $\text{BH}_4^-$  spontaneous hydrolysis: A sight from *ab initio* calculation. *Int J Hydrogen Energy* 2016;41:22668-76. <http://dx.doi.org/10.1016/j.ijhydene.2016.10.057>
- [59] Sermiagin A, Meyerstein D, Rolly GS, Mondal T, Kornweitz H, Zidki T. Mechanistic implications of the solvent kinetic isotope effect in the hydrolysis of  $\text{NaBH}_4$ . *Int J Hydrogen Energy* 2022;47:3972-9. <https://doi.org/10.1016/j.ijhydene.2021.11.040>
- [60] Petit E, Salles F, Alligier D, Demirci UB. Hydrolysis of the borohydride anion  $\text{BH}_4^-$ : A  $^{11}\text{B}$  NMR study showing the formation of short-living reaction intermediates including  $\text{BH}_3\text{OH}^-$ . *Molecules* 2022;27:1975. <https://doi.org/10.3390/molecules27061975>
- [61] Zyubin AS, Zyubina TS, Kravchenko OV, Solov'ev MV, Dobrovol'skii YuA. Quantum-chemical modeling of dehydrogenation of a sodium borohydride molecule in water. *Russ J Inorg Chem* 2016;61:731-9. <http://dx.doi.org/10.1134/S0036023616060231>
- [62] Budroni MA, Garroni S, Mulas G, Rustici M. Bursting dynamics in molecular hydrogen generation via sodium borohydride hydrolysis. *J Phys Chem C* 2017;121:4891-8. <http://dx.doi.org/10.1021/acs.jpcc.6b12797>
- [63] Netskina OV, Komova OV, Mukha SA, Simagina VI. Aqueous-alkaline  $\text{NaBH}_4$  solutions: The influence of hydride decomposition on catalytic properties of  $\text{Co}_3\text{O}_4$ . *Catal Commun* 2016;85:9-12. <http://dx.doi.org/10.1016/j.catcom.2016.07.004>
- [64] Netskina OV, Komova OV, Simagina VI, Odegova GV, Prosvirin IP, Bulavchenko OA. Aqueous-alkaline  $\text{NaBH}_4$  solution: The influence of storage duration of solutions on reduction and activity of cobalt catalysts. *Renew Energy* 2016;99:1073-81. <http://dx.doi.org/10.1016/j.renene.2016.08.005>
- [65] Alligier D, Petit E, Demirci UB. A boron-11 NMR study of the stability of the alkaline aqueous solution of sodium borohydride that is both an indirect fuel and a direct fuel for low-temperature fuel cells. *Int J Hydrogen Energy* 2022;47:23310-5. <https://doi.org/10.1016/j.ijhydene.2022.05.119>
- [66] Mosier-Boss PA, Becker CA, Anderson GW, Wiedemeier BJ. Feasibility studies of the  $\text{NaBH}_4/\text{H}_2\text{O}$  hydrolysis to generate hydrogen gas to inflate lighter than air (LTA) vehicles. *Ind Eng Chem Res* 2015;54:7706-14. <http://dx.doi.org/10.1021/acs.iecr.5b01647>
- [67] Oh S, Yoo D, Kim T, Kim I, Part KP. Generation of hydrogen from hydrolysis reaction of  $\text{NaBH}_4$  using fresh water. *Korean Chem Eng Res* 2021;59:503-7. <https://doi.org/10.9713/kcer.2021.59.4.503>



- [68] Lee HR, Prk DH, Ju W, Na IC, Park KP. Characteristics of byproduct after  $\text{NaBH}_4$  hydrolysis reaction using unsupported catalyst. *Korean Chem Eng Res* 2017;55:13-8. <https://doi.org/10.9713/kcer.2017.55.1.13>
- [69] Vilarinho-Franco T, Chiriac R, Tenu R, Counioux JJ, Delmas J, Capron P, Goutaudier C. Polythermal diagrams of aqueous boundary ternary systems involving sodium borohydride hydrolysis for hydrogen generation. *Fluid Phase Equil* 2018;460:189-97. <https://doi.org/10.1016/j.fluid.2017.12.014>
- [70] Schubert D, Neiner D, Bowden M, Whittemore S, Holladay J, Huang Z, Autrey T. Capacity enhancement of aqueous borohydride fuels for hydrogen storage in liquids. *J Alloys Compd* 2015;645:5196-9. <http://dx.doi.org/10.1016/j.jallcom.2015.01.063>
- [71] Petit E, Demirci UB, Miele P. By-product carrying humidified hydrogen: An underestimated issue in the hydrolysis of sodium borohydride. *Chem Sus Chem* 2016;9:1777-80. <https://doi.org/10.1002/cssc.201600425>
- [72] Kuliyeve S, Fettah S, Timurkutluk B. Purity investigation of hydrogen produced by hydrolysis of sodium borohydride via phosphoric acid process. *Chem Prob* 2017;2:136-45.
- [73] Paladini M, Arzac GM, Godinho V, Hufschmidt D, Jimenez de Haro MC, Beltran AM, Fernandez A. The role of cobalt hydroxide in deactivation of thin film Co-based catalysts for sodium borohydride hydrolysis. *Appl Catal B: Environ* 2017;210:342-51. <http://dx.doi.org/10.1016/j.apcatb.2017.04.005>
- [74] Singh VV, Soto F, Kaufmann K, Wang J. Micromotor-based energy generation. *Angew Chem Int Ed* 2015;54:6896-9. <https://doi.org/10.1002/anie.201501971>
- [75] Oh TH, Gang BG, Kim H, Kwon S. Sodium borohydride hydrogen generator using Co-P/Ni foam catalysts for 200 W proton exchange membrane fuel cell system. *Energy* 2015;90:1163-70. <http://dx.doi.org/10.1016/j.energy.2015.06.055>
- [76] Gang BG, Jung W, Kwon S. Transient behavior of proton exchange membrane fuel cells over a cobalt-phosphorous/nickel foam catalyst with sodium borohydride. *Int J Hydrogen Energy* 2016;41:524-33. <http://dx.doi.org/10.1016/j.ijhydene.2015.11.064>
- [77] Kim H, Oh TH, Kwon S. Simple catalyst bed sizing of a  $\text{NaBH}_4$  hydrogen generator with fast startup for small unmanned aerial vehicles. *Int J Hydrogen Energy* 2016;41:1018-26. <http://dx.doi.org/10.1016/j.ijhydene.2015.11.134>
- [78] Jung ES, Kim H, Kwon S, Oh TH. Fuel cell system with sodium borohydride hydrogen generator for small unmanned aerial vehicles. *Int J Green Energy* 2018;15:385-92. <https://doi.org/10.1080/15435075.2018.1464924>



- [79] Lee YJ, Badakhsh A, Min D, Jo YS, Sohn H, Yoon CW, Jeong H, Kim Y, Kim KB, Nam SW. Development of 3D open-cell structured Co-Ni catalysts by pulsed electrodeposition for hydrolysis of sodium borohydride. *Appl Surf Sci* 2021;554:149530.
- [80] Lee YJ, Lee YS, Shin HA, Jo YS, Jeong H, Sohn H, Yoon CW, Kim Y, Kim KB, Nam SW. Surface area enhancement of nickel foam by low-temperature chemical alloying/dealloying and its application for sodium borohydride hydrolysis. *J Alloys Compd* 2020;843:155759. <https://doi.org/10.1016/j.jallcom.2020.155759>
- [81] Marchionni A, Bevilacqua M, Filippi J, Folliero MG, Innocenti M, Lavacchi A, Miller HA, Pagliaro MV, Vizza F. High volume hydrogen production from the hydrolysis of sodium borohydride using a cobalt catalyst supported on a honeycomb matrix. *J Power Sources* 2015;299:391-7. <http://dx.doi.org/10.1016/j.jpowsour.2015.09.006>
- [82] Dai P, Zhao X, Xu D, Wang C, Tao X, Liu X, Gao J. Preparation, characterization, and properties of Pt/Al<sub>2</sub>O<sub>3</sub>/cordierite monolith catalyst for hydrogen generation from hydrolysis of sodium borohydride in a flow reactor. *Int J Hydrogen Energy* 2019;44:28463-70. <https://doi.org/10.1016/j.ijhydene.2019.02.013>
- [83] Minkina VG, Kalinin VI, Shabunya SI. Producing hydrogen from sodium borohydride using mesh nickel catalyst. *Theor Found Chem Eng* 2016;50:536-41. <https://doi.org/10.1134/S0040579516040229>
- [84] Serin RB, Abdullayeva N, Sankir M. Dealloyed ruthenium film catalysts for hydrogen generation from chemical hydrides. *Materials* 2017;10:738. <https://doi.org/doi:10.3390/ma10070738>
- [85] Cao X, Zhou J, Zhai Z, Li S, Yuan G, Qin G. Synchronous growth of porous MgO and half-embedded nano-Ru on a Mg plate: A monolithic catalyst for fast hydrogen production. *ACS Sust Chem Eng* 2021;9:3616-23. <https://dx.doi.org/10.1021/acssuschemeng.1c00072>
- [86] Tariq M, Ali M, Li Y, Han J, Ning F, He L, Shen M, Bai C, Jin H, Zhou X. Unraveling the facile reproducible modeled approach for bifunctional catalytic decorated polydopamine coated sponge composite for hydrogen generation. *Int J Energy Res* 2022;46:23615-29. <https://dx.doi.org/10.1002/er.8660>
- [87] Sankir M, Semiz L, Sankir ND. Catalyst free hydrogen generation from directly disulfonated poly (arylene ether sulfone) copolymer membranes. *J Membr Sci* 2015;496:318-24. <http://dx.doi.org/10.1016/j.memsci.2015.07.059>

- [88] Ley MB, Meggouh M, Moury R, Peinecke K, Felderhoff M. Development of hydrogen storage tank systems based on complex metal hydrides. *Materials* 2015;8:5891-921. <http://dx.doi.org/10.3390/ma8095280>
- [89] Demirci UB. About the technological readiness of the H<sub>2</sub> generation by hydrolysis of B(–N)–H compounds. *Energy Technol* 2018;6:470-6. <http://dx.doi.org/10.1002/ente.201700486>
- [90] Türk BE, Sarul MH, Cengelci E, Karadag CI, Boyaci San FG, Kilic M, Okumus E, Yazici S. Integrated process control-power management system design and flight performance tests for fuel cell powered mini-unmanned aerial vehicle. *Energy Technol* 2021;9:2000879. <http://dx.doi.org/10.1002/ente.202000879>
- [91] Jung HS, Jo BJ, Lee JH, Lee HJ, Na IC, Chu CH, Park KP. Hydrogen supply to PEMFC for unmanned aero vehicles using hydrolysis reaction of NaBH<sub>4</sub>. *Korean Chem Eng Res* 2016;54:11-5. <https://doi.org/10.9713/kcer.2016.54.1.11>
- [92] Lee CJ, Kim T. Hydrogen supply system employing direct decomposition of solid-state NaBH<sub>4</sub>. *Int J Hydrogen Energy* 2015;40:2274-82. <http://dx.doi.org/10.1016/j.ijhydene.2014.12.032>
- [93] Kwon SM, Kim MJ, Kang S, Kim T. Development of a high-storage-density hydrogen generator using solid-state NaBH<sub>4</sub> as a hydrogen source for unmanned aerial vehicles. *Appl Energy* 2019;251:113331. <https://doi.org/10.1016/j.apenergy.2019.113331>
- [94] Sim JH, Kim T. Accelerated hydrolysis of solid-state NaBH<sub>4</sub> by injecting NaHCO<sub>3</sub> solution for hydrogen generation. *Appl Energy* 2015;160:999-1006. <http://dx.doi.org/10.1016/j.apenergy.2015.05.012>
- [95] Boran A, Erkan S, Eroglu I. Hydrogen generation from solid state NaBH<sub>4</sub> by using FeCl<sub>3</sub> catalyst for portable proton exchange membrane fuel cell applications. *Int J Hydrogen Energy* 2019;44:18915-26. <https://doi.org/10.1016/j.ijhydene.2018.11.033>
- [96] Kim J, Kim T. Compact PEM fuel cell system combined with all-in-one hydrogen generator using chemical hydride as a hydrogen source. *Appl Energy* 2015;160:945-53. <http://dx.doi.org/10.1016/j.apenergy.2015.03.084>
- [97] Gang BG, Kim H, Kwon S. Ground simulation of a hybrid power strategy using fuel cells and solar cells for high-endurance unmanned aerial vehicles. *Energy* 2017;141:1547-54. <https://doi.org/10.1016/j.energy.2017.11.104>

- [98] Gang BG, Kwon S. All-in-one portable electric power plant using proton exchange membrane fuel cells for mobile applications. *Int J Hydrogen Energy* 2018;43:6331-9. <https://doi.org/10.1016/j.ijhydene.2018.02.006>
- [99] Gang BG, Kwon S. Design of an energy management technique for high endurance unmanned aerial vehicles powered by fuel and solar cell systems. *Int J Hydrogen Energy* 2018;43:9787-96. <https://doi.org/10.1016/j.ijhydene.2018.04.049>
- [100] Lapena-Rey N, Blanco JA, Ferreyra E, Lemus JL, Pereira S, Serrot, A fuel cell powered unmanned aerial vehicle for low altitude surveillance missions, *Int J Hydrogen Energy* 2017;42:6926-40. <https://doi.org/10.1016/j.ijhydene.2017.01.137>
- [101] Li SC, Wang FC. The development of a sodium borohydride hydrogen generation system for proton exchange membrane fuel cell. *Int J Hydrogen Energy* 2016;41:3038-51. <http://dx.doi.org/10.1016/j.ijhydene.2015.12.019>
- [102] Hsu L, Huang M, Anderson G, Rubio A, Kerber M, Putnam M, Phipps A. Evaluation of acid accelerators for an off-grid PEM fuel cell power station utilizing solid sodium borohydride for hydrogen storage. *ECS Trans* 2016;75:515-20. <https://doi.org/10.1149/07514.0515ecst>
- [103] Funakawa R, Fukuzawa T, Tomoda K, Hoshi K, Katayama N, Yoshizaki A, Hirata K. Verification of appropriate temperature range of acid accelerant in hydrogen generation system from  $\text{NaBH}_4$ . *ECS Trans* 2015;71:99-105. <https://doi.org/10.1149/07101.0099ecst>
- [104] Fukuzawa T, Tomoda K, Funakawa R, Hoshi K, Katayama N, Yoshizaki A, Hirata K. Consideration on acid accelerator oriented to reproduction of sodium borohydride from by-product. *ECS Trans* 2016;71:123-9. <https://doi.org/10.1149/07101.0123ecst>
- [105] Avrahami I, Shvalb N, Sasson M, Nagar Y, Dahan O, Dayee I, Schechter A. Hydrogen production on-demand by hydride salt and water two-phase generator. *Int J Hydrogen Energy* 2020;45:15270-80. <https://doi.org/10.1016/j.ijhydene.2020.03.203>
- [106] Zakhvatkin L, Zolotih M, Maurice Y, Schechter A, Avrahami I. Hydrogen production on demand by a pump controlled hydrolysis of granulated sodium borohydride. *Energy Fuels* 2021;35:11507-14. <https://doi.org/10.1021/acs.energyfuels.1c00367>
- [107] Kao HY, Lin CC, Hung CJ, Hu CC. Kinetics of hydrogen generation on  $\text{NaBH}_4$  powders using cobalt catalysts. *J Taiwan Inst Chem Eng* 2018;87:123-30. <https://doi.org/10.1016/j.jtice.2018.03.022>
- [108] Higier A, Hsu L, Oiler J, Phipps A, Hooper D, Kerber M. Polymer electrolyte fuel cell (PEMFC) based power system for long-term operation of leave-in-place sensors in

- Navy and Marine Corps applications. *Int J Hydrogen Energy* 2017;42:4706-9. <http://dx.doi.org/10.1016/j.ijhydene.2016.09.066>
- [109] Minkina VG, Shabunya SI, Kalinin VI, Smirnova A. Hydrogen generation from sodium borohydride solutions for stationary applications. *Int J Hydrogen Energy* 2016;41:9227-33. <http://dx.doi.org/10.1016/j.ijhydene.2016.03.063>
- [110] Li M, Deng H, Zhang Y, Hou C. A small hybrid power system of photovoltaic cell and sodium borohydride hydrolysis-based fuel cell. *Micromachines* 2021;12:278. <https://doi.org/10.3390/mi12030278>
- [111] Jung HS, Oh SJ, Jeong JJ, Na IC, Chu CH, Park KP. Characteristics of Al alloy as a material for hydrolysis reactor of NaBH<sub>4</sub>. *Korean Chem Eng Res* 2015;53:677-81. <http://dx.doi.org/10.9713/kcer.2015.53.6.677>
- [112] Nunes HX, Ferreira MJF, Rangel CM, Pinto AMFR. Hydrogen generation and storage by aqueous sodium borohydride (NaBH<sub>4</sub>) hydrolysis for small portable fuel cells (H<sub>2</sub> - PEMFC). *Int J Hydrogen Energy* 2016;41:15426-32. <http://dx.doi.org/10.1016/j.ijhydene.2016.06.173>
- [113] Tomoda K, Katayama N, Hoshi N, Yoshizaki A, Hirata K. Modeling of sodium tetrahydroborate power system for fuel cell vehicle. *ECS Trans* 2015;65:33-43. <http://dx.doi.org/10.1149/06501.0033ecst>
- [114] Shabunya SI, Kalinin VI, Minkina VG, Martynenko. Modeling of the process of hydrolysis of sodium borohydride in a circulating reactor. *J Eng Phys Thermophys* 2018;91:1617-22. <https://doi.org/10.1007/s10891-018-1900-2>
- [115] Chen YH, Lin JC. Reactant feeding strategy analysis of sodium borohydride hydrolysis reaction systems for instantaneous hydrogen generation. *Energies* 2020;13:4674. <https://doi.org/10.3390/en13184674>
- [116] Jung KM, Choi SH, Lee HJ. Pressure drop and catalytic dehydrogenation of NaBH<sub>4</sub> solution across pin fin structures in a microchannel reactor. *Trans Korean Soc Mech Eng B* 2017;41:381-7. <https://doi.org/10.3795/KSME-B.2017.41.6.381>
- [117] Yao J, Wu Z, Wang H, Yang F, Ren J, Zhang Z. Application-oriented hydrolysis reaction system of solid-state hydrogen storage materials for high energy density target: A review. *J Energy Chem* 2022;74:218-238. <https://doi.org/10.1016/j.jechem.2022.07.009>
- [118] Cakanyildirim C, Guru M. Hydrogen cycle with sodium borohydride. *Int J Hydrogen Energy* 2008;33:4634-9. <https://doi.org/10.1016/j.ijhydene.2008.05.084>

- [119] Tan Y, Yu X. Chemical regeneration of hydrogen storage materials RSC Adv 2013;3:23879-94. <https://doi.org/10.1039/C3RA44103B>
- [120] Liu CH, Chen BH. The concept about the regeneration of spent borohydrides and used catalysts from green electricity. Materials 2015;8:3456-66. <https://doi.org/10.3390/ma8063456>
- [121] Chamoun R, Demirci UB, Miele P. Cyclic dehydrogenation–(re)hydrogenation with hydrogen-storage materials : An overview. Energy Technol 2015;3:100-17. <https://doi.org/10.1002/ente.201402136>
- [122] Nunes HX, Silva DL, Rangel CM, Pinto AMFR. Rehydrogenation of sodium borates to close the  $\text{NaBH}_4\text{-H}_2$  cycle: A review. Energies 2021;14:3567. <https://doi.org/10.3390/en14123567>
- [123] Ouyang L, Zhong H, Li HW, Zhu M. A recycling hydrogen supply system of  $\text{NaBH}_4$  based on a facile regeneration process: A review. Inorganics 2018;6:10. <http://dx.doi.org/10.3390/inorganics6010010>
- [124] Ouyang L, Jiang J, Chen K, Zhu M, Liu Z. hydrogen production via hydrolysis and alcoholysis of light metal-based materials: A review. Nano-Micro Lett 2021;13:134. <https://doi.org/10.1007/s40820-021-00657-9>
- [125] Kantürk Figen A, Piskin S. Parametric investigation on anhydrous sodium metaborate ( $\text{NaBO}_2$ ) synthesis from concentrated tincal. Adv Powder Technol 2010;21:413-520. <https://doi.org/10.1016/j.appt.2010.01.012>
- [126] Chen W, Ouyang LZ, Liu JW, Yao XD, Wang H, Liu ZW, Zhu M. Hydrolysis and regeneration of sodium borohydride ( $\text{NaBH}_4$ ) – A combination of hydrogen production and storage. J Power Sources 2017;359:400-407. <http://dx.doi.org/10.1016/j.jpowsour.2017.05.075>
- [127] Ouyang L, Chen W, Liu J, Felderhoff M, Wang H, Zhu M. Enhancing the regeneration process of consumed  $\text{NaBH}_4$  for hydrogen storage. Adv Energy Mater 2017;1:1700299. <http://dx.doi.org/10.1002/aenm.201700299>
- [128] Zhong H, Ouyang L, Ye JS, Liu JW, Wang H, Yao XD, Zhu M. An one-step approach towards hydrogen production and storage through regeneration of  $\text{NaBH}_4$ . Energy Storage Mater 2017;7:222-8. <http://dx.doi.org/10.1016/j.ensm.2017.03.001>
- [129] Zhong H, Ouyang L, Liu J, Peng C, Zhu X, Zhu W, Fang F, Zhu M. Sodium borohydride regeneration via direct hydrogen transformation of sodium metaborate tetrahydrate. J Power Sources 2018;390:71-7. <https://doi.org/10.1016/j.jpowsour.2018.04.037>

- [130] Huang M, Zhong H, Ouyang L, Peng C, Zhu X, Zhu W, Fang F, Zhu M. Efficient regeneration of sodium borohydride via ball milling dihydrate sodium metaborate with magnesium and magnesium silicide. *J Alloys Compd* 2017;729:1079-85. <https://doi.org/10.1016/j.jallcom.2017.09.262>
- [131] Qin C, Ouyang L, Wang H, Liu J, Shao H, Zhu M. Regulation of high-efficient regeneration of sodium borohydride by magnesium-aluminum alloy. *Int J Hydrogen Energy* 2019;44:29108-15. <https://doi.org/10.1016/j.ijhydene.2019.05.010>
- [132] Zhong H, Ouyang L, Zeng M, Liu J, Wang H, Shao H, Felderhoff M, Zhu M. Realizing facile regeneration of spent NaBH<sub>4</sub> with Mg-Al alloy. *J Mater Chem A* 2019;7:10723-10728. <https://doi.org/10.1039/c9ta00769e>
- [133] Lang C, Jia Y, Liu J, Wang H, Ouyang L, Zhu M, Yao X. NaBH<sub>4</sub> regeneration from NaBO<sub>2</sub> by high-energy ball milling and its plausible mechanism. *Int J Hydrogen Energy* 2017;42:13127-35. <http://dx.doi.org/10.1016/j.ijhydene.2017.04.014>
- [134] Zhu Y, Ouyang L, Zhong H, Liu J, Wang H, Shao H, Huang Z, Zhu M. Closing the loop for hydrogen storage: Facile regeneration of NaBH<sub>4</sub> from its hydrolytic product. *Angew Chem* 2020;132:8701-7. <https://doi.org/10.1002/anie.201915988>
- [135] Zhu Y, Ouyang L, Zhong H, Liu J, Wang H, Shao H, Huang Z, Zhu M. Efficient synthesis of sodium borohydride: Balancing reducing agents with intrinsic hydrogen source in hydrated borax. *ACS Sust Chem Eng* 2020;8:13449-58. <https://dx.doi.org/10.1021/acssuschemeng.0c04354>
- [136] Zhu Y, Zhong H, Ouyang L, Liu J, Wang H, Shao H, Zhu M. Synthesis of NaBH<sub>4</sub> as a hydrogen carrier from hydrated borax using a Mg-Al alloy. *Inorg Chem Front* 2022;9:370-8. <https://dx.doi.org/10.1039/d1qi01247a>
- [137] Zhu Y, Zhong H, Wang H, Ouyang L, Liu J, Huang Z, Zhu M. Breaking the passivation: Sodium borohydride synthesis by reacting hydrated borax with aluminum. *Chem Eur J* 2021;27:9087-93. <https://doi.org/10.1002/chem.202100552>
- [138] Ouyang L, Liu M, Chen K, Liu J, Wang H, Zhu M, Yartys V. Recent progress on hydrogen generation from the hydrolysis of light metals and hydrides. *J Alloys Compd* 2022;910:164831. <https://doi.org/10.1016/j.jallcom.2022.164831>
- [139] Ar I, Güler ÖÜ, Gürü. Synthesis and characterization of sodium borohydride and a novel catalyst for its dehydrogenation. *Int J Hydrogen Energy* 2018;43:20214-33. <https://doi.org/10.1016/j.ijhydene.2018.06.184>

- [140] Nielsen TK, Karkamkar A, Bowden M, Besenbacher F, Jensen TR, Autrey T. Methods to stabilize and destabilize ammonium borohydride. *Dalton Trans* 2013;42:680-7. <https://doi.org/10.1039/C2DT31591B>
- [141] Le TT, Pistidda C, Puszkiel J, Milanese C, Garroni S, Emmeler T, Capurso G, Gizer G, Klassen T, Dornheim M. Efficient synthesis of alkali borohydrides from mechanochemical reduction of borates using magnesium-aluminum-based waste. *Metals* 2019;9:1061. <https://doi.org/10.3390/met9101061>
- [142] Rivarolo M, Improta O, Magistri L, Panizza M, Barbucci A. Thermo-economic analysis of a hydrogen production system by sodium borohydride ( $\text{NaBH}_4$ ). *Int J Hydrogen Energy* 2018;43:1606-14. <https://doi.org/10.1016/j.ijhydene.2017.11.079>